

Agro–Industrial Waste Blends on Mechanical Response of Selected Soils [†]

Imoh Attah ^{1,*}, George Alaneme ², Roland Etim ¹, Ahmad Jagaba ³ and Nimay Giri ^{4,5}

¹ Department of Civil Engineering, Akwa Ibom State University, Ikot Akpaden, Nigeria; email1@email.com (R.E.)

² Department of Civil Engineering, Kampala International University, Kampala, Uganda; email2@email.com (G.A.)

³ Department of Civil Engineering, Abubakar Tafawa Balewa University, Bauchi, Nigeria; email3@email.com (A.J.)

⁴ Department of Electronics and Communication Engineering, Centurion University of Technology and Management, Odisha 752050, India; email4@email.com (N.G.)

⁵ Centre of Renewable Energy and Environment, Centurion University of Technology and Management, Odisha 752050, India

* Correspondence: imohattah@aksu.edu.ng or attahimoh@gmail.com

[†] Presented at the 4th International Electronic Conference on Applied Sciences, 27 October–10 November 2023; Available online: <https://asec2023.sciforum.net/>.

Abstract: Due to urbanization, it is nearly impossible to construct civil infrastructures without encountering soil materials with poor geotechnical response. In soil re-engineering, the trending practise is the use of supplementary cementitious material with the aim to reduce carbon footprint and construction cost. This has necessitated the usability of integrating the blends of palm oil fuel residue (POFR) and calcium carbide powder (CCP) in the amelioration protocols of two soil materials. The amelioration protocols were implemented by inclusion of 0, 2, 4, 6, 8 and 10% dosages of POFR and 0, 2, 4, 6, and 8% dosages of CCP by requisite weight of soil materials. The experimental works were performed in three phases, namely: material characterization, mechanical performance and microstructural testing. Judging from the index performance, black clayey soil (BCS) and reddish lateritic soil (RLS) are clayey materials having plasticity index of 28.70 and 28.80% respectively. Concerning the mechanical performance (compaction, California bearing ratio and durability), the inclusion of the blends of POFR-CCP into the soils (BCS and RLS) activated a positive response and was later validated via means of microstructural tests. This research has shown the potential of blended waste residues in soil re-engineering studies. The study was vividly achieved through a qualitative approach known as scanning electron microscopy and Fourier transform infrared.

Keywords: California bearing ratio; durability; micro-fabric arrangement; sustainable materials

Citation: Attah, I.; Alaneme, G.;

Etim, R.; Jagaba, A.; Giri, N.

Agro–Industrial Waste Blends on

Mechanical Response of Selected

Soils. *Eng. Proc.* **2023**, *52*, x.

<https://doi.org/10.3390/xxxxx>

Academic Editor(s): Name

Published: date



Copyright: © 2023 by the authors.

Submitted for possible open access publication under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Rapid population growth in the rural and urban areas has resulted in the shortage of stable road construction materials, thereby instigating civil engineers to build road infrastructure on soft and unstable soil materials. Soil materials form an integral part of any road pavement and as such they should be of good strength. In the tropical areas such as Nigeria, the predominant soil materials are black cotton soil and reddish lateritic soil materials [1]. In their natural form, they contain a considerable volume of clay minerals which renders the material unfavorable for civil engineering applications. Materials with such behavior beneath road pavements are mostly linked to undesirable foundation difficulties such as loading movements, bearing capacity issues and differential settlement problems [2]. Thus, the technique of substituting the unfavorable soil with borrow to fill material of good geotechnical performance or enhancing the mechanical performance of

the soil is the trending practice by construction experts. The most common amelioration agents known by soil scientists are lime and cement. However, environmental concerns such as the high rate of carbon footprint, global warming, sustainability issues attached to cement production has made soil scientist to question its continuous usage in soil amelioration studies. Thus, the need for utilization of eco-friendly materials such as by-products from industrial and agricultural processes would be a viable sustainable and economic option. Based on a literature search, some by-products of industrial and agricultural processes have displayed good pozzolanic tendency and a good number of scientists have engaged them as cement replacement materials (CRMs) in civil engineering infrastructures [3–7].

However, an enormous amount of experimental work have been performed on the usage of waste residue in civil infrastructures such as the improvement of soil materials. CCP which is a calcium-based industrial waste residue has been proven practicable in soft soil amelioration process with documented positive responses [8]. Chindaprasirt et al. [9] studied the engineering response and evaluation of marginal soil treated with CCP for civil engineering applications. The experimental work shows that the incorporation of CCP instigated the studied soil properties to display positive performance when compared to the unmodified soil. A step further, Akinwumi et al. [10] explored the usability of CCP as an amelioration agent and reported that incorporating CCP diminished the soil's plasticity index, specific gravity, and maximum dry density and resulted in enhancement of the soil's strength behavior. The investigation of Behnood, [11] affirmed that utilizing CCP in combination with other pozzolanic materials ensures a better cementing performance. In the same vein, POFR is a derivative of the burning processes of palm waste and its utilization is gaining momentum in highway applications. It has been explored experimentally as a standalone cement replacement material (CRM) in concrete studies [12]. Furthermore, POFR has magnificently been admixed in conjunction with cement, lime, and high calcium fly ashes for the enhancement of marginal soil's geotechnical performance [13–15]. The use of CCP-POFR mixtures in soil re-engineering is due to their inherent cementitious materials. It may interest one to know that multiple investigations have been done using CCP and POFR either as a standalone stabilizer or combined with other surrogate materials to investigate the strength behavior of soil materials. It is worth noting that the trust of this current manuscript is to unravel the mechanical performance (such as California Bearing Ratio and durability) and microstructural arrangement of two soil materials treated with CCP-POFR. It is believed that this investigation will provide innovative insight into the utilization of CCP-POFR stabilized BCS and RLS soil materials for civil infrastructural construction and it may also proffer solutions of minimizing the impact of waste in society which will in return promote a sustainable environment.

2. Materials and Methods

In this existing study, locally sourced BCS together with RLS, POFR and CCP were utilized as constituent materials and their elemental oxides revealed in Table 1. Using a disturbed sampling strategy, BCS was acquired from its deposit at Deba LGA, Gombe State whereas RLS was collected from its deposit at Mkpatt Enin LGA, Akwa Ibom State.

Methods

Basic geotechnical investigations were performed on the unaltered soil (BCS and RLS). In the course of achieving the compaction response of the studied marginal soil materials, a 2.5 kg rammer and a standard proctor mould were utilized with reference to British standard light principles. For the CBR testing, the guiding principles of British standard light compacting effort were utilized and the test was conducted on the unaltered and typically additives-altered soil samples according to the steps as specified by BS 1377 [16] and BS 1924 [17]. Both the virgin and additives-altered soil samples were

subjected to durability testing also known as resistance to loss in strength based on the guiding principles of BS 1924 [17] and Ola [18].

3. Results

Soil materials BCS and RLS are clayey materials having percentages passing BS no. 200 of approximately 72 and 42.50%, plasticity index of 28.70 and 28.80% and specific gravity of 2.40 and 2.58 respectively. In the course of this study, it was obvious that CCP and POFR had specific gravity of 2.26 and 2.43 respectively. Their specific gravity is parallel with the upshots of [19]. However, the lower specific gravity recorded for CCP might not be far from its powdered form. The CBR values indicates that both soil are unsuitable materials and far from the minimum benchmark for usage as road construction material (NGS) [20], therefore a need for soil amelioration. In summary, the AASHTO [21] classification rates BCS and RLS as A-7-6 (14) and A-7-6 (20), respectively.

Table 1. Elemental compositions of constituent materials used in this manuscript.

Elemental Compositions	Al ₂ O ₃	CaO	FeO ₃	SiO ₂	SO ₃	TiO ₂	MgO	Na ₂ O	K ₂ O	LOI
BCS *	18.60	0.90	2.20	48.50	-	-	2.22	1.55	0.70	10.10
RLS **	22.60	0.45	6	56.70	-	0.75	0.20	-	-	8.50
CCP	1.80	62.10	1.90	2.95	0.76	0.12	-	-	0.96	29.20
POFR	24.10	9.09	5.10	40.15	1.11	0.60	1.22	1.50	7.10	8.80

* [22]; ** [1].

3.1. Maximum Dry Density (MDD) of BCS-CCP-POFR and RLS-CCP-POFR

The MDD of the soil materials (RLS and BCS) was studied by blending the proportions of CCP-POFR as shown in Figure 1. The MDD behaviour of both soil materials dropped by the inclusion of varying CCP-POFR contents compared to the virgin soil materials. The MDD of BCS and RLS dropped from its natural values of 1.615 and 1.825 Mg/m³ to 1.528 and 1.695 Mg/m³ at 8% POFR–8% CCP. The documented decrease in MDD might be attributable to POFR and CCP having low specific gravity of 2.43 and 2.28 compared to BCS and RLS having higher specific gravity of 2.40 and 2.58, respectively [23].

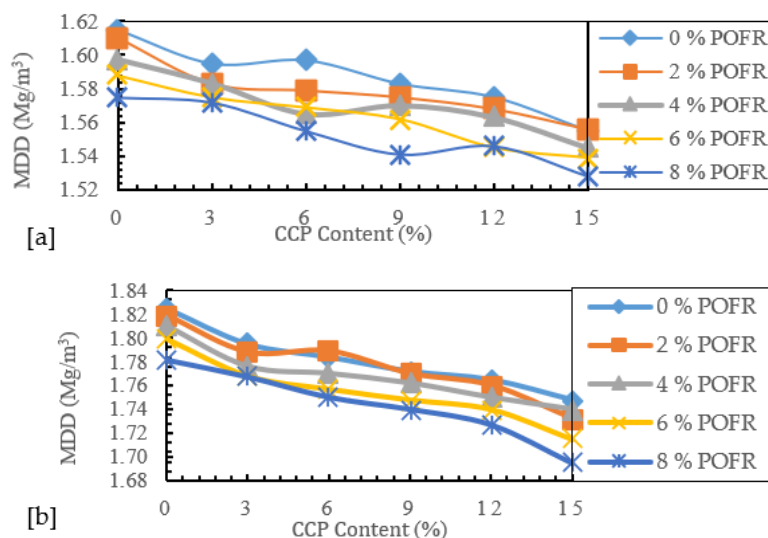


Figure 1. MDD of (a) BCS-CCP-POFR and (b) RLS-CCP-POFR.

3.2. Optimum Moisture Content (OMC) of BCS-CCP-POFR and RLS-CCP-POFR

Figure 2 display the consequence of POFR and CCP on the OMC of BCS and RLS, respectively. The OMC values for mixtures of BCS ranged from 18 to 20.15%, whereas that

of RLS mixtures varied from 13.10 to 15%. These values depict an incremental trend in the course of blending the studied soil materials with POFR and CCP. Probably, the cause of this trend of outcome might not be far from the accumulation of fines as well as the pozzolanic interplay instigated by the additive materials. The response of the studied soil materials aligns with the trend reported by [24].

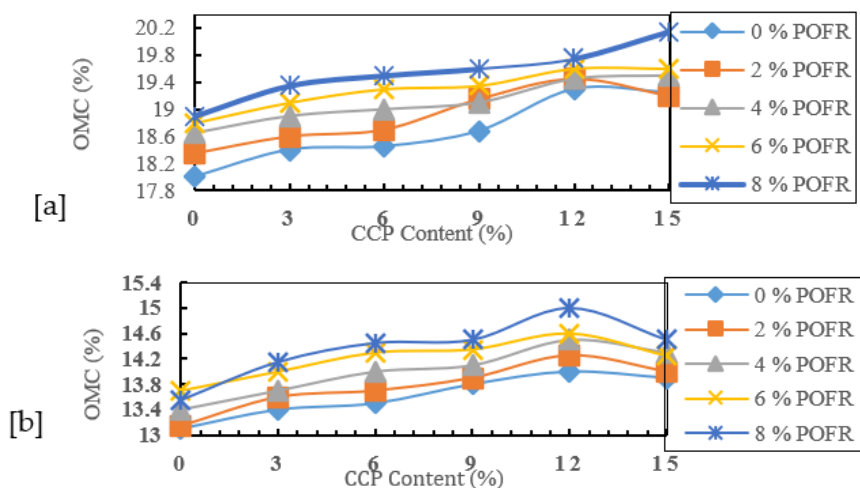


Figure 2. OMC of (a) BCS-CCP-POFR and (b) RLS-CCP-POFR.

3.3. Strength Performance of BCS-CCP-POFR and RLS-CCP-POFR

The upshots of the California bearing ratio (CBR) testing of soil BCS and RLS performed under soaked conditions exhibited a substantial percentage increase as the mixtures of POFR-CCP are being incorporated (see Figure 3). The soil material under study had CBR values of 3 and 6% in their unmodified form and the incorporation of 8% POFR–15% CCP instigated an upsurge of approximately 10 and 6 times of their initial values. Remarkably, the CBR values for both additive blended soil materials revealed an inclination pattern and this could be ascribed to the fact that the finer fractions of POFR and CCP filled up the pores within the soil matrix which thereby engendered a reduction in plasticity and as well altered the soil structure. This phenomenon is similar to the report of other investigators who utilized other additives in soil re-engineering [25].

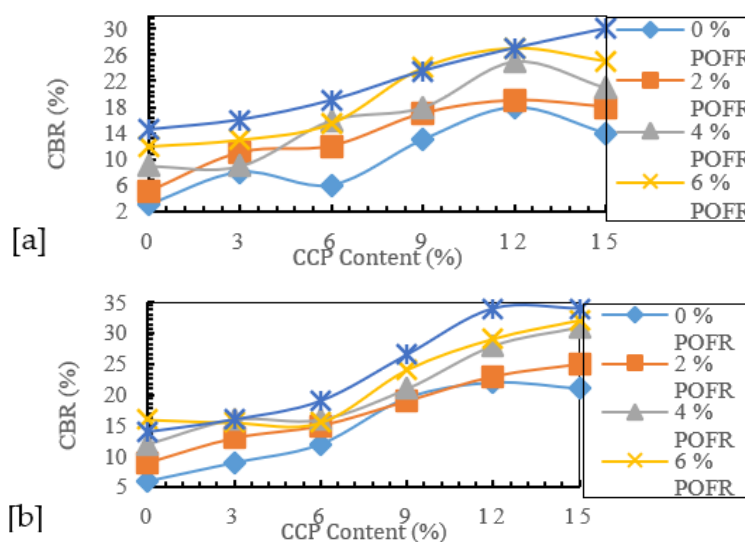


Figure 3. CBR of (a) BCS-CCP-POFR and (b) RLS-CCP-POFR.

3.4. Durability Performance of BCS-CCP-POFR and RLS-CCP-POFR

Figure 4 reveals the durability outcomes of BCS-POFR-CCP and RLS-POFR-CCP, respectively. Generally, the durability response varied between 9 and 39% and 11.5 and 41% for BCS-POFR-CCP and RLS-PPOFR-CCP mixtures. Looking at these values, the incorporation of additive materials instigated some level of alteration in terms of durability response. This alteration might be endorsed by the inter additives reaction building-up bonds and tightening the soil matrix due to pozzolanic interplay. Howbeit, the durability values for RLS-POFR-CCP mixtures were high when compared to those documented for BCS-POFR-CCP mixtures. Judging from the recommendation made by [20], the peak values looked promising. Interestingly this was not expected, it is believed that due to the exposure of soil mixtures for 7 days as against the 4 days soaking duration.

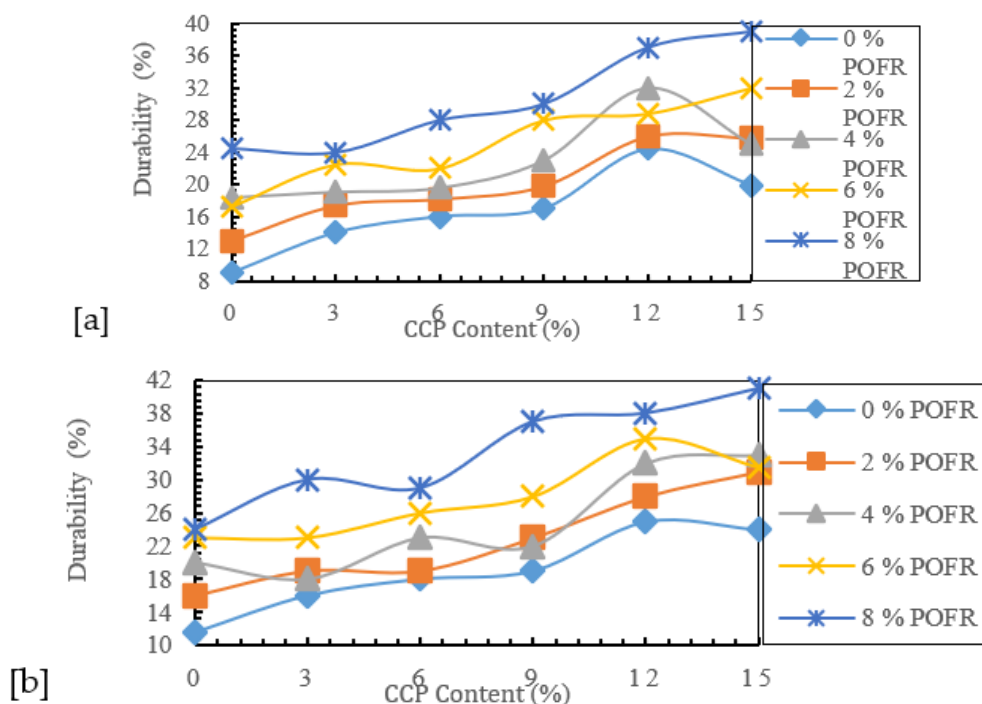


Figure 4. Durability of (a) BCS-CCP-POFR and (b) RLS-CCP-POFR.

3.5. Morphological Performance of BCS-CCP-POFR and RLS-CCP-POFR

The micrographs of the unmodified soil materials were compared with that of the soil materials modified at 8% POFR–15% CCP to unravel the possible alteration within the microstructural fabric of the soil (see Figures 5 and 6). The unmodified BES displayed a good number of dark-coloured cavities whereas the unmodified RLS was made up of few broken grain particles which may possibly be a result of poor linkage performance manifesting in the soil. In the course of incorporating the mixtures of POFR-CCP into the soil materials (BCS and RLS), the morphology was altered (Figures 5b and 6b). The micrograph of both treated soils appears to show the presence of whitish fissures and dense grain structures. The whitish background might be a result of the presence of additive material which might as well translate to strength development in the modified samples. In addition, the dense matrix might be linked with the micro filling of the soil matrix by the additive materials. This report is not at variance with other authors who used other solid wastes [1].

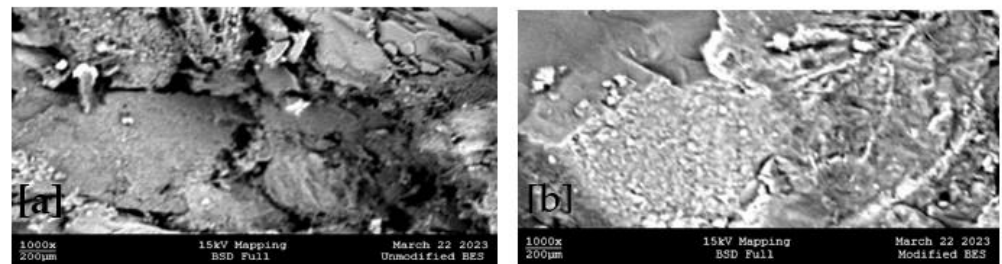


Figure 5. SEM morphology of (a) unmodified BES (b) CCP-POFR modified BES.

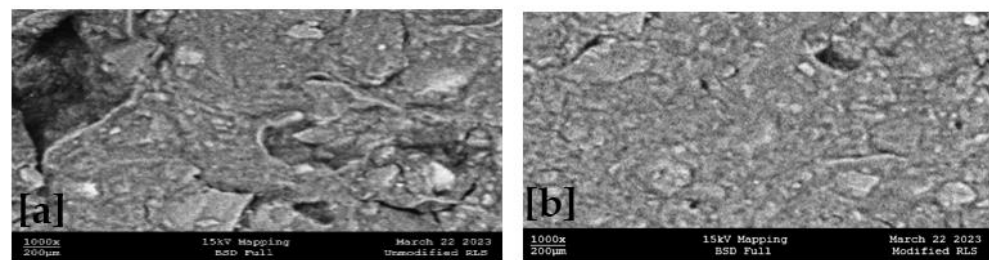


Figure 6. SEM morphology of (a) unmodified RLS (b) CCP-POFR modified RLS.

4. Conclusions

In the course of completing this study on the impact of blending POFR-CCP on the mechanical response of two marginal soils, the following conclusions could be made. Judging from AASHTO, the marginal soil materials (BCS and RLS) in their unmodified form were categorized as A-7-6 (14) and A-7-6 (20) or CH and SC in USCS. For both soil materials, the MDD displayed a downward trend with a corresponding increasing OMC on the incorporation of POFR-CCP blends. In a step further, the highest CBR values of 30 and 34% for BCS and RLS was within the safe limit of 20–30% as stated for sub-base material by the NGS. Additionally, the highest durability performance of the optimally modified soil materials were found to be 39 and 41%, respectively. The micro fabric assessment confirmed that the modified soils had morphological alteration. Finally, it is believed that the additives instigated the presence of new phases such as calcium silicate hydrate and calcium aluminate hydrate in the soil and were alleged to be the major factor of increase in strength.

Author Contributions: Conceptualization, I.A. and G.A.; methodology, I.A.; software, G.A.; validation, I.A., G.A. and R.E.; formal analysis, A.J.; investigation, N.G.; resources, I.A.; data curation, G.A.; writing—original draft preparation, I.A.; writing—review and editing, G.A.; visualization, R.E.; supervision, A.J.; project administration, N.G. All authors have read and agreed to the published version of the manuscript.

Funding: This research received no external funding.

Institutional Review Board Statement:

Informed Consent Statement: Not applicable.

Data Availability Statement: Data generated in this study are included in this article.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Attah, I.C.; Etim, R.K.; Alaneme, G.U.; Ekpo, D.U.; Usanga, I.N. Scheffe's approach for single additive optimization in selected soils amelioration studies for cleaner environment and sustainable subgrade materials. *Clean. Mater.* **2022**, *5*, 100126.
2. Ijaz, N.; Ye, W.; Rehman, Z.; Ijaz, Z.; Faisal, M. New binary paper/wood industry waste blend for solidification/stabilisation of problematic soil subgrade: Macro-micro study. *Road Mater Pavement Des.* **2023**, *24*, 1215–1232.
3. Attah, I.C.; Etim, R.K.; Yohanna, P.; Usanga, I.N. Understanding the effect of compaction energies on the strength indices and durability of oyster shell ash-lateritic soil mixtures for use in road works. *Eng. Appl. Sci. Res.* **2021**, *48*, 151–160. <https://doi.org/10.14456/easr.2021.17>.
4. Dao, P.L.; Bui Van, D.; Onyelowe, K.C.; Ebid, A.M.; Le, V.D.; Ahaneku, I.E. Effect of metakaolin on the mechanical properties of lateritic soil. *Geotech. Res.* **2022**, *9*, 211–218. <https://doi.org/10.1680/jgere.22.00046>.
5. Alaneme, G.U.; Attah, I.C.; Etim, R.K.; Dimonyeka, M.U. Mechanical properties optimization of soil-cement kiln dust mixture using extreme vertex design. *Int. J. Pavement Res. Technol.* **2022**, *15*, 719–750. <https://doi.org/10.1007/s42947-021-00048-8>.
6. Kampala, A.; Horpibulsuk, S. Engineering properties of calcium carbide residue stabilized silty clay. *J. Mater. Civil Eng.* **2013**, *25*, 632–644.
7. Chalee, W.; Cheewaket, T.; Jaturapitakkul, C. Enhanced durability of concrete with palm oil fuel ash in a marine environment. *J Mater Res Technol.* **2021**, *13*, 128–137.
8. Liu, Y.; Chang, C.W.; Namdar, A.; She, Y.; Lin, C.H.; Yuan, X.; Yang, Q. Stabilization of expansive soil using cementing material from rice husk ash and calcium carbide residue. *Constr Build Mater.* **2019**, *221*, 1–11.
9. Chindapasirt, P.; Kampala, A.; Jitsangiam, P.; Horpibulsuk, S. Performance and evaluation of calcium carbide residue stabilized lateritic soil for construction materials. *Case Stud. Constr. Mater.* **2020**, *13*, e00389.
10. Akinwumi, I.I.; Ajayi, O.O.; Agarana, M.C.; Ogbiye, A.S.; Ojuri, O.O.; David, A.O. Investigation of calcium carbide residue as a stabilizer for tropical sand used as pavement material. *WIT Trans Built Environ.* **2019**, *182*, 285–294.
11. Behnood, A. Transportation geotechnics soil and clay stabilization with calcium- and non-calcium-based additives: A state-of-the-art review of challenges, approaches and techniques. *Transp Geotech.* **2018**, *17*, 14–32. <https://doi.org/10.1016/j.trgeo.2018.08.002>.
12. Tangchirapat, W.; Jaturapitakkul, C.; Kiattikomol, K. Compressive strength and expansion of blended cement mortar containing palm oil fuel ash. *J. Mater. Civ. Eng.* **2009**, *21*, 426–431.
13. Khalid, N.; Arshad, M.F.; Mukri, M.; Kamarudin, F.; Ghani, A.H.A. The California bearing ratio value for banting soft soil subgrade stabilized using Lime-Pofa mixtures. *EJGE* **2014**, *19*, 155–163.
14. Pourakbar, S.; Asadi, A.; Huat, B.B.K.; Fasihnikoutalab, M.H. Stabilization of clayey soil using ultrafine palm oil fuel ash (POFA) and cement. *Transp. Geotech.* **2015**, *3*, 24–35.
15. Jafer, H.; Atherton, W.; Sadique, M.; Ruddock, F.; Loffill, E. Stabilisation of soft soil using binary blending of high calcium fly ash and palm oil fuel ash. *Appl. Clay Sci.* **2018**, *152*, 323–332.
16. *British Standard 1377*; Methods of Testing Soils for Civil Engineering Purposes. British Standard Institute: London, UK, 1990.
17. *British Standard 1924*; Methods of Tests for Stabilized Soils. British Standards Institute: London, UK, 1990.
18. Ola, S.A. Need for estimated cement requirement for stabilizing lateritic soil. *J Transp Divi.* **1974**, *17*, 379–388.
19. Horpibulsuk, S.; Phetchuay, C.; Chinkulkijniwat, A. Soil Stabilization by calcium carbide residue and fly ash. *J. Mater. Civ. Eng.* **2012**, *24*, 184–193. [https://doi.org/10.1061/\(asce\)mt.1943-5533.0000370](https://doi.org/10.1061/(asce)mt.1943-5533.0000370).
20. Federal Ministry of Works & Housing. *General Specifications*; Government of the Federal Republic of Nigeria: Abuja, Nigeria, 1997.
21. American Association of State Highway and Transportation Official. *Standard Specifications for Transportation, Material and Method of Sampling and Testing*, 14th ed.; AASHTO: Washington DC, USA, 1986.
22. Attah, I.C.; Okafor, F.O.; Ugwu, O.O. Optimization of California bearing ratio of tropical black clay soil treated with cement kiln dust and metakaolin blend. *Int. J. Pavement Res. Technol.* **2021**, *14*, 655–667. <https://doi.org/10.1007/s42947-020-0003-6>.
23. Ayodele, F.O.; Fajimi, M.S.; Alo, B.A. Stabilization of tropical soil using calcium carbide residue and rice husk ash. *Mater. Today: Proc.* **2022**, *60*, 216–222. <https://doi.org/10.1016/j.matpr.2021.12.465>.
24. Roy, A. Soil stabilization using rice husk ash and cement. *Int. J. Civ. Eng. Res.* **2014**, *5*, 49–54.
25. Alaneme, G.U.; Attah, I.C.; Etim, R.K.; Dimonyeka, M.U. Mechanical properties optimization of soil-cement kiln dust mixture using extreme vertex design. *Int. J. Pavement Res. Technol.* **2022**, *15*, 719–750. <https://doi.org/10.1007/s42947-021-00048-8>.

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.