

Proceeding Paper

# New Azo Carboxylic Dyes Derived from Eugenol: Synthesis and Preliminary Application to Polyamide <sup>†</sup>

José R. A. Coelho <sup>\*</sup>, Maria José G. Fernandes and M. Sameiro T. Gonçalves

Centre of Chemistry (CQ-UM), Department of Chemistry, University of Minho, Campus of Gualtar, 4710-057 Braga, Portugal; mjfernandes@quimica.uminho.pt (M.J.G.F.); msameiro@quimica.uminho.pt (M.S.T.G.)

<sup>\*</sup> Correspondence: a85799@alunos.uminho.pt

<sup>†</sup> Presented at the 27th International Electronic Conference on Synthetic Organic Chemistry (ECSOC-27), 15–30 November 2023; Available online: <https://ecsoc-27.sciforum.net/>.

**Abstract:** A series of azo dyes containing eugenol, the major phenolic compound in clove (*Syzygium aromaticum*) essential oil, was synthesized by coupling reactions of diazonium salts of different amines based on 3-aminobenzoic acid with eugenol. The new eugenol-based azo dyes were fully characterized by the usual analytical techniques and used in preliminary reactive dyeing tests on polyamide fabric to determine the colour fastness and staining under domestic washing conditions. The results obtained revealed the potential of these dyes for applications in the textile area.

**Keywords:** eugenol derivatives; essential oils; azo dyes

## 1. Introduction

Every day, dyeing is used in large scale in order to optimize and improve the aesthetics of textiles to face the growth of the textile industry [1]. Consequently, this growth has negative impact on the environment once textile industry is a significant contributor to environmental pollution [2]. To face this problem, dyes derived from natural compounds are a new and eco-friendly alternative to synthetic dyes [3].

Eugenol, a natural compound present in clove oil, allows the azo coupling reaction leading to the formation of azo dyes [4–6]. As is well-known, azo dyes being the most important synthetic colourants that have been widely used in textile manufacturing [7].

From a chemical perspective, azo derivatives consist of aryl/alkyl and –N=N– groups, which are usually synthesized by diazotization of a primary aromatic amines and the coupling of the corresponding diazonium salts with an activated aromatic substrate [8,9]. The azo reactive dyes are characterized by having chemical groups capable of forming covalent bonds with the textile substrates, through a certain dye activation process [10].

Considering all these facts, the synthesis and full characterization of three azo dyes from diazonium salts of 3-aminobenzoic acids and eugenol was conducted. Polyamide fabric was dyed with the dyes obtained and the colour fastness was evaluated under domestic washing conditions.

## 2. Results and Discussion

### *Synthesis of Eugenol Derivatives*

Eugenol dyes **3a–c** were synthesized by coupling eugenol with different aromatic amines. The reaction from 3-aminobenzoic acid **1a**, 3-amino-2-methylbenzoic acid **1b** or 3-amino-4-methylbenzoic acid **1c** with sodium nitrite, under acidic conditions, resulted in formation of the corresponding diazonium salts, which reacted with eugenol (4-allyl-2-methoxyphenol), in the presence of sodium hydroxide, to give 3-((5-allyl-2-hydroxy-3-methoxyphenyl)diazenyl)benzoic acid **3a**, 3-((5-allyl-2-hydroxy-3-methoxyphenyl)diazenyl)-2-

**Citation:** Coelho, J.R.A.; Fernandes, M.J.G.; Gonçalves, M.S.T. New Azo Carboxylic Dyes Derived from Eugenol: Synthesis and Preliminary Application to Polyamide. *Chem. Proc.* **2023**, *14*, x. <https://doi.org/10.3390/xxxxx>


Academic Editor: Firstname Last-name

Published: 15 November 2023



**Copyright:** © 2023 by the authors. Submitted for possible open access publication under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

methylbenzoic acid **3b** and 3-((5-allyl-2-hydroxy-3-methoxyphenyl)diazenyl)-4-methylbenzoic acid **3c**, respectively (Scheme 1).

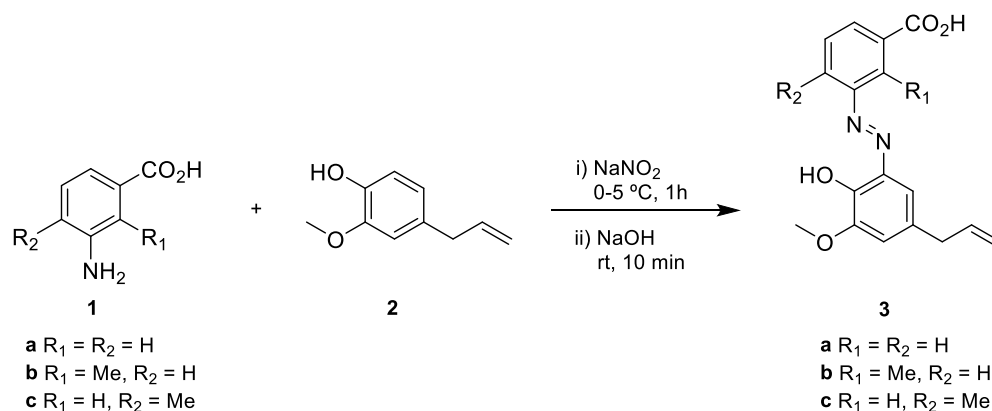

**Scheme 1.** Synthesis of eugenol carboxylic dyes **3a–c**.


Compounds **3a–c** were obtained as orange (**3a**) or red-brown solids (**3b,c**) in 40 to 76% yields, and were fully characterized by the usual analytical techniques.


Their  $^1\text{H}$  NMR spectra showed the different characteristic signals for the aliphatic protons, namely for the methyl ( $\delta$  2.69–2.80 ppm), methoxyl ( $\delta$  3.84–3.86 ppm) and methylenic groups ( $\delta$  at about 3.4 ppm), as well as the expected protons for the eugenol's double bond as multiplets,  $\text{CH}_2$  ( $\delta$  5.05–5.17 ppm) and  $\text{CH}$  ( $\delta$  5.95–6.05 ppm), in addition to the aromatic protons from eugenol H-4 and H-6 as doublets ( $\delta$  6.97–7.23 ppm), and the amines, H-2, H-4, H-5 and H-6 ( $\delta$  7.56–8.44 ppm).

The  $^{13}\text{C}$  NMR spectra of all compounds showed signals of the aliphatic carbons from the methyl ( $\delta$  14.25–17.48 ppm), methylene groups ( $\delta$  at about 38.90 ppm) and methoxyl ( $\delta$  at about 56.06 ppm), in addition to carbons of the aromatic rings ( $\delta$  111.92–151.67 ppm) and the carbonyl groups ( $\delta$  166.79–168.82 ppm).

The FTIR spectra of respective dyes also confirmed the presence of  $\text{CO}_2\text{H}$  groups, showing the corresponding  $\text{C}=\text{O}$  stretching vibrations bands at  $1679\text{ cm}^{-1}$ . The  $-\text{N}=\text{N}-$  groups stand out at  $1425\text{ cm}^{-1}$ , which indicates the asymmetric stretching of the respective bond.

The UV-visible absorption spectra of dyes **3a–c** in solvents of different polarities revealed wavelengths of maximum absorption ( $\lambda_{\text{max}}$ ) in the range 341–347 nm (Figure 1), with molar extinction coefficient ( $\epsilon$ ), showed as  $\log \epsilon$ , between 3.84 and 4.39 (Table 1). The presence of the methyl group influences the  $\lambda_{\text{max}}$ , since it causes a slight bathochromic shift in dyes **3b** and **3c** compared to **3a**. The  $\lambda_{\text{max}}$  is identical in **3b** and **3c** because they are constitutional isomers (only the position of the methyl group changes).

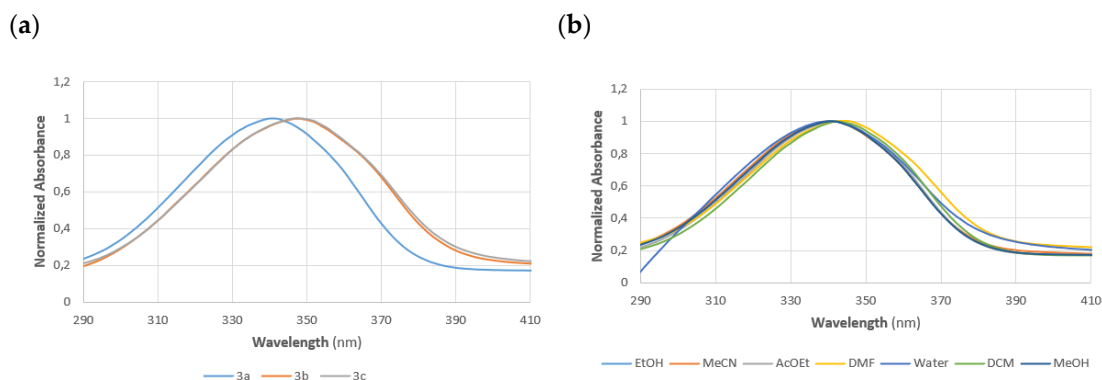

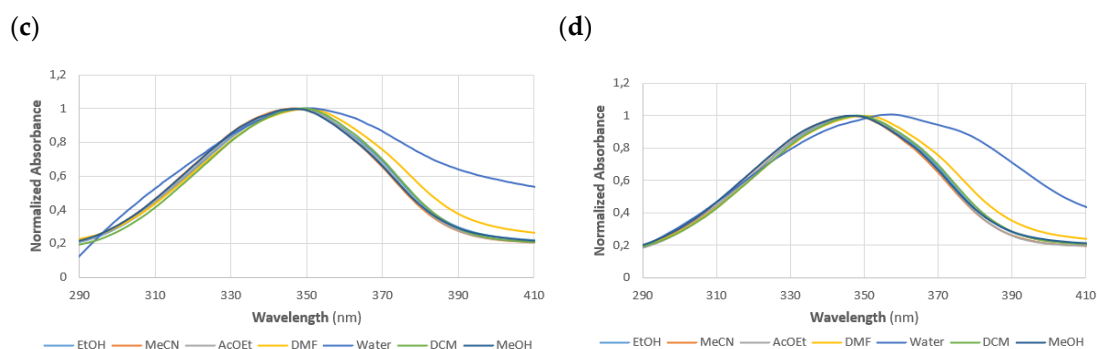

**Figure 1.** Absorption spectra of dyes **3a–c** in absolute ethanol (a). Absorption spectra of dyes **3a** (b), **3b** (c) and **3c** (d) in different solvents.

**Table 1.** The absorption data of compounds **3a–c** at  $1.0 \times 10^{-4}$  M in different solvents.


| Solvent          | Dye              |                 |                  |                 |                  |                 |
|------------------|------------------|-----------------|------------------|-----------------|------------------|-----------------|
|                  | 3a               |                 | 3b               |                 | 3c               |                 |
|                  | $\lambda_{\max}$ | $\log \epsilon$ | $\lambda_{\max}$ | $\log \epsilon$ | $\lambda_{\max}$ | $\log \epsilon$ |
| EtOH             | 342              | 4.34            | 347              | 4.26            | 347              | 4.18            |
| MeCN             | 341              | 4.23            | 347              | 4.27            | 347              | 4.25            |
| AcOEt            | 342              | 4.25            | 347              | 4.28            | 348              | 4.19            |
| DMF              | 344              | 4.16            | 350              | 4.22            | 350              | 4.18            |
| H <sub>2</sub> O | 341              | 3.84            | 350              | 3.88            | 357              | 4.10            |
| DCM              | 342              | 4.39            | 349              | 4.21            | 348              | 4.20            |
| MeOH             | 341              | 4.34            | 347              | 4.23            | 346              | 4.17            |

The dyeing of polyamide fabrics was performed at 100 °C during 30 min. by using ethyl chloroformate activation of the carboxylic acid group of the dyes **3a–c** for the reactive dyeing of the textile material, and the coloured samples were submitted to the ISO 105 CO6, AS1 test [11,12]. The results of wash fastness shown in Table 2 demonstrates that eugenol dyes **3a–c** exhibited moderate or good fastness levels to washing, with change in colour of 3 or 4 (**3b**) and colour staining of 5 (with exception of **3c** in cotton) in the grey scale.


**Table 2.** Washing fastness indices of dyes with colours **3a–c**.

| Dye       | Change in Shade | Staining |        |
|-----------|-----------------|----------|--------|
|           |                 | Wool     | Cotton |
| <b>3a</b> | 3               | 5        | 5      |
| <b>3b</b> | 4               | 5        | 5      |
| <b>3c</b> | 3               | 5        | 4      |

The FTIR spectra of the dyed fabric (Nylon 6) suggested that previously activated dye bonded to polyamide through the disappearance of the band attributed to the stretching of the N-H bond at  $3297 \text{ cm}^{-1}$  and the appearance of a band associated with the C=O group of an imide at  $1713 \text{ cm}^{-1}$ , which was previously at  $1631 \text{ cm}^{-1}$ , due to the C=O group of an amide (Figure 2).

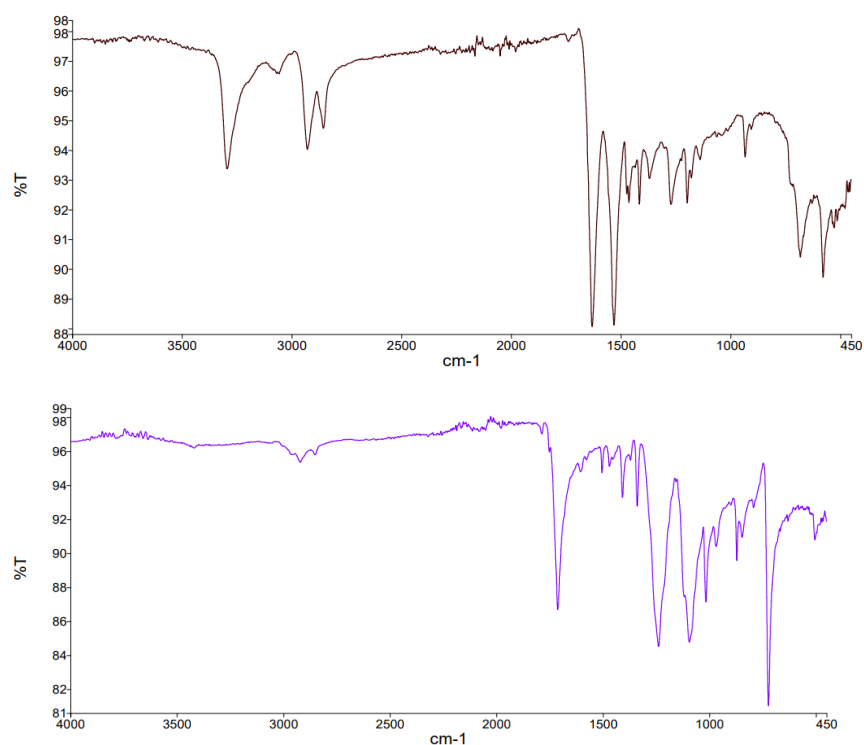

**Figure 2.** FTIR spectra of polyamide fabric (in brown) and the dyed polyamide with the dye **3b** (in purple).

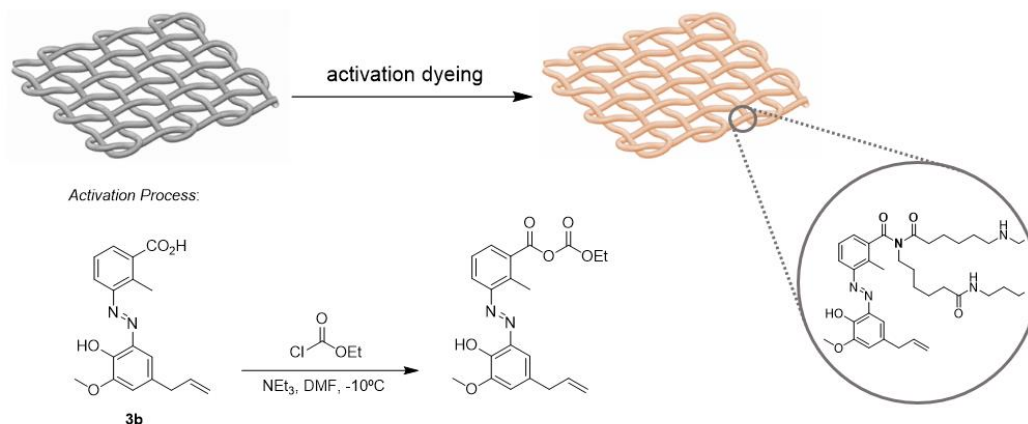

**Figure 3.** Dyeing approach by dye **3b** activation.

### 3. Experimental

#### 3.1. Typical Procedure for the Preparation of Compounds **3a–c** (Illustrated for **3a**)

A mixture of 3-aminobenzoic acid **1a** (0.500 g,  $3.65 \times 10^{-3}$  mol, 2 equiv), 1 M HCl (7.5 mL) and 6 M HCl (0.42 mL) was cooled to 0–5 °C. Aqueous sodium nitrite (0.251 g,  $1.83 \times 10^{-3}$  mol, 1 equiv, in 1 mL of water) was added and the reaction mixture was stirred for 45 min. The diazonium salt solution previously prepared was added dropwise to a solution of eugenol, 4-allyl-2-methoxyphenol **2** (0.300 g,  $1.83 \times 10^{-3}$  mol, 1 equiv) in NaOH (0.120 g,  $3.00 \times 10^{-3}$  mol, 1.6 equiv) and H<sub>2</sub>O (1 mL). The precipitated dye was filtered, washed with cold water and diethyl ether, and dried. The crude product was subjected to flash column chromatography on silica gel, with DCM:MeOH, mixtures of increasing polarity, as eluent giving 3-((5-allyl-2-hydroxy-3-methoxyphenyl)diazenyl)benzoic acid **3a** as an orange solid (0.221 g, 40% yield).  $R_f = 0.63$  (silica; dichloromethane:methanol 90:10), m.p. = 127–

129 °C. IR ( $\nu_{\max}$ ): 2844, 2565, 1679, 1639, 1606, 1575, 1495, 1480, 1455, 1424, 1379, 1308, 1293, 1263, 1224, 1143, 1102, 1074, 905, 847, 762  $\text{cm}^{-1}$ .  $^1\text{H}$  NMR (DMSO- $d_6$ , 400 MHz):  $\delta_{\text{H}}$  3.41 (2H, d,  $J = 6.8$  Hz,  $\text{CH}_2\text{Ph}$ ), 3.84 (3H, s,  $\text{OCH}_3$ ), 5.05–5.14 (2H, m,  $\text{CH}=\text{CH}_2$ ), 5.95–6.02 (1H, m,  $\text{CH}=\text{CH}_2$ ), 6.98 (1H, d,  $J = 2.0$  Hz, H-4), 7.17 (1H, d,  $J = 2.0$  Hz, H-6), 7.70 (1H, t,  $J = 8.0$  Hz, H-5 Ph-COOH), 8.07 (1H, dt,  $J = 8.0$  and 1.6 Hz, H-4 Ph-COOH), 8.22 (1H, dq,  $J = 8.0$  and 2.0 Hz, H-6 Ph-COOH), 8.44 (1H, t,  $J = 1.6$  Hz, H-2 Ph-COOH), 10.60 (1H, s, OH), 13.25 (1H, br s, COOH) ppm.  $^{13}\text{C}$  NMR (DMSO- $d_6$ , 100 MHz):  $\delta_{\text{C}}$  38.93 ( $\text{CH}_2\text{Ph}$ ), 56.06 ( $\text{OCH}_3$ ), 111.92 (C-6), 115.90 (C-4), 116.00 ( $\text{CH}=\text{CH}_2$ ), 122.79 (C-2 Ph-COOH), 127.06 (C-6 Ph-COOH), 129.75 (C5 Ph-COOH), 130.35 (C-1), 131.29 (C-4 Ph-COOH), 132.19 (C-1 Ph-COOH), 137.53 ( $\text{CH}=\text{CH}_2$ ), 138.50 (C-5), 144.10 (C-2), 149.11 (C-3), 151.67 (C-3 Ph-COOH), 166.79 (COOH) ppm.

### 3.2. Typical Procedure for Dyeing of Polyamide Fabric (Illustrated for 3a)

To a cooled solution of the dye 3a (0.015 g,  $4.80 \times 10^{-4}$  mol) in DMF (1.25 mL), triethylamine (0.020 mL,  $1.44 \times 10^{-3}$  mol) and ethyl chloroformate (0.014 mL,  $1.44 \times 10^{-3}$  mol) were added and the solution was kept stirred for 30 min. The triethylamine hydrochloride was filtered off and after adding water (100 mL) and the polyamide fabric (0.750 g) (the concentration of the dye in the dye bath was 2% to the fibre weight; liquor ratio 67:1) the mixture was stirred for 30 min. at 100 °C. The fabric was removed, washed, and boiled for 15 min in water with Kieralon OLB soap (4 g/L) and, after drying, submitted to the ISO 105 C06-AS1 test [11,12].

## 4. Conclusions

Three azo carboxylic dyes that incorporate the eugenol unit in their structures displayed absorption maxima at 342–347 nm (in absolute ethanol), were obtained in good yields and applied through a reactive dyeing process, where they showed moderate to good fastness levels to washing on polyamide fabric. Encouraged by these results, new dyes will be synthesized and used in the dyeing of other textile materials, in order to generate more knowledge in terms of the potential application in the textile area of this type of semi-synthetic dyes based on eugenol.

**Funding:** Foundation for Science and Technology (FCT, Portugal), and FEDER-COMPETE-QREN-EU for financial support to the research centre CQ-UM (UID/QUI/00686/2020). The NMR spectrometer Bruker Avance III 400 is part of the National NMR Network and was purchased within the framework of the National Program for Scientific Re-equipment, contract REDE/1517/RMN/2005 with funds from POCI 2010 (FEDER) and FCT.

**Conflicts of Interest:** The authors declare no conflict of interest.

## References

1. Pizzicato, B.; Pacifico, S.; Cayuela, D.; Mijas, G.; Riba-Moliner, M. Advancements in sustainable natural dyes for textile applications: A review. *Molecules* **2023**, *28*, 5954.
2. Mouro, C.; Gomes, A.P.; Costa, R.V.; Moghtader, F.; Gouveia, I.C. The sustainable bioactive dyeing of textiles: A novel strategy using bacterial pigments, natural antibacterial ingredients, and deep eutectic solvents. *Gels* **2023**, *9*, 800.
3. Vespignani, L.; Bonanni, M.; Marradi, M.; Pizzo, B.; Bianchini, R.; Goli, G. Naturalized dyes: A new opportunity for the wood colouring. *Polym. J.* **2023**, *15*, 3632.
4. Ryzhkov, A.I.; Fedor, V.; Drozdov, F.V.; Georgij, V.; Cherkaev, G.V.; Buzin, M.I.; Svidchenko, E.A.; Muzafarov, A.M. Synthesis and properties of new siloxane with terminal azo dyes functions based on eugenol. *J. Appl. Polym. Sci.* **2022**, *139*, e52340.
5. Drozdov, F.V.; Cherkaev, G.V.; Mihail, I.; Buzin, M.I.; Muzafarov, A.M. Facile methods of siloxanes derivatives modification by azo dyes based on eugenol. *J. Organomet. Chem.* **2018**, *871*, 135–139.
6. Kantar, C.; Baltas, N.; Karaoglu, S.A.; Sasmaz, S. Some azo dyes containing eugenol and guaiacol, synthesis, antioxidant capacity, urease inhibitory properties and anti-helicobacter pylori activity. *Rev. Roum. Chim.* **2018**, *63*, 189–197.
7. Benkhaya, S.; M'rabet, S.; El Harfi, A. Classifications, properties, recent synthesis and applications of azo dyes. *Heliyon* **2020**, *6*, e03271.
8. Singh, A.; Sheikh, J. Synthesis of a novel cationic dye to impart mosquito-repellent and UV protection to an acrylic fabric. *ACS Omega* **2023**, *8*, 10214–10224.

9. Tahir, T.; Ashfaq, M.; Saleem, M.; Rafiq, M.; Shahzad, M.I.; Kotwica-Mojzych, K.; Mojzych, M. Pyridine scaffolds, phenols and derivatives of azo moiety: Current therapeutic perspectives. *Molecules* **2021**, *26*, 4872.
10. Mezgebe, K.; Mulugeta, E. Synthesis and pharmacological activities of azo dye derivatives incorporating heterocyclic scaffolds: A review. *RSC Adv.* **2022**, *12*, 25932–25946.
11. Gonçalves, M.S.T.; Oliveira-Campos, A.M.F.; Moura, J.C.V.P.; Maia, H.L.S.; Gomes, J.I.N.R.; Hrdina, R. Reaction of carboxylic dyes with wool and polyamide. Part III: Effect of the activating agent. *Dyes Pigm.* **1998**, *36*, 373–379.
12. *Norma Portuguesa NP EN ISO 105-C06:1999*; Têxteis: Ensaio de Solidez Dos Tintos: Parte C06: Solidez Dos Tintos à Lavagem Doméstica e Industrial: (ISO 105-C06:1999). Instituto Português da Qualidade: Almada, Portugal, 1999.

**Disclaimer/Publisher's Note:** The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.