

Proceeding Paper

Carbon Dots from *Porphyridium cruentum* Microalgae by High-Efficient Hydrothermal Approaches: Biocompatibility and Antioxidant Capabilities †

Inês Chouzende ¹, Alexandra I. Costa ^{1,2,*}, Patrícia D. Barata ^{1,2}, Sónia Martins ^{1,3}, Magda C. Semedo ^{1,3}, Fernando M. H. Cardoso ^{4,5}, Maria Luísa Lobo ^{4,5} and José V. Prata ^{1,2}

¹ Departamento de Engenharia Química (DEQ), Instituto Superior de Engenharia de Lisboa, Instituto Politécnico de Lisboa, R. Conselheiro Emídio Navarro, 1, 1959-007 Lisboa, Portugal; a49140@alunos.isel.pt (I.C.); patricia.barata@isel.pt (P.D.B.); sonia.martins@isel.pt (S.M.); magda.semedo@isel.pt (M.C.S.); jvprata@deq.isel.ipl.pt (J.V.P.)

² Centro de Química-Vila Real (CQ-VR), Universidade de Trás-os-Montes e Alto Douro, 5001-801 Vila Real, Portugal

³ Centro de Geobiociências, Geoengenharias e Geotecnologias (GeoBioTec), FCT-UNL, Monte de Caparica, 2829-516 Caparica, Portugal

⁴ Medical Parasitology Unit, Group of Opportunistic Protozoa/HIV and Other Protozoa, Global Health and Tropical Medicine, IHMT-UNL, R. da Junqueira 100, 1349-008 Lisboa, Portugal; fcardoso@ihmt.unl.pt (F.M.H.C.); luisalc@ihmt.unl.pt (M.L.L.)

⁵ LA-REAL, IHMT-UNL, R. da Junqueira 100, 1349-008 Lisboa, Portugal

* Correspondence: acosta@deq.isel.ipl.pt

† Presented at the 27th International Electronic Conference on Synthetic Organic Chemistry (ECSOC-27), 15–30 November 2023; Available online: <https://ecsoc-27.sciforum.net/>.

Abstract: Fluorescent carbon dots (μ Algae-CDs) were successfully prepared from renewable *Porphyridium cruentum* biomass using hydrothermal carbonization approach and ethylenediamine (ED) as nitrogen additive. Structural and photophysical properties of the as-synthesized nanomaterials were evaluated by FTIR, UV-Vis, and fluorescence spectroscopies. The new μ Algae-CDs synthesized with a ratio of 0.16 of ED did not exhibit cytotoxicity against non-tumor Vero cells and tumor Hela cells, showing potential application in bioimaging.

Keywords: carbon dots; microalgae; fluorescent; antioxidants; cytotoxicity

Citation: Chouzende, I.; Costa, A.I.; Barata, P.D.; Martins, S.; Semedo, M.C.; Cardoso, F.M.H.; Lobo, M.L.; Prata, J.V. Carbon Dots from *Porphyridium cruentum* Microalgae by High-Efficient Hydrothermal Approaches: Biocompatibility and Antioxidant Capabilities. *Chem. Proc.* **2023**, *14*, x. <https://doi.org/10.3390/xxxxx>

Academic Editor(s): Name

Published: 15 November 2023



Copyright: © 2023 by the authors. Submitted for possible open access publication under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Carbon dots (C-dots), a new “zero-dimensional” nanomaterial, have become one of the most prominent members of carbon materials family due to their excellent luminescence, great photostability, small size, low toxicity, and biocompatibility [1]. Especially, green carbon dots derived from natural resources have received extensive attention due to their unique benefits, including abundant sources, cost-effectiveness, and environmental friendliness [2].

Bottom-up green approaches based on the use of renewable biomass for producing C-dots are particularly attractive since high-valued nanomaterials can be obtained from low-value precursors, contributing to a circular economy [3,4]. Regarding their unique properties, green C-dots have shown tremendous potential application in several areas such as biomedicine, (bio)sensors, photocatalysis, optoelectronics and bioimaging [1,5].

Among the various green sources explored, microalgae (μ Algae) have prominent advantages with respect to their ease in growth, ability to survive in extreme conditions of pH and temperature, that make them a promising green low-cost feedstock for the large-scale synthesis of nanoparticles [6]. Additionally, their richness in compounds that benefit human health, including lutein, astaxanthin, β -carotene and unsaturated fatty

acids provide this biomass source with enormous potential to produce carbon materials with varied physicochemical and morphological properties [7,8].

In this work, we highlight the synthesis of green C-dots (μ Algae-CDs) by one-pot hydrothermal treatment of *Porphyridium cruentum* biomass, a red marine microalgae. Results concerning biocompatibility and antioxidant capabilities of the new nanomaterials will also be presented.

2. Materials and Methods

2.1. Materials

The biomass of *Porphyridium cruentum* microalgae used in the experiments was produced in flat-panel photobioreactors at Allmicroalgae® industrial facilities and was kept refrigerated at 5 °C until use. All reagents were used as received and the solvents were of analytical grade and/or were purified by standard methods. In all experiments was used ultrapure water (Milli-Q, Millipore).

2.2. Methods

A high-pressure reactor (Parr model 4560) equipped with pressure, temperature, and stirring sensors/controllers (Parr, model 4843), was used for hydrothermal carbonization of the biomass.

The structural characterisation of the as-prepared μ Algae-CDs was accomplished by FTIR on a Bruker Vertex 70 as KBr pellets, while for UV-Vis analysis the aqueous dispersions were directly employed after appropriate dilution on a Jasco UV V-750 spectrophotometer using 1 cm quartz cells.

Fluorescence spectra were obtained on a Perkin Elmer LS45 fluorimeter using a 1 cm quartz cuvette at 25 °C in right angle (RA) geometry. Fluorescence quantum yields (Φ_F) were measured in aqueous solutions using quinine sulphate in 0.01 M H₂SO₄ ($\Phi_F = 0.54$) as reference standard [9,10]. The optical density of the samples was kept below 0.05 at the excitation wavelength to prevent homo-inner filter effects. The microscopy fluorescence images were obtained on a fluorescence microscope Olympus BX51.

2.2.1. Synthesis of Carbon Dots (CDs)

The biomass was fed into an inox vessel with water and ethylenediamine (ED) as additive in several ratios. The hydrothermal carbonization of the biomass was achieved at the desired temperature (200–250 °C) for a certain period (4–6 h), under air-equilibrated conditions, using wet biomass (after removed the nutrient by centrifugation) or dry biomass achieved from the wet biomass.

The as-synthesized μ Algae-CDs were cooled to room temperature and the reaction mixture was filtered through a 0.2 μ m cellulose membrane, yielding aqueous dispersions. Low polarity molecular species were removed by liquid-liquid extraction with CH₂Cl₂/AcOEt.

2.2.2. In Vitro Cytotoxicity Assays and Cell Imaging

The viability of Vero (ATCC™ CCL-81) and HeLa (ATCC™ CCL-2) cell-lines was determined using the 3-(4,5-dimethylthiazol-2-yl)-2,5-diphenyltetrazolium bromide (MTT) assay [11]. Cells were seeded in a 96-well plate in Dulbecco® Modified Eagle Medium (GIBCO®, Thermo Fisher Scientific). After spreading, cells were treated with the μ Algae-CDs concentrations of 0.02–4000 μ g mL⁻¹ and incubated at 37 °C under a 5% CO₂ enriched atmosphere. After incubation for 18 h, an MTT solution was added into each well and microtiter plates were incubated. The concentration of blue formazan crystals produced by live cells by reduction of MTT in mitochondria were determined by UV-Vis spectroscopy. The absorption spectrum was acquired, and the absorbance was read at 570 nm using 650 nm as reference.

Cellular uptake of μ Algae-CDs was observed by fluorescence microscopy.

2.2.3. Evaluation of Antioxidant Capacity

The antioxidant capacities of the μ Algae-CDs were evaluated by ABTS radical cation method [12]. The reaction was conducted at room temperature in the dark for 6 min and the absorbance was measured at 655 nm. The radical scavenging effect was calculated using the following equation:

$$\text{Inhibition (\%)} = (A_c - A_s) \times 100/A_c$$

where A_c is the absorbance of the negative control and A_s is the absorbance of the sample solution. Trolox was used as positive control.

3. Results and Discussion

3.1. Synthesis and Surface Characterization

The μ Algae-CDs were synthesized by one-step hydrothermal method in a high-pressure reactor using an aqueous suspension from *Porphyridium cruentum* biomass (4.0 g) and ED as nitrogen source (ED/biomass ratio = 0.16) under stirring. After dwell time of 6 h at 250 °C, the resultant material was filtrated through a cellulose membrane, resulting in a yellowish-brown liquor.

The FTIR spectrum of μ Algae-CDs (Figure 1) showed an intense broad band at 3430 cm^{-1} from O-H, with a shoulder near 3270 cm^{-1} and N-H stretching, and weak bands at ~2930–2858 cm^{-1} , assigned to C-H bonds. The presence of intense band at 1656 cm^{-1} is attributed to conjugated C=O and carboxylate functionalities, and C=C stretching. C-H bending bands at 1440 cm^{-1} (CH_2) and 1370 cm^{-1} (CH_3) are also present.

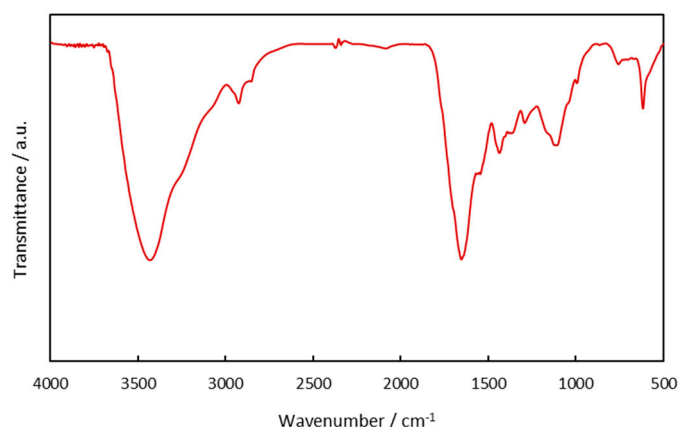


Figure 1. FTIR spectrum of the synthesized μ Algae-CNDs (KBr).

3.2. Optical Characterization

Aqueous dispersions of μ Algae-CDs were prepared in appropriate concentrations to the optical assays. The UV-Vis absorption spectrum of μ Algae-CDs showed long absorption edge in both UV and visible region (300–600 nm) (Figure 2a).

The aqueous dispersions of μ Algae-CDs displayed a maximum excitation and emission at 346 and 438 nm, respectively (Figure 2a) and exhibited blue colour when irradiated with 366 nm ultraviolet light (Figure 2a, inset).

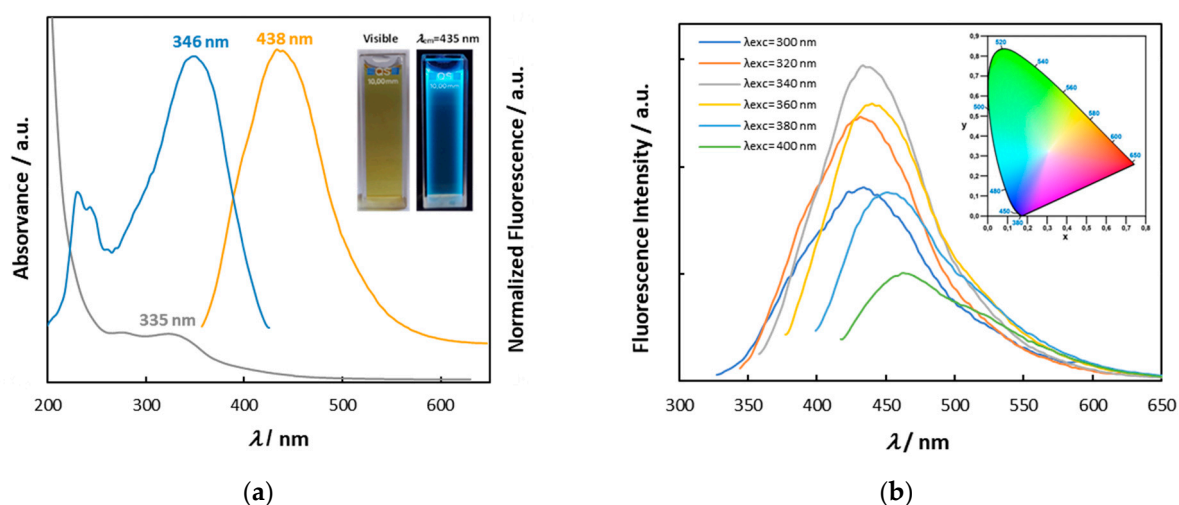


Figure 2. (a) UV-Vis (grey), excitation (blue, monitored at 435 nm) and emission (orange; $\lambda_{\text{exc}} = 340$ nm) spectra of $\mu\text{Algae-CDs}$ in aqueous dispersion (0.1 mg mL^{-1}) (inset: photograph of $\mu\text{Algae-CDs}$ showing emission colours); (b) Emission spectra of $\mu\text{Algae-CDs}$ with different excitation wavelengths (inset: CIE chromaticity diagram).

The $\mu\text{Algae-CDs}$ synthesized with ED as nitrogen source using wet and dry biomass of *P. cruentum* showed relevant fluorescence quantum yields ($0.07 < \Phi_{\text{F}} < 0.16$), revealing a strong dependence between λ_{exc} and λ_{em} (Figure 2b) and excellent photostability (not shown).

3.3. Antioxidant Performance of $\mu\text{Algae-CDs}$

An important property of C-dots is their antioxidant activity, i.e., the ability to act as a free radical scavenger. The antioxidant capacity of $\mu\text{Algae-CDs}$ at 5 mg mL^{-1} was evaluated with the ABTS radical inhibition assay (Table 1).

Table 1. Antioxidant activity and quantum yield of $\mu\text{Algae-CDs}$.

Entry	Antioxidant Activity/%	$\Phi_{\text{F}} (\lambda = 340 \text{ nm})$
1	94.2 ± 0.47^1	0.065
2	38.3 ± 0.08^1	0.159

¹ Values are mean \pm SD for three determinations for antioxidant activity.

The results showed that the $\mu\text{Algae-CDs}$ obtained from wet biomass (Entry 1, Table 1) had better biological properties, even though they revealed a lower quantum yield as compared to the carbon dots achieved from dry biomass (Entry 2, Table 1).

3.4. Toxicity Evaluation and Cell Imaging

Using MTT assays, the biocompatibility of $\mu\text{Algae-CDs}$ against two epithelial cell lines, Vero (kidney epithelial cells extracted from an African green monkey) and HeLa (human cervical tumour cells) was evaluated over a concentration range of 0.02 to $4000 \mu\text{g mL}^{-1}$ (Figures 3 and 4, respectively).

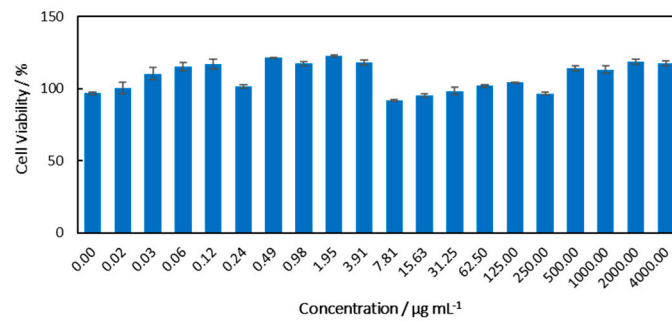


Figure 3. Cell viability of μ Algae-CDs at different concentrations for Vero cell-line.

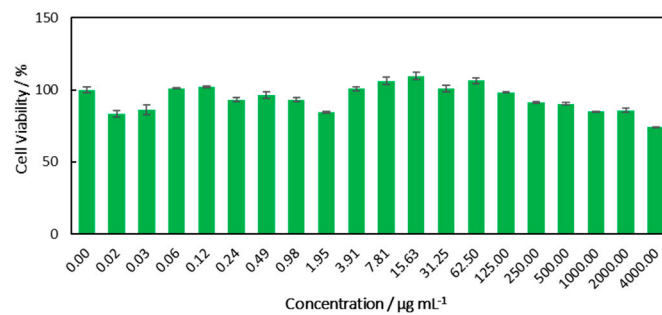


Figure 4. Cell viability of μ Algae-CDs at different concentrations for HeLa cell-line.

Even for high levels of μ Algae-CDs, no significant cytotoxicity was observed for both cell lines, showing cell viability higher than 80%.

After incubation with μ Algae-CDs for 18 h at 37 °C, both cell lines were observed by fluorescence microscopy and the images in Figure 5 were collected.

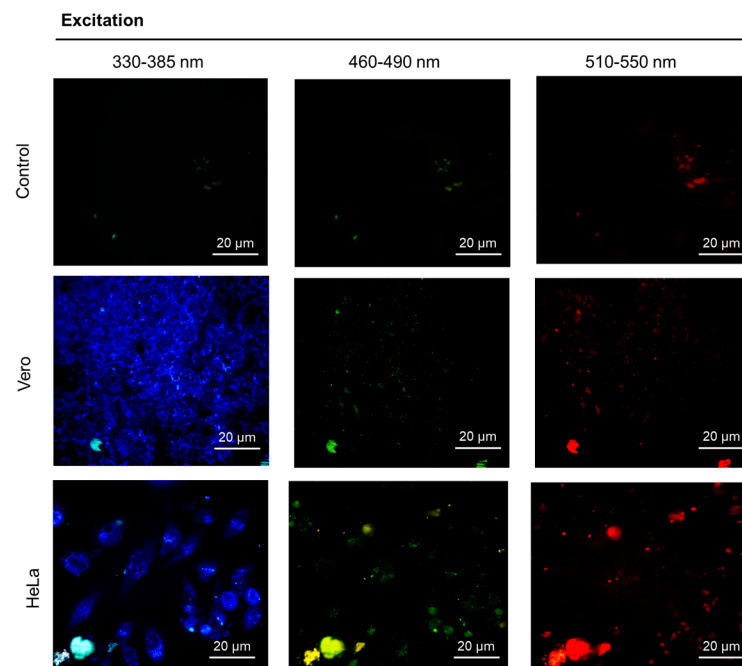


Figure 5. Optical microscopy fluorescence images of Vero and HeLa cell-lines with μ Algae-CDs (400 \times).

4. Conclusions

The μ Algae-CDs were prepared from biomass of red microalgae *Porphyridium cruentum* using an ecofriendly method and showed good photostability and relevant quantum yield.

The ABTS assay showed high efficacy in radical scavenging, suggesting good antioxidant properties for the μ Algae-CDs.

The μ Algae-CNDs did not exhibit cytotoxicity against Vero and Hela cells and by fluorescence microscopy was observed μ Algae-CNDs internalization by both cell lines, that opens up new applications for these nanomaterials.

Author Contributions: Conceptualization, A.I.C., J.V.P. and P.D.B.; methodology, J.V.P., F.M.H.C. and M.L.L.; investigation, I.C., F.M.H.C. and M.L.L.; resources, A.I.C.; data curation, A.I.C., I.C., M.C.S., P.D.B. and S.M.; writing-original draft preparation, A.I.C., M.C.S., P.D.B. and S.M.; writing-review and editing, A.I.C., J.V.P., M.C.S., P.D.B. and S.M. All authors have read and agreed to the published version of the manuscript.

Funding: We are grateful to Fundação para a Ciência e a Tecnologia/Ministério da Ciência, Tecnologia e Ensino Superior (FCT/MCTES) for financial support (UIDB/00616/2023, UIDP/00616/2023 and UIDP/04035/2020), and Instituto Politécnico de Lisboa (IPL/2022/ μ Algae2Dot_ISEL).

Acknowledgments: We thank Allmicroalgae-Natural Products, S.A. for μ Algae biomass supply.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Ozyurt, D.; Kobaisi, M.A.; Hocking, R.K.; Fox, B. Properties, synthesis, and applications of carbon dots: A review. *Carbon Trends* **2023**, *12*, 100276. <https://doi.org/10.1016/j.cartre.2023.100276>.
2. Bressi, V.; Balu, A.M.; Iannazzo, D.; Espro, C. Recent advances in the synthesis of carbon dots from renewable biomass by high-efficient hydrothermal and microwave green approaches. *Curr. Opin. Green Sustain. Chem.* **2023**, *40*, 100742. <https://doi.org/10.1016/j.cogsc.2022.100742>.
3. Costa, A.I.; Barata, P.D.; Moraes, B.; Prata, J.V. Carbon Dots from Coffee Grounds: Synthesis, Characterization, and Detection of Noxious Nitroanilines, *Chemosensors* **2022**, *10*, 113. <https://doi.org/10.3390/chemosensors10030113>.
4. Sousa, D.A.; Costa, A.I.; Alexandre, M.R.; Prata, J.V. How an Environmental Issue could Turn into Useful High-valued Products: The Olive Mill Wastewater Case. *Sci. Total Environ.* **2019**, *647*, 1097–1105.
5. Đorđević, L.; Arcudi, F.; Cacioppo, M.; Prato, M. A multifunctional chemical toolbox to engineer carbon dots for biomedical and energy applications. *Nat. Nanotechnol.* **2022**, *17*, 112–130. <https://doi.org/10.1038/s41565-021-01051-7>.
6. Jacob, J.M.; Ravindran, R.; Narayanan, M.; Samuel, S.M.; Pugazhendhi, A.; Kumar, G. Microalgae: A prospective low cost green alternative for nanoparticle synthesis. *Curr. Opin. Environ. Sci. Health* **2021**, *20*, 100163. <https://doi.org/10.1016/j.coesh.2019.12.005>.
7. Dong, D.; Liu, T.; Liang, D.; Jin, X.; Qi, Z.; Li, A.; Ning, Y. Facile Hydrothermal Synthesis of Chlorella-Derived Environmentally Friendly Fluorescent Carbon Dots for Differentiation of Living and Dead Chlorella. *ACS Appl. Bio Mater.* **2021**, *4*, 3697–3705. <https://doi.org/10.1021/acsubm.1c00178>.
8. Ramanan, V.; Thiyagarajan, S.K.; Raji, K.; Suresh, R.; Sekar, R.; Ramamurth, P. Outright Green Synthesis of Fluorescent Carbon Dots from Eutrophic Algal Blooms for In Vitro Imaging. *ACS Sustainable Chem. Eng.* **2016**, *4*, 4724–4731. <https://doi.org/10.1021/acssuschemeng.6b00935>.
9. Eaton, D.F. Reference materials for fluorescence measurement. *Pure Appl. Chem.* **1988**, *60*, 1107–1114.
10. A Guide to Recording Fluorescence Quantum Yields, Horiba Scientific. Available online: https://static.horiba.com/fileadmin/Horiba/Application/Materials/Material_Research/Quantum_Dots/quantumyieldstrad.pdf (accessed on 10 October 2023).
11. Mosmann, T. Rapid Colorimetric Assay for Cellular Growth and Survival: Application to Proliferation and Cytotoxicity Assays. *J. Immunol. Methods* **1983**, *65*, 55–63.
12. Re, R.; Pellegrini, N.; Proteggente, A.; Pannala, A.; Yang, M.; Rice-Evans, C. Antioxidant activity applying an improved ABTS radical cation decolorization assay. *Free Radic. Biol. Med.*, **1999**, *26*, 1231–1237.

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.