

Sonochemically synthesized microporous metal-organic framework for rapid and efficient ultrasonic-assisted removal of mercury(II) ions in water solution and study of antibacterial activity

Ehsan Moradi ^{a*}, Rahmatollah Rahimi ^{a*}, Vahid Safarifard ^{a*}, Shahram Azari ^b

^a Department of Chemistry, Iran University of Science and Technology, Tehran 16846-13114, Iran

^b National Cell Bank of Iran, Pasteur Institute of Iran, Tehran, Iran

moradi_e@alumni.iust.ac.ir, rahimi_rah@iust.ac.ir, vsafarifard@iust.ac.ir; Tel: +982177240290;

Fax: +982177491204

Abstract

Nowadays, water pollution through heavy metal ions is a great concern in all human communities. In this project, metal-organic frameworks (MOFs), which named by $[\text{Zn}_2(\text{oba})_2\text{bpy}]$, (**1**; H_2oba = 4,4-oxybisbenzoic acid and bpy = 4,4-bipyridine) linkers, were successfully synthesized. Properties of this MOF were performed using different techniques, such as FT-IR, XRD and SEM analysis. This framework has special characteristics like rapid, efficient and selective removal of metal ions from contaminated water. The use of an ultrasonic device plays an important role in shortening the absorption time of mercury(II) ions by increasing the absorbent dispersion in the solution. The adsorption capacity was affected by variables such as pH solution, Hg^{2+} initial concentration, adsorbent dosage and contact time. For Hg(II) metal ions the sorption capacities of 338 mgg^{-1} were obtained effectively by $\text{Zn}_2(\text{oba})_2\text{bpy}$ structures. The experimental adsorption data for $\text{Zn}_2(\text{oba})_2\text{bpy}$ MOF, is well suited with the pseudo-second-order kinetic model ($R^2 = 0.99$), and the adsorption isotherms of Hg^{2+} metal ions are in good agreement with the Langmuir model. This work displays to remove Hg^{2+} ions from pollutant water under 30 min effectively. The antibacterial activities of $[\text{Zn}_2(\text{oba})_2\text{bpy}]$ (**1**) were tested against gram-positive and gram-negative species. The as-synthesized **1** exhibited excellent antibacterial effectiveness against E.coli and S. aureus.

Keywords: Metal-Organic Framework; Ultrasound; Removal; Hg^{2+}

Introduction

Among various heavy metal ions, mercury (II) is known to cause acute and chronic poisoning, also has the ability to target almost all organs of the body, especially the central nervous system [1-3]. Because of these reasons, the adsorption of mercury (II) from contaminated water systems is so important [4]. Over the past two decades, different types of methods including membrane filtration, ion exchange, chemical precipitation, electrochemical treatment technologies, and adsorption have been used to remove metal ions [5]. Recently, the absorption method is known as an effective solution for the removal of heavy metals. The absorption method is a simple, low cost, and high-performance method that can be used on a large scale [6]. These properties of the absorption method depend on various factors such as solution pH, adsorbent dosage, contact time, ionic strength, background electrolyte, temperature and the

nature of adsorbent [7, 8]. Different adsorbents were used to absorb metal ions from water [9-11]. Conventional adsorbents have deficiencies such as high operating and maintenance costs, emission of secondary pollutants and, most importantly, the poor performance at very low concentrations. The preparation of metal-organic frameworks (MOFs) is an effective method for the absorption and selective separation of metal ions from water [12-15]. MOF is a solid adsorbent material made of secondary building units (SBUs), which includes metal clusters and organic linkers that caused to create three-dimensional grids [16, 17]. The selection of metal and linkers has a great influence on the structure and properties of MOFs [18]. The characteristics of these MOFs are large-sized cavities, high surface area, selectable absorption of small molecules, controllable particle dimensions and morphology, etc., which attracted the attention of researchers [19]. These features have promising results in applications such as sensing [20-22], gas storage [23], separation [24], drug delivery [25], and catalysis [26]. The use of MOFs is a growing approach to remove pollutants from water. The ultrasonic technique was used to increase and improve mass transfer [27]. The ultrasound power can accelerate the absorption process [28, 29]. Cavitation (nucleus, growth, and collapse of small gas bubbles) and the high-pressure variation caused by ultrasound cause this phenomenon [30]. In addition, by developing effective in-particle interaction using physical phenomena such as micro-turbulences, microstreaming, acoustic waves, and microjets, the chemical reactivity of particles in the solution can be improved [31]. Ultrasound has been proven to be a very useful tool for accelerating the absorption of metal ions and paint on adsorbent by enhancing the dependence between adsorbate and adsorbent [32-36]. In this study, $[\text{Zn}_2(\text{oba})_2\text{bpy}]$ (**1**) MOF with H_2oba = 4,4-oxybisbenzoic acid and bpy = 4,4-bipyridine linkers have been synthesized to remove mercury(II) ions from water. We evaluated the contact time, pH parameters, adsorbent dosage, and also the concentrations of mercury (II) metal ions. We show that nanoporous materials can play an effective role in the selective and effective removal of heavy metal ions from water.

Experimental Section

Materials and Measurements

All materials used during synthesis were purchased from a commercial provider. The infrared spectra were collected with a Nicolet 100 Fourier transform infrared (FTIR) spectrometer in the range of 400-4000 cm^{-1} . Powder X-ray diffraction (PXRD) measurements were done by using a Philips X'Pert diffractometer with a monochromated $\text{Cu K}\alpha$ radiation ($\lambda = 1.54056 \text{ \AA}$). Inductively coupled plasma atomic emission spectrometry (ICP-AES) on a Varian Vista-PRO instrument, equipped with a charge-coupled detector, was used to determine the remaining concentration of metal ions.

Solvothermal Synthesis of $[\text{Zn}_2(\text{oba})_2(\text{bpy})]$ (1**)**

$\text{Zn}(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ (0.116 g, 0.5 mmol), 4,4-oxybisbenzoic acid (0.129 g, 0.5 mmol) and 4,4-bipyridine (0.074 g, 0.25 mmol) were dissolved in 10 ml N,N-dimethylformamide (DMF) in a 20 ml glass vial. The mixture was stirred under sonication for 10 min to obtain a clear solution. The sealed vial was then placed in an oven and heated at 100 °C for 48 h. The solid product was then filtered and washed with DMF.

Sonochemical Synthesis of [Zn₂(oba)₂bpy] (1)

To prepared nano-sized [Zn₂(oba)₂(bpy)] (1), 25 ml solution of zinc (II) acetate dihydrate (0.5 mmol, 0.116 g; 0.02 M) in DMF was positioned in a high-density ultrasonic probe at ambient temperature and atmospheric pressure. Into this solution, 0.5 mmol (0.129 g) and 0.25 mmol (0.074 g) of the ligands H₂oba and bpy, respectively, were added and sonicated for 1 h. Moreover, the MOF was prepared in different concentrations of initial reagents of 0.01, 0.02 and 0.04 M using constant US generator power of 50W for 1 h irradiation time. The resulting powders were isolated by centrifugation, washed with DMF three times and dried in air for characterization.

Ultrasonic-Assisted Adsorption Experiments

In the batch absorption test, the effect of different parameters on the absorption performance of (1) was studied. In this way, 50 ml of mercury solution was added to 10 mg of adsorbent, at room temperature and in ultrasonic baths. Hg(NO₃)₂ were applied as the source of Hg (II). The solution pH was adjusted by adding 0.1 ml of 0.1 M NaOH or 0.1 M HCl. The mixture was centrifuged for 5 minutes after removing the ultrasonic bath. In the next step, sampling from the solution was performed. The total amount of adsorbed heavy-metal ions on [Zn₂(oba)₂(bpy)] (1), the removal efficiency were calculated from eqs 1 and 2, respectively:

$$Q_t = \frac{(C_0 - C_t)V}{m} \quad (1)$$

$$\%R = \frac{(C_0 - C_e)}{C_0} \times 100 \quad (2)$$

In these equations, C₀ and C_e point to the initial and equilibrium concentrations of Hg(II) ions (mg L⁻¹), V refers to the volume (L) of samples, and m to the adsorbent mass (g). The kinetics of the adsorption process on [Zn₂(oba)₂(bpy)] were evaluated by sampling a solution containing mercury and adsorbent ion at intervals of 5-30 min. Also, adsorbent isotherms [Zn₂(oba)₂(bpy)] were evaluated by adding 10 mg of adsorbent to various concentrations (5 to 120 mg L⁻¹) of mercury ions.

Results and Discussion

Characterization [Zn₂(oba)₂(bpy)] (1)

The compound [Zn₂(oba)₂(bpy)] (1) was sonochemically synthesized by mixing zinc acetate, 4,4-oxybis(benzoic acid) (H₂oba), 4,4-bipyridine (bpy), and DMF for 1 h. Compound 1 possesses a porous 3D network built from a Zn₂(oba)₄ paddle-wheel secondary building unit. Each SBU is linked by oba to form a distorted 4⁴ 2D network. Two identical 4⁴ nets interpenetrate to form a layered structure. The bpy acts as a linker between the paddle-wheel units from two adjacent layers to yield a highly stable 3D framework (Fig. 1a). The structure contains 1D open channels running along both the a and b axes. For 1, the strong vibrations at 1600 and 1590 cm⁻¹ correspond to the asymmetric stretching vibration of the carboxylate group coordinated to the cation, whereas it's symmetric stretching vibrations appear at 1415 and 1371 cm⁻¹ (Fig. 1b). The difference in frequency between asymmetric and symmetric stretching vibration is more than 200 cm⁻¹ indicating the bidentate-bridging coordination mode of the

carboxylate group [37]. The powder XRD pattern of the resulting ultrasound synthesized product (Fig. 1c) agrees well with the literature value [38]. Moreover, the sonochemically as-prepared **1** was also monitored by TG analysis (Fig. 1d). The weight loss of the guest molecule (DMF) started at 250 °C and the framework was stable up to 400°C, before it collapsed, implying the good thermal stability of this MOF. The morphology and sizes of nanostructures prepared using US techniques are dependent on various parameters such as the concentration of initial reagents [39]. In order to investigate the role of this parameter on the morphology and size of the MOF, **1** sample prepared by the US method using a different concentration of initial reagents were characterized by scanning electron microscopy (SEM). Fig. 2 shows the SEM of the MOF prepared in different concentrations of initial reagents of 0.01, 0.02 and 0.04 M using constant US generator power of 50W for 1 h irradiation time. A comparison between the samples with different concentrations shows that high concentrations of initial reagents decreased the particle size (Fig. 2c, d). Interestingly, the size of **1** particle formed without US irradiation is much larger than that with US irradiation (Fig. 2e, f). In addition, no formation of nanostructures was confirmed. From these results, it is suggested that US cavitation affects the formation of small and uniform **1** nanostructures [40]. Such a size difference is commonly observed in sonochemistry [41]. One explanation is that the fast kinetics does not permit the growth of the nuclei, and in each collapsing bubble a few nucleation centers are formed whose growth is limited by the short collapse [18].

Hg(II) Adsorption Studies.

Ultrasonic-assisted adsorption of Hg(II) ions from aqueous solutions using **1** MOF were studied to find the optimal ions initial concentration, adsorbent dosage, pH and contact time. All experiments were carried out at room temperature at various conditions, according to the designed experiments. Moreover, Our MOF displayed a significantly high adsorption capacity for Hg²⁺ ions.

Effect of pH

The absorption process strongly depends on pH. First, 50 ppm of mercury (II) was prepared to investigate the absorption property with **1**. 0.01 g of adsorbent was added to 50 ml of mercury (II)-containing solution in separate containers. At low pH, competition between mercury (II) and hydrogen ions for placement on adsorbent sites decreases the absorption rate. By increasing the pH of the solution, the effect of the competition of Hg²⁺ and H⁺ is reduced and, as a result, more mercury (II) is absorbed. At higher pH, the amount of H⁺ ion decreased and at pH=5, the maximum amount of mercury (II) adsorption was reached (Fig. 3a).

Study of Sorption Kinetics

To study the sorption mechanism, which governs the sorption procedure, and to estimate whether the sorption mechanism can be considered as a physical or chemical mechanism, various adsorption models, such as intraparticle diffusion, pseudo-first-order, and pseudo-second-order models, were applied to investigate the adsorption data. A high value of correlation coefficient of pseudo-second-order model was achieved for Hg(II) ions ($R^2 = 0.99$ for **1**), which indicated that this adsorption model is more fitted with the sorption data than the pseudo-first-order model (Fig. 4). These results demonstrate that the pseudo-second-order

model displays a more satisfactory correlation in comparison with the pseudo-first-order model for the sorption of Hg^{2+} metal ions, suggesting that the sorption process was predominantly controlled by chemical reactions between the metal ions and the adsorption sites of the MOF [42-44]. The kinetic parameters of **1** were evaluated by exploring the impact of various contact times on $\text{Hg}(\text{II})$ sorption. As shown in Fig. 3b fast kinetics was obtained in less than 30 min. The Weber-Morris intraparticle diffusion model was then used to better identify the diffusion mechanism. This model can be ascribed to the mass transfer steps in the Hg^{2+} ions adsorption onto adsorbents. The plots of Q_t versus $t^{1/2}$ in the range of the calculated adsorption give a nonlinear curve, which did not pass through the origin ($C \neq 0$), and describes that the intraparticle diffusion mechanism is not the only rate-determining step (Fig. 3b). The initial portion can be assigned to boundary layer diffusion, and the second portion with a lower slope indicated the slow adsorption step, where the intraparticle diffusion is involved in the sorption process, but it is not the only rate-determining step. The initial portion with a larger slope has a faster rate than the second portion. Also, the second part represents the equilibrium level.

Adsorption Isotherm

To achieve significant data for the judicious design of a favorable sorption system, the adsorption tests were performed in seven different initial concentrations (between 5 and 120 ppm) with 10 mg of adsorbent and then stirred for 30 min at ambient temperature. To evaluate the efficacy of the sorption process, sorption models, namely, Freundlich and Langmuir's models were employed (Fig. 4c,d). Monolayer adsorption is defined by the Langmuir model upon the homogeneous surface of the adsorbent and represented as: (3) Whereas multilayer adsorption is described by the Freundlich model upon the heterogeneous surface of sorbent material and illustrated as:

$$q_e = K_F C_e^{1/n} \quad (4)$$

Where C_e (mg L^{-1}) is the ion concentration at equilibrium, b (L mg^{-1}) is devoted to the energy of the sorption process, q_m (mgg^{-1}) points to the maximum sorption capacity obtained for monolayer sorption, and K_F is the Freundlich constant. Langmuir model is a better model to explain the adsorption isotherm based on R^2 values. As shown in Fig. 4c,d the maximum sorption capacity of **1** for $\text{Hg}(\text{II})$ ions was 338 mgg^{-1} . The **1** reveals outstanding adsorption performance due to its large adsorption capacity.

Effect of Adsorbent Dosage

Adsorbent dosage had an inverse effect on the adsorption capacity. Because, at higher adsorbent dosage, the ratio of adsorbing concentration to adsorbent sites is lower, which caused decreasing adsorption capacity.

Investigation of Comparative Adsorption

Ligands display very fast adsorption and highly efficient capacity for $\text{Hg}(\text{II})$ removal. In addition, the comparative sorption tests were performed for various metal ions. Cd^{2+} , CO^{2+} , Hg^{2+} , Cr^{+3} , As^{3+} , Ni^{2+} , Fe^{3+} , Cu^{2+} , and Al^{3+} metal ions were used to study the adsorption

performance by this MOF. As illustrated in Fig. 3(c), for the compound Hg(II), was adsorbed more efficiently in comparison to other metal ions.

Reusability Study

To investigate the reusability of this MOF, three adsorption-desorption cycles were accomplished. Satisfactory results were obtained as illustrated in Fig. 3d. The desorption process was performed by adding 2 mL of deionized water to the adsorbent, and the solution was stirred for 20 min at ambient temperature. The amounts of total Hg(II) metal ions were then determined by ICP-AES. The percentage of adsorption obtained after three cycles shows that MOF **1** is reusable in absorbing metal ions.

Antibacterial Activity

The antibacterial activity is measured from the inhibition zone. In the present work, *Escherichia coli* (a gram-negative bacteria) and *Staphylococcus aureus* (a gram-positive bacteria), were used as the biological agents. This is shown in Fig 5(a) and (b). The results demonstrated a relationship between the $[\text{Zn}_2(\text{oba})_2(\text{bpy})]$ (**1**) concentration and antibacterial activity. Kirby–Bauer disk diffusion susceptibility test was used to measure the antibacterial activity of **1**. Colonies of each strain of *E. coli* and *S. aureus* were cultured overnight on trypticase soy agar medium and transferred through a loop in a sterilized test tube containing 5 mL sterilized the normal saline solution. The mixture was completely mixed. Then, uniform suspensions of bacteria with 0.5 McFarland turbidity standards were cultured by swab on Muller Hinton agar. To prepare the disks, 50 mg mL^{-1} synthesized material was added to sterilized blank disks and left for 2 days the prepared, materials on the paper disks, completely. The disks were then seeded onto the plate at appropriate time intervals and incubation was carried out, at 37°C for 18 h. Then, the zones of bacterial inhibition were measured. Zn^{2+} is readily released from the **1**. structure in water and interacts with the bacterial membrane. **1**, therefore acts as a Zn ion reservoir. Moreover, the structure undergoes gradual degradation, providing sustained ion release. However, the antibacterial test for both bacteria was shown an excellent effect against *E. coli* and *S. aureus* [45-47].

Conclusions

In summary, $[\text{Zn}_2(\text{oba})_2\text{bpy}]$ (**1**) metal-organic framework was synthesized using an organic linker $\text{H}_2\text{oba} = 4,4\text{-oxybisbenzoic acid}$ and $\text{bpy} = 4,4\text{-bipyridine}$, with the target of absorbing mercury(II) ions from water. The results of the absorption experiments showed that the framework has a similar function in absorbing and separating of mercury (II) ions. Also, the maximum absorption capacity for this framework was 338 mgg^{-1} for **1**, in less than 30 minutes. Also, in comparison with the previous report, **1** displayed a higher adsorption capacity for Hg^{2+} removal performance. Due to the inability of most adsorbents to absorb metal ions at low initial concentrations, the framework **1** provided acceptable performance. These results indicate that the $\text{H}_2\text{oba} = 4,4\text{-oxybisbenzoic acid}$ and $\text{bpy} = 4,4\text{-bipyridine}$ ligands based framework can be considered an adsorbent for the treatment of sewage to recover environmental health. model. This work displays to remove Hg^{2+} ions from pollutant water under 30 min effectively. The antibacterial activities of $[\text{Zn}_2(\text{oba})_2\text{bpy}]$ (**1**) were tested against gram-positive and gram-

negative species. The as-prepared **1** exhibited excellent antibacterial effectiveness against *E. coli* and *S. aureus*.

Acknowledgments

Support of this investigation by Iran University of Science and Technology and Iran's National Elites Foundation is gratefully acknowledged.

References

- [1] X. Zhang, T. Xia, K. Jiang, Y. Cui, Yu Yang, G Qian, Highly sensitive and selective detection of mercury (II) based on a zirconium metal-organic framework in aqueous media, *Jour of Solid State Chem.*, 253 (2017) 277-281.
- [2] X-Y. Xu and B. Yan, Fabrication and application of a ratiometric and colorimetric fluorescent probe for Hg²⁺ based on dual-emissive metal-organic framework hybrids with carbon dots and Eu³⁺, *Jour Mater Chem C.*, 4(2016)1543-1570.
- [3] P. Samanta, A. V. Desai, S. Sharma, P. Chandra, and S K. Ghosh, Selective Recognition of Hg²⁺ ion in Water by a Functionalized Metal–Organic Framework (MOF) Based Chemodosimeter, *Inorg. Chem.*, 57 (2018) 2360–2364.
- [4] P. Wu, Y. Liu, Y. Liu, J. Wang, Y. Li, W. Liu, and J. Wang, Cadmium-Based Metal–Organic Framework as a Highly Selective and Sensitive Ratiometric Luminescent Sensor for Mercury(II), *Inorg. Chem.*, 54 (2015)11046-11048.
- [5] D. Mustafa, E. Breynaert, S.R. Bajpe, J.A. Martens, C.E. Kirschhock, Stability improvement of Cu₃(BTC)₂ metal-organic frameworks under steaming conditions by encapsulation of a Keggin polyoxometalate, *Chem. Comm.*, 47 (2011) 8037-8039.
- [6] M.S. Tehrani, R. Zare-Dorabei, Highly efficient simultaneous ultrasonic-assisted adsorption of methylene blue and rhodamine B onto metal-organic framework MIL-68 (Al): central composite design optimization, *RSC Adv.*, 6 (2016) 27416-27425.
- [7] X.-j. Hu, Y.-g. Liu, H. Wang, G.-m. Zeng, X. Hu, Y.-m. Guo, T.-t. Li, A.-w. Chen, L.-h. Jiang, F.-y. Guo, Adsorption of copper by magnetic graphene oxide-supported β-cyclodextrin: Effects of pH, ionic strength, background electrolytes, and citric acid, *Chem. Eng. Res. and Des.*, 93 (2015) 675-683.
- [8] M.S. Tehrani, R. Zare-Dorabei, Competitive removal of hazardous dyes from aqueous solution by MIL-68 (Al): derivative spectrophotometric method and response surface methodology approach, *Spectrochim. Acta Part A*, 160 (2016) 8-18.
- [9] J.U.K. Oubagaranadin, Z. Murthy, Adsorption of divalent lead on a montmorillonite– illite type of clay, *Ind . & Eng. Chem. Res.*, 48 (2009) 10627-10636.
- [10] L. Esrafil, V. Safarifard, E. Tahmasebi, M. Esrafil, A. Morsali, Functional group effect of isoreticular metal-organic frameworks on heavy metal ion adsorption, *New J. Chem.*, 42 (2018) 8864-8873.
- [11] E. Tahmasebi, M.Y. Masoomi, Y. Yamini, A. Morsali, Application of mechanosynthesis azine-decorated zinc (II) metal-organic frameworks for highly efficient removal and extraction of some heavy metal ions from aqueous samples: a comparative study, *Inorg. Chem.*, 54 (2014) 425-433.
- [12] Y.Y. Xiong, H.Q. Wu, F. Luo, The MOF⁺ Technique: A Potential Multifunctional Platform, *Chem.: Eur. J.*, 24 (2018) 13701-13705.

- [13] H.-G. Jin, W. Zong, L. Yuan, X.-B. Zhang, Nanoscale zeolitic imidazole framework-90: selective, sensitive and dual-excitation ratiometric fluorescent detection of hazardous Cr(VI) anions in aqueous media, *New J. Chem.*, 42 (2018) 12549-12556.
- [14] T.-T. Zheng, J. Zhao, Z.-W. Fang, M.-T. Li, C.-Y. Sun, X. Li, X.-L. Wang, Z.-M. Su, A luminescent metal-organic framework with high sensitivity for detecting and removing copper ions from simulated biological fluids, *Dalton Trans.*, 46 (2017) 2456-2461.
- [15] Y.Y. Xiong, J.Q. Li, L. Le Gong, X.F. Feng, L.N. Meng, L. Zhang, P.P. Meng, M.B. Luo, F. Luo, Using MOF-74 for Hg²⁺ removal from ultra-low concentration aqueous solution, *J. Solid State Chem.*, 246 (2017) 16-22.
- [16] R.J. Kuppler, D.J. Timmons, Q.-R. Fang, J.-R. Li, T.A. Makal, M.D. Young, D. Yuan, D. Zhao, W. Zhuang, H.-C. Zhou, Potential applications of metal-organic frameworks, *Coord. Chem. Rev.*, 253 (2009) 3042-3066.
- [17] S. Kazemi, V. Safarifard, Carbon dioxide capture in MOFs: The effect of ligand functionalization, *Polyhedron*, 154 (2018) 236-251.
- [18] E. Moradia, R. Rahimib, V. Safarifardc, Sonochemical synthesis of fabrication nanoporous metal-organic framework base on tetrakis (4-carboxyphenyl) porphyrin (TCPP) linker, MDPI AG., 2017.
- [19] M. Eddaoudi, J. Kim, N. Rosi, D. Vodak, J. Wachter, M. O'Keeffe, O.M. Yaghi, Systematic design of pore size and functionality in isorecticular MOFs and their application in methane storage, *Science.*, 295 (2002) 469-472.
- [20] L.E. Kreno, K. Leong, O.K. Farha, M. Allendorf, R.P. Van Duyne, J.T. Hupp, Metal-organic framework materials as chemical sensors, *Chem. Rev.*, 112 (2011) 1105-1125.
- [21] E. Khezerloo, S.M. Mousavi-khoshdel, V. Safarifard, Sensitive and selective detection of metal ions and small molecules in aqueous media using a hydrolytically stable amide-functionalized metal-organic framework, *Polyhedron*, 166 (2019) 166-174.
- [22] M. Tanhaei, A.R. Mahjoub, V. Safarifard, Energy-efficient sonochemical approach for the preparation of nanohybrid composites from graphene oxide and metal-organic framework, *Inorg. Chem. Commun.*, 102 (2019) 185-191.
- [23] Y. Zhao, M. Seredych, Q. Zhong, T.J. Bandosz, Superior performance of copper-based MOF and aminated graphite oxide composites as CO₂ adsorbents at room temperature, *ACS Appl. Mater. Interfaces*, 5 (2013) 4951- 4959.
- [24] J.A. Johnson, Design and Synthesis of Novel Octacarboxy Porphyrinic Metal-Organic Frameworks, in, The University of Nebraska-Lincoln, 2016.
- [25] P. Horcajada, R. Gref, T. Baati, P.K. Allan, G. Maurin, P. Couvreur, G. Ferey, R.E. Morris, C. Serre, Metal-organic frameworks in biomedicine, *Chem. Rev.*, 112 (2011) 1232-1268.
- [26] M.Y. Masoomi, A. Morsali, Applications of metal-organic coordination polymers as precursors for the preparation of nano-materials, *Coord. Chem. Rev.*, 256 (2012) 2921-2943.
- [27] E. Moradi, R. Rahimi, V. Safarifard, Sonochemically synthesized microporous metal-organic framework representing unique selectivity for detection of Fe³⁺ ions, *Polyhedron*, 159 (2019) 251-258.
- [28] F. Zare, M. Ghaedi, A. Daneshfar, The headspace solid-phase microextraction of polycyclic aromatic hydrocarbons in environmental water samples using silica fiber modified by self-assembled gold nanoparticles, *Anal. Methods*, 7 (2015) 8086-8093.

- [29] M. Roosta, M. Ghaedi, A. Daneshfar, R. Sahraei, Ultrasound-assisted microextraction-nano material solid-phase dispersion for extraction and determination of thymol and carvacrol in pharmaceutical samples: Experimental design methodology, *J. Chromatogr. B*, 975 (2015) 34-39.
- [30] A. Asfaram, M. Ghaedi, S. Hajati, A. Goudarzi, Synthesis of magnetic γ -Fe₂O₃-based nanomaterial for ultrasonic-assisted dyes adsorption: modeling and optimization, *Ultrason. Sonochem.*, 32 (2016) 418-431.
- [31] K.S. Suslick, Y. Didenko, M.M. Fang, T. Hyeon, K.J. Kolbeck, W.B. McNamara III, M.M. Mdleleni, M. Wong, Acoustic cavitation and its chemical consequences, *Philosophical Transactions of the Royal Society of London. Series A: Mathematical, Phy. Eng. Sci.*, 357 (1999) 335-353.
- [32] R. Zare-Dorabei, S.M. Ferdowsi, A. Barzin, A. Tadjarodi, Highly efficient simultaneous ultrasonic-assisted adsorption of Pb (II), Cd (II), Ni (II) and Cu (II) ions from aqueous solutions by graphene oxide modified with 2, 2'-dipyridylamine: central composite design optimization, *Ultrason. Sonochem.*, 32 (2016) 265-276.
- [33] S. Dashamiri, M. Ghaedi, K. Dashtian, M.R. Rahimi, A. Goudarzi, R. Jannesar, Ultrasonic enhancement of the simultaneous removal of quaternary toxic organic dyes by CuO nanoparticles loaded on activated carbon: central composite design, kinetic and isotherm study, *Ultrason. Sonochem.*, 31 (2016) 546-557.
- [34] M. Jamshidi, M. Ghaedi, K. Dashtian, S. Hajati, A. Bazrafshan, Sonochemical assisted the hydrothermal synthesis of ZnO: Cr nanoparticles loaded activated carbon for simultaneous ultrasound-assisted adsorption of ternary toxic organic dye: derivative spectrophotometric, optimization, kinetic and isotherm study, *Ultrason. Sonochem.*, 32 (2016) 119-131.
- [35] F.N. Azad, M. Ghaedi, K. Dashtian, S. Hajati, V. Pezeshkpour, Ultrasonically assisted hydrothermal synthesis of activated carbon–HKUST-1-MOF hybrid for efficient simultaneous ultrasound-assisted removal of ternary organic dyes and antibacterial investigation: Taguchi optimization, *Ultrason. Sonochem.*, 31 (2016) 383-393.
- [36] M. Jamshidi, M. Ghaedi, K. Dashtian, A. Ghaedi, S. Hajati, A. Goudarzi, E. Alipanahpour, Highly efficient simultaneous ultrasonic-assisted adsorption of brilliant green and eosin B onto ZnS nanoparticles loaded activated carbon: artificial neural network modeling and central composite design optimization, *Spectrochim. Acta A*, 153 (2016) 257-267.
- [37] K. Nakamoto, *Infrared and Raman Spectra of Inorganic and Coordination Compounds*, fifth ed., John Wiley and Sons, New York, 1997.
- [38] S. Pramanik, C. Zheng, X. Zhang, T.J. Emge, J. Li, *J. Am. Chem. Soc.* 133 (2011) 4153.
- [39] J. Kim, S.-T. Yang, S.B. Choi, J. Sim, J. Kim, W.-S. Ahn, *J. Mater. Chem.* 21 (2011) 3070.
- [40] X. Zhou, H. Li, H. Xiao, L. Li, Q. Zhao, T. Yang, J. Zuo, W. Huang, *Dalton Trans.* 42 (2013) 5718.
- [41] A. Gedanken, *Ultrason. Sonochem.* 11 (2004) 47.
- [42] J. Li, X. Wang, G. Zhao, C. Chen, Z. Chai, A. Alsaedi, T. Hayat, X. Wang, Metal-organic framework-based materials: superior adsorbents for the capture of toxic and radioactive metal ions, *Chem. Soc. Rev.*, 47 (2018) 2322-2356.
- [43] J. Li, Y. Wu, F. Song, G. Wei, Y. Cheng and C. Zhu, A highly selective and sensitive polymer-based OFF-ON fluorescent sensor for Hg²⁺ detection incorporating salen and perylenyl moieties, *Jour of Mater Chem.*, 22 (2012) 478-483.

- [44] J. Wang, W. Zhang, X. Yue, Q. Yang, F. Liu, Y. Wang, D. Zhang, Z. Li, J. Wang, One-pot synthesis of multifunctional magnetic ferrite–MoS₂–carbon dot nanohybrid adsorbent for efficient Pb (II) removal, *J. Mater. Chem. A*, 4 (2016) 3893-3900.
- [45] K. Singbumrung, K. Motina, P. Pisitsak, P. Chitichotpanya, S. Wongkasemjit, and T. Inprasit, Preparation of Cu-BTC/PVA Fibers with Antibacterial Applications, *Fibers and Polymers*, 19 (2018) 1373-1378.
- [46] H. Nabipour, B. Soltani, N. Ahmadi Nasab, Gentamicin Loaded Zn₂(bdc)₂(dabco) Frameworks as Efficient Materials for Drug Delivery and Antibacterial Activity, *Jour of Inorg and Organometal Poly and Mater*, 28 (2018) 1206–1213.
- [47] H. Nabipour, M. Hossaini Sadr, and G. Rezanejade Bardajee, Release behavior, kinetic and antimicrobial study of nalidixic acid from [Zn₂(bdc)₂(dabco)] metal-organic frameworks, *Jour of Coord Chem*, 70 (2017) 2771-2784.

Figures

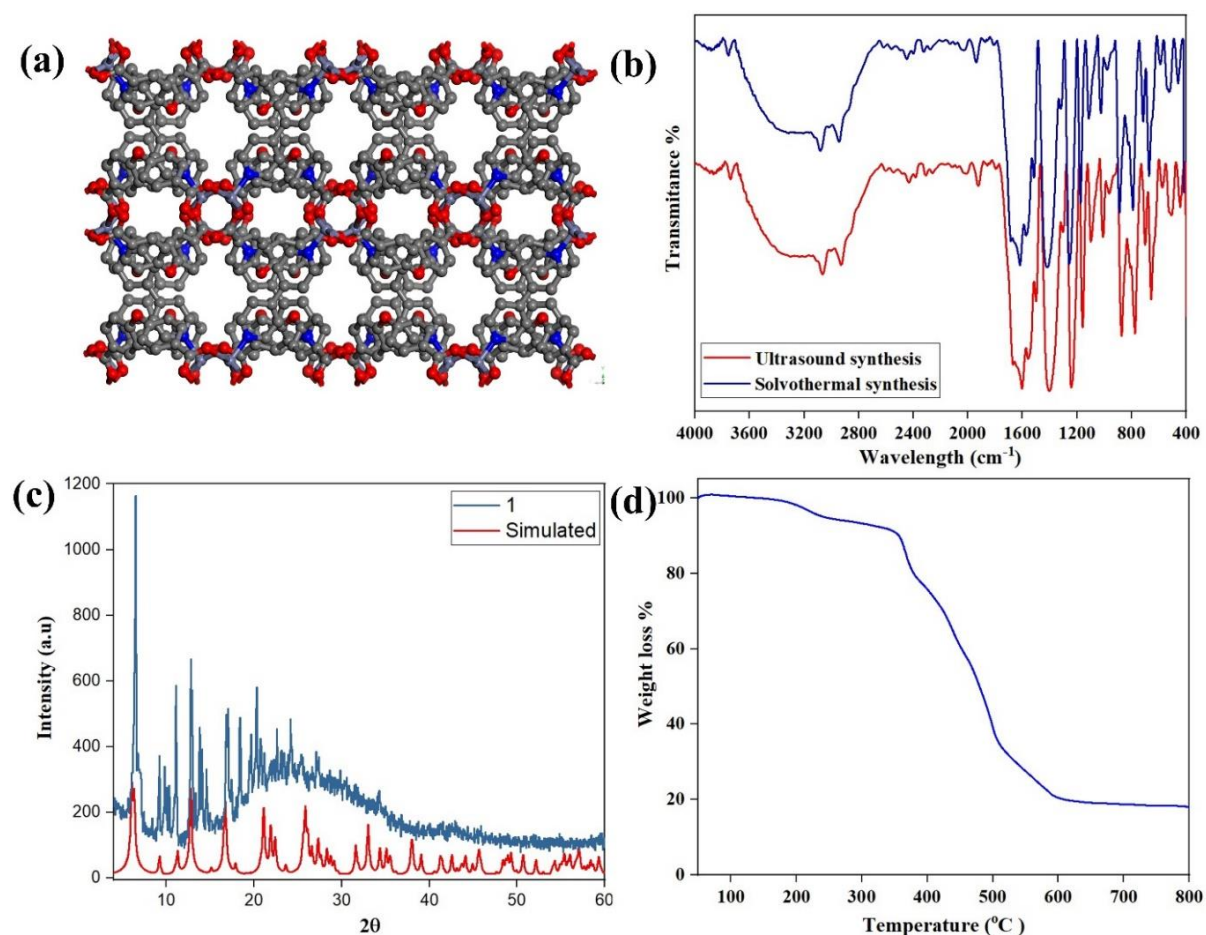


Figure 1. (a) Crystal structure of the 3D framework [Zn₂(oba)₂(bpy)] (**1**), showing the 1D channels running along the *a* axis (The disordered guest molecules are omitted for clarity). (b) FT-IR spectra of sonochemical (red) and solvothermal (blue) synthesized **1**. (c) PXRD of as-synthesized (blue) and simulated (red) [Zn₂(oba)₂(bpy)] (**1**). (d) TGA of activated [Zn₂(oba)₂(bpy)] (**1**).

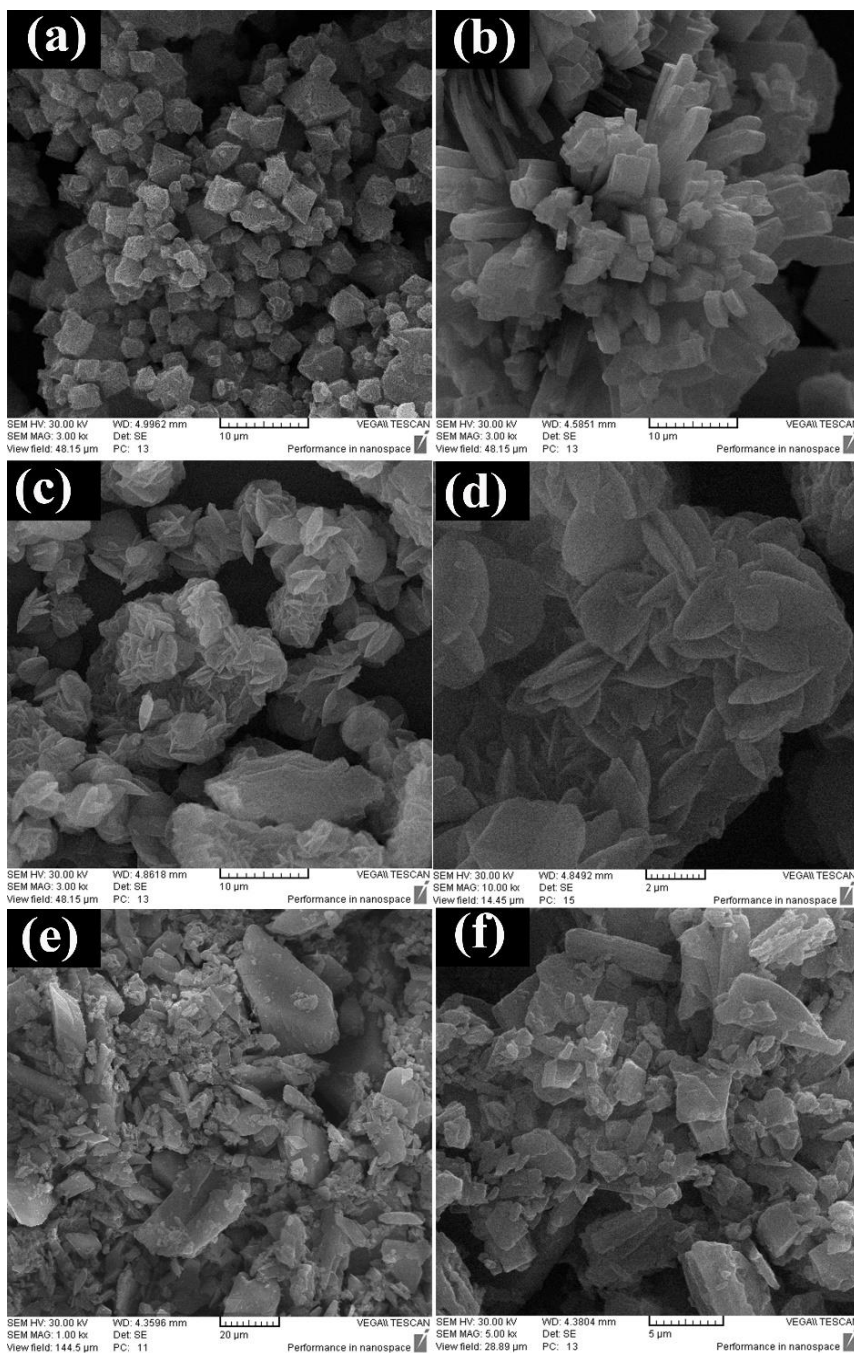


Figure 2. SEM images of $[Zn_2(oba)_2(bpy)]$ (**1**) nanostructures prepared by US generator power of 50W at 1 h irradiation time in different concentration of initial reagents (a) 0.01 M, (b) 0.02 M and (c, d) 0.04 M. (e, f) SEM image of **1** bulk powder formed via solvothermal reaction without ultrasonic irradiation.

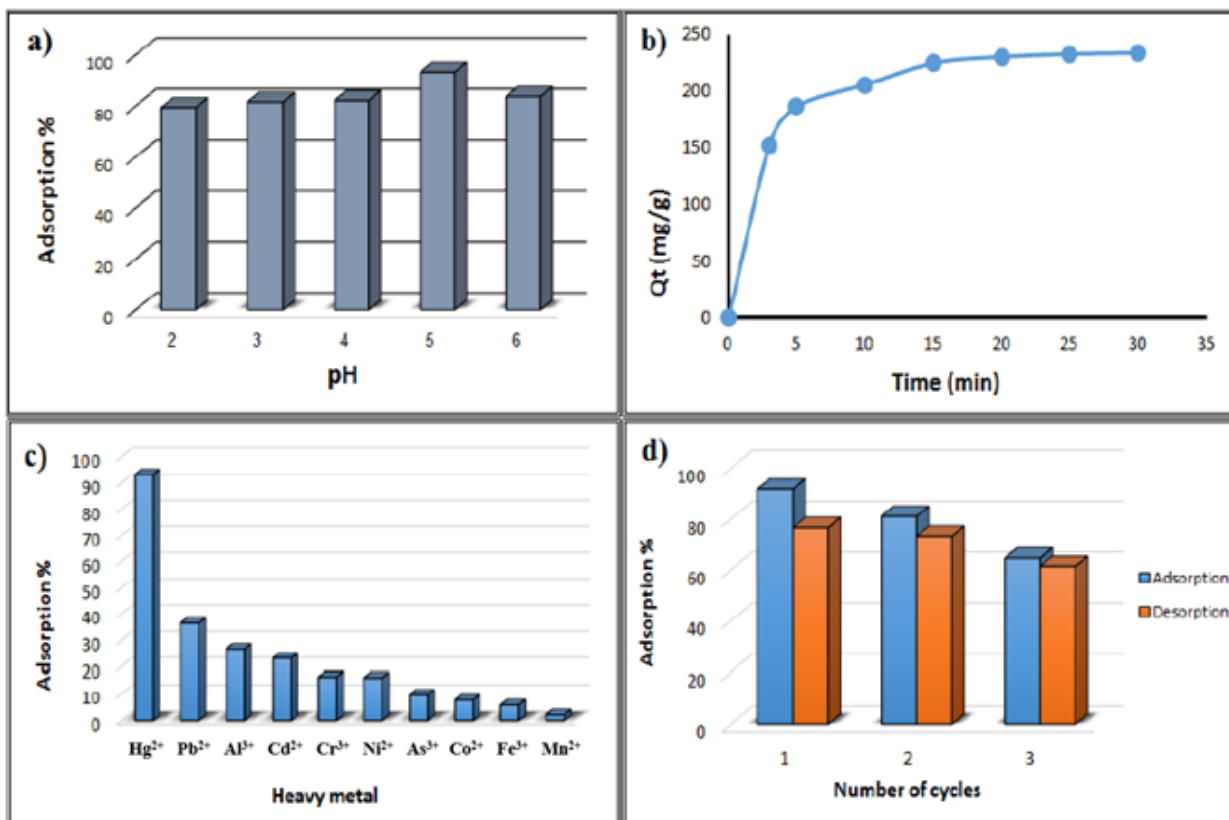


Figure 3. (a) pH solution effect on Hg(II) adsorption efficiency, (b) Effect of various contact time on Hg(II) sorption, (c) Comparative adsorption of different heavy-metal ions and (d) adsorption-desorption cycles of [Zn₂(oba)₂(bpy)] (1). (The percentage of desorption was calculated based on the amount of adsorption).

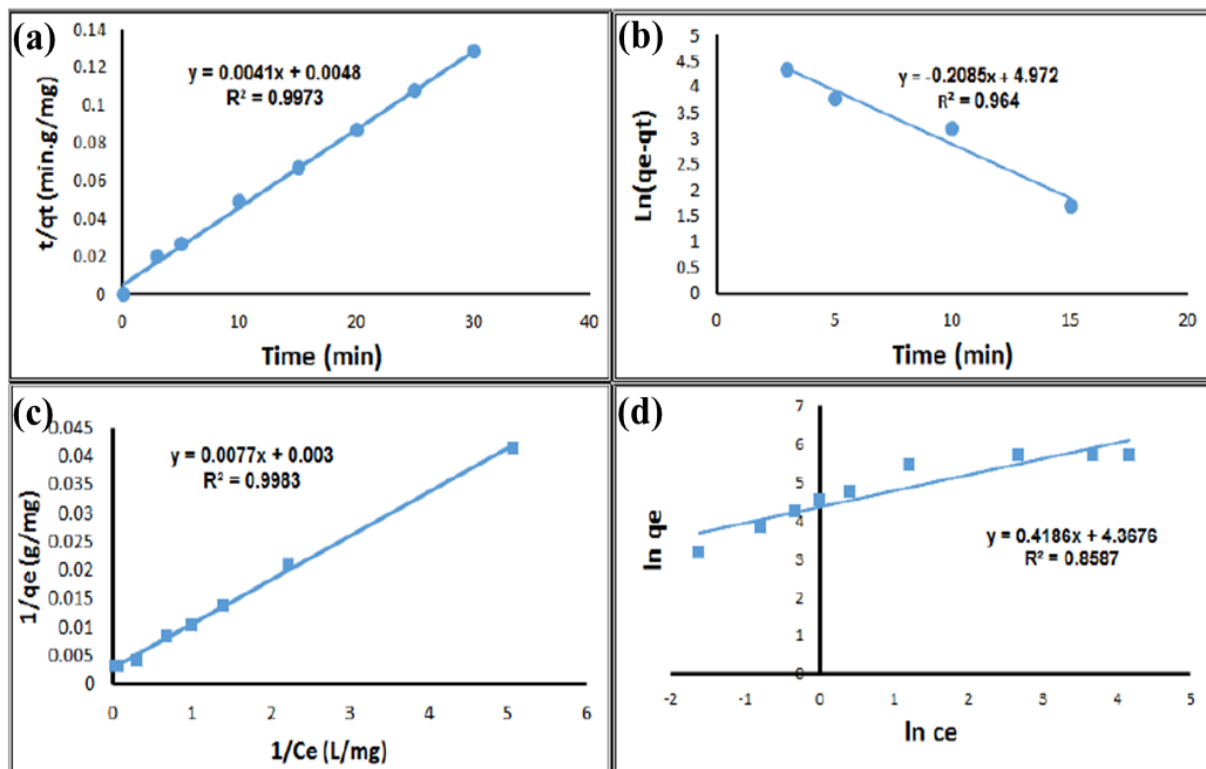


Figure 4. (a) Pseudo-second-order and (b) Pseudo-First-order kinetics model of Hg^{2+} adsorption on $[\text{Zn}_2(\text{oba})_2(\text{bpy})]$ (1), (c) Linear curve fitting with the Langmuir model and (d) Linear curve fitting with Freundlich model for Hg^{2+} for $[\text{Zn}_2(\text{oba})_2(\text{bpy})]$ (1).

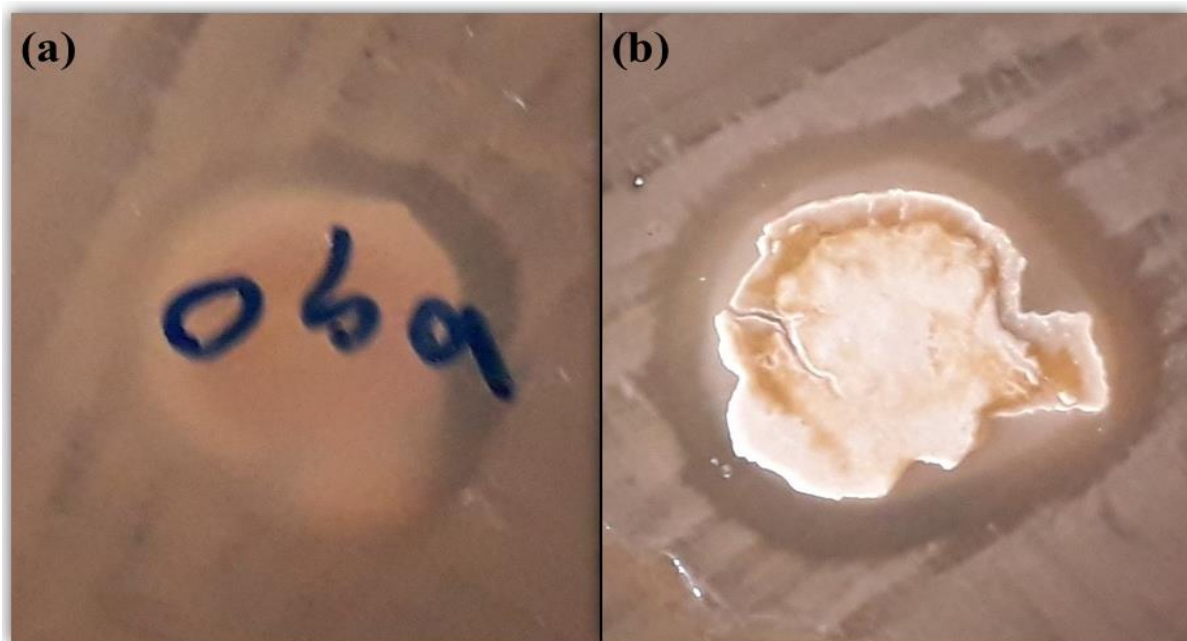


Figure 5. The antibacterial activity zone of inhibition with [Zn₂(oba)₂(bpy)] (**1**) powders, for different bacterial strains: (a) *E. coli* (b) *S. aureus*.

Highlights

- Sonochemically microporous metal-organic framework $[\text{Zn}_2(\text{oba})_2(\text{bpy})]$ (**1**) were synthesized
- $[\text{Zn}_2(\text{oba})_2(\text{bpy})]$ (**1**) MOF showed the maximum absorption of Hg^{2+} ions at PH=5
- The absorption kinetics was followed by the pseudo-second-order model
- The adsorption isotherm was followed by the Langmuir model
- The maximum absorption capacity for this framework was 338 mgg^{-1} for $[\text{Zn}_2(\text{oba})_2(\text{bpy})]$ (**1**), in less than 30 minutes
- The antibacterial activity study of $[\text{Zn}_2(\text{oba})_2(\text{bpy})]$ (**1**)