

Type of the Paper (Abstract, Meeting Report, Preface, Proceedings, etc.)

Design of biologically active surfaces based on functionalized polysulfones by electrospinning [†]

Anca Filimon ^{1*}, Nicolae Olaru ¹, Florica Doroftei ¹, Cristian Logigan ², and Simona Dunca ³

¹ "Petru Poni" Institute of Macromolecular Chemistry, 41A Grigore Ghica Voda Alley, 700487 Iasi, Romania; capataanca@yahoo.com

² Chemical Company SA, 14 Chimiei Bvd., Iasi, Romania

³ "Alexandru Ioan Cuza" University of Iasi, Biology Faculty, 11 Carol I Bvd., 700506 Iasi, Romania

* Correspondence: capataanca@yahoo.com; Tel.: +40-232-217-454

† Presented at the 23rd International Electronic Conference on Synthetic Organic Chemistry, 15 November -15 December 2019.

Received: date; Accepted: date; Published: date

Abstract: Development of a new generation of electrospun polymeric materials designed to accomplish multi-performance in a bioinspired integrated system represents main goal of the present research. Polysulfones promise to become such nanosize fibrous structures with attractive properties associated with biomedical applications by the development of a new "construct". Therefore, the homogeneous solutions of the functionalized polysulfones with quaternary ammonium groups (PSFQ) dissolved in various solvents were processed by electrospinning to create of polymeric scaffolds that can modulate cellular behavior. Additionally, the antibacterial activity of PSFQ fibers against Gram-negative and Gram-positive bacteria has indicated the potential of these scaffolds for biomedical use.

Keywords: quaternized polysulfones; electrospinning; nanofibrous scaffolds; biomedical applications

1. Introduction

The topic on nanofibers has been attracted attention both in the scientific community and industries because of their unique performances. Literature [1-3] indicates different techniques for the fabrication of nanomaterials, including drawing-processing, template-assisted synthesis, self-assembly, solvent casting, phase separation, and electrospinning techniques. With the increasing knowledge about nanotechnology, electrospinning has become preferred technique over solvent casting and phase-separation because nanofibers achieved with electrospinning possess a high surface area to volume ratio and large number of inter-/intra fibrous pores [4]. Current trends in industrial research on such new materials have opened the way for advancements in diverse fields such as biomedicine, bioengineering, environmental protection [5-8]. The notable applications include in tissue engineering, biosensors, filtration, wound dressings, drug delivery, and enzyme immobilization [9]. In this direction, research awareness is rapidly growing and attracting greater attention to fabricate nanostructures from various types of raw materials, ranging from natural and synthetic polymers to composites, which can find applications in almost every field. The nanofibrous mats produced by this technique mimics the nanoscale properties of native extracellular matrix components much closely as compared to the conventional techniques. It is well-known that almost all tissues and organs, i.e., skin, cartilage, and bone, etc., show a kind of similarity to nanosize fibrous structures. In this context, polysulfones promise to become such generation of nanofibrous scaffolds with attractive properties associated with biomedical applications.


A variety of polysulfones (PSFs) have been molecularly designed [10-12] to enhance their performance, becoming biologically inert and nontoxic compounds, exhibiting stable mechanical, morphological and adhesion characteristics during their exploitation. In this context, the cationic polyelectrolytes containing quaternary ammonium side groups (PSFQ) belong to this group of compounds which have many useful characteristics, such as hydrophilicity and high water permeability (of a special interest for biomedical applications) [13], biocompatibility and antibacterial activity [14,15], and better separation [16]. Based on the above-mentioned properties, has been found that these polymers have numerous applications as biomaterials and semipermeable membranes in a variety of fields, including textile, food, cosmetics, chemical, and pharmaceutical industries.

Recently, the technology of high-performance materials fabrication has advanced significantly by the development of new materials with nanoscale properties. Thus, electrospun nanofibers play an important role in the biomedical field, the fact determined by numerous articles which highlight their importance in the area of biomaterials. Additionally, the electrospun nanofibers scaffolds can be tailored in accordance with the purpose of their use. For example, such hybrid nanofibers scaffolds play an important role in providing a familiar environment to the cells, which ultimately results in their better attachment, proliferation, and differentiation [17,18]. Similarly, electrospun nanofibers scaffolds are also used as a drug delivery carrier for carrying drugs to their target sites [19,20]. Beside, biomedical application, electrospun nanofiber has also found application in the protection of environment (both air and water) as affinity membrane [21,22]. Electrospun nanofiber could also be used for producing high-surface-area chemical and biological nanosensors [23,24]. Furthermore, ultrafine electrospun nanofiber scaffolds had also been used for the preparation of nanotubes, which are of prime importance in various industries [25]. Consequently, the production of nanomaterials (nanofibers) via electrospinning, lead to significantly improvement of design material used and implicitly, of achieved nanomaterials. In this context, the solutions of the functionalized polysulfone, with a tunable density of quaternary ammonium functional groups, were processed by electrospinning to create the new materials with high-performance characteristics - biologically active surfaces - designed to be integrated in a bioinspired system in medical therapy. Therefore, the present study includes two challenges, namely the processing of quaternized polysulfones solutions, by electrospinning to obtain fibers scaffolds and extending the possible applications of these materials in biomedical field. Thus, we examine the effects of solutions and processing parameters, and solvents properties on fiber morphology and the impact of this efficient technology in the biomedical field.

2. Experimental

2.1. Materials

Commercial aromatic polysulfone in powder form (UDEL-3500 – PSF, Union Carbide Company, Texas) ($M_n=39,000$ g/mol; $M_w/M_n=1.625$) was used in the synthesis of functionalized polysulfones [10-12]. Thus, the cationic polysulfone containing quaternary ammonium side groups (PSFQ, $M_n=28,000$ g/mol) was synthesized by the reaction of chloromethylated polysulfone (CMPSF with a content in chlorine of 7.42% and $M_n=29,000$ g/mol) with a tertiary amine, N,N-dimethylbutylamine (DMBA) [12,26]. The quaternary polymer was isolated from the reaction medium by precipitation in diethylether, washed 3 times with diethylether, and dried for 48 h under vacuum, at room temperature. The general chemical structure of the quaternized polysulfone is illustrated in Scheme I.

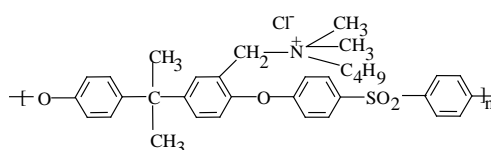

Scheme I. Chemical structure of the monomer units of the polysulfone with quaternary groups (PSFQ).

2.2. Processing of PSFQ solutions by electrospinning

The PSFQ homogeneous solutions for electrospinning were prepared by dissolving the polymer in N,N-dimethylformamide (DMF) and 2-Methoxyethanol (2-MOEt) at room temperature. The polymer solutions concentration of 40% was chosen to obtain fibers with sizes in the sub-micrometer range. Electrospinning was carried out at normal laboratory conditions. Around 3 mL PSFQ solution was electrospun under to applied voltage potential of 15-20 kV with a needle tip-collector distance of 15 cm and flow rate of the solution through the syringe of 0.75 mL/h. An aluminum rotary disc was used as collector for PSFQ fibers.

2.3. Scanning electron microscopy

The morphology of electrospun fibers was investigated using an environmental scanning electron microscope (ESEM), Quanta 200 operating at an accelerating voltage of 20 kV with secondary electrons in low vacuum mode.

2.4. Antibacterial testes

The *in vitro* antibacterial activity of electrospun PSFQ assessed on two bacteria strains, by the diffusion method (Kirby-Bauer) certificated by the National Committee on Clinical Laboratory Standards (NCCLS), was evidenced by the occurrence of an inhibition zone. The Gram-positive *Staphylococcus aureus* ATCC 25923 (*S. aureus*) and the Gram-negative bacteria *Escherichia coli* ATCC 10536 (*E. coli*) were used as test microorganisms. The preincubation conditions of the test bacteria were 37°C for 18 h.

Plates with Müeller-Hinton-Broth medium (pH 7.3 at 25°C) were uniformly inoculated with the test microorganism using a sterile cotton swab. Circular polysulfones fibers, 10 mm in diameter were applied on the surface of the medium. The plates were incubated at 37°C for 24 h. The diameter of the inhibition zone (mm) depends both on the polymer present on the medium as well as by the microorganism susceptibility. Finally, the diameter of the inhibition clear zone was measured with a ruler.

3. Results and Discussion

3.1. Effects of Parameters on Electrospinning

Literature [27,28] mentions that, there are several factors that affect the electrospinning process. These factors are classified as electrospinning parameters (the applied electric field, distance between the needle and collector, flow rate, and needle diameter), solution (the solvent, polymer concentration, viscosity, and solution conductivity) and environmental parameters (relativity humidity and temperature). All of these parameters directly influence the electrospinning process, affecting the generation of smooth and bead-free electrospun fibers. Therefore, to gain a better understanding of the electrospinning technique and fabrication of polymeric nanofibers, it is essential to thoroughly understand the effects of all of these governing parameters.

The electrospinning process begins when electric charges move into the polymer solution via the metallic needle. This causes instability within the polymer solution as a result of the induction of charges on the polymer droplet. At the same time, the reciprocal repulsion of charges produces a force that opposes the surface tension, and ultimately the polymer solution flows in the direction of the electric field (Figure 1). A further increase in the electric field causes the spherical droplet to deform and assume a conical shape. At this stage, ultrafine nanofibers emerge from the conical polymer droplet (Taylor cone), which are collected on the metallic collector kept at an optimized distance.

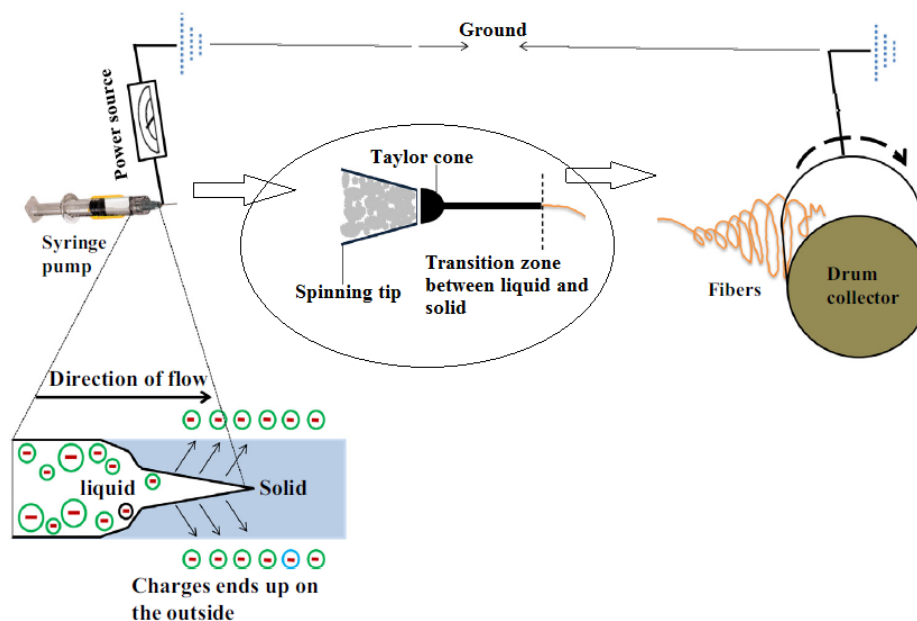


Figure 1. Schematic depicting electrospinning setup and phenomenon of electrospinning.

A stable charge jet can be formed only when the polymer solution has sufficient cohesive force. During the process, the internal and external charge forces cause the whipping of the liquid jet in the direction of the collector. This whipping motion allows the polymer chains within the solution to stretch and slide past each other, which results in the creation of fibers with diameters small enough to be called nanofibers [29,30].

Based on these remarks, in particular, the electrospinning of the PSFQ solutions was carried out and continuous cylindrical fibers were obtained in the experiments. The morphology of the PSFQ electrospun fibers was examined by SEM, with representative images shown in Figures 2 and 3.

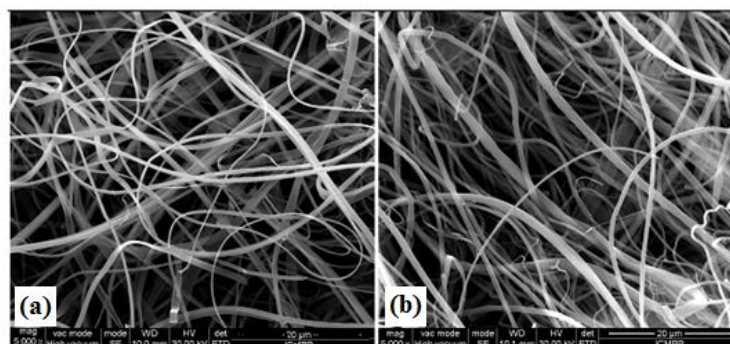


Figure 2. SEM images of PSFQ fibers obtained in: DMF (a) and 2-MOEt (b) at 40% polymer concentration for 50 μm scan area and magnification of 2000x.

Results suggested that long, uniform and continuous fibers can be obtained without any beads structure, which exhibit a smooth surface with variations in diameters. Fibers morphology, by different forms and dimensions, can be explained in terms of the different solution properties, (i.e., the boiling point of the solvents, the viscosity, and the surface tension) and intramolecular repulsive interactions between the ionized groups (i.e., ammonium groups). Thus, SEM images show that the morphology of fibers electrospun from PSFQ solution in DMF for a concentration of 40% (Figure 2a) with different forms and dimensions (average fibers diameters was 1.60 μm) can be explained in terms of the various solution properties, namely the boiling point of the solvents, the viscosity, and the surface tension. On the other hand, the fibers obtained from PSFQ solution of 40% in 2-MOEt have a wide distribution of diameters, ranging from 0.65 μm to 2.40 μm (Figure 2b). This fact shows

that, changes of surface and characteristics of nanofibers (e.g., increases in the diameter) are attributed the effect of the concentration/viscosity of polymer solutions, including the surface tension and conductivity, according to Fong et al. [28].

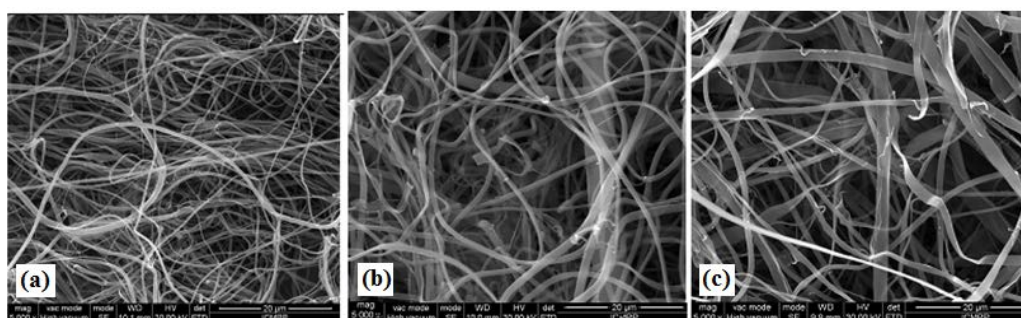


Figure 3. SEM images of PSFQ fibers obtained in various mixing ratios of solvents: 75DMF/25 2-MOEt (a), 50DMF/50 2-MOEt (b), 25DMF/75 2-MOEt 2-MOEt (c) at 40% concentration for 50 μm scan area and magnification of 2000x.

Therefore, usually, two things need to be kept in mind before selecting the solvent, namely first, the preferred solvents for electrospinning process have polymers that are completely soluble and second the solvent should have a moderate boiling point [31]. Thus, the effects of the solvent and/or solvents system in conjunction with the applied voltage affect the morphology of nanofibers (Figures 2 and 3). Moreover, the formation of smaller-diameter nanofibers is attributed to the stretching of the polymer solution in correlation with the charge repulsion within the polymer jet, following to with an increase in the applied voltage [32].

3.2. Antibacterial Activity

Growing resistance of microorganisms - disease-causing microbes - to drug therapy are an increasing public health problem. For this reason, has renewed a great interest towards investigating bactericidal properties of polymeric materials, as an alternative. Therefore, there is an urgent need to develop new bactericides. In this sense, quaternary ammonium groups represent one of the most popular types of antimicrobial agent, which affect structural organization and integrity of the cytoplasmic membrane [33]. Their biological activity depends on their structure and physicochemical properties which affects the interaction with the cytoplasmic membrane of bacteria and influences their cell metabolism.

In particular, the antibacterial activity of PSFQ fibers obtained in DMF and 2-MOEt for 40% polymer concentration, was investigated against Gram-positive *Staphylococcus aureus* and the Gram-negative *Escherichia coli* bacteria. Tests performed to assess the antibacterial activity of fibers electrospun against the two types of bacteria showed a significant antibacterial activity (Figure 4). Results were assessed semi-quantitatively by the agar diffusion method against both bacteria, with a higher activity against *Staphylococcus aureus* as compared to *Escherichia coli*. This fact can be explained take in account the specific compositions of the cell wall of Gram negative (*E. coli*) and Gram-positive (*S. aureus*) bacteria which induce different antimicrobial activity. Thus, from literature [34], it is known that the component of Gram-positive bacteria cell walls (peptidoglycan) confers the hydrophobic character of *S. aureus*, while the major constituent of Gram-negative bacteria cell walls (peptidoglycan, together with other membranes, such as lipopolysaccharides and proteins) ensures the hydrophilic character of *E. coli*. Therefore, inhibition of the hydrophilic *E. coli* to the hydrophilic PSFQ fibers is lower than the inhibition of hydrophobic *S. aureus* cells. Moreover, the PSFQ fibers obtained in DMF, with the smaller diameters (around 1.60 μm), inhibit the growth of microorganisms and the inhibition becoming stronger against *S. aureus*.

Consequently, all these aspects indicate that the antibacterial activity depends not only on the substituent groups of the quaternized polysulfones, fiber organization during the electrospinning process, but also on the bacterial cell membrane characteristics.

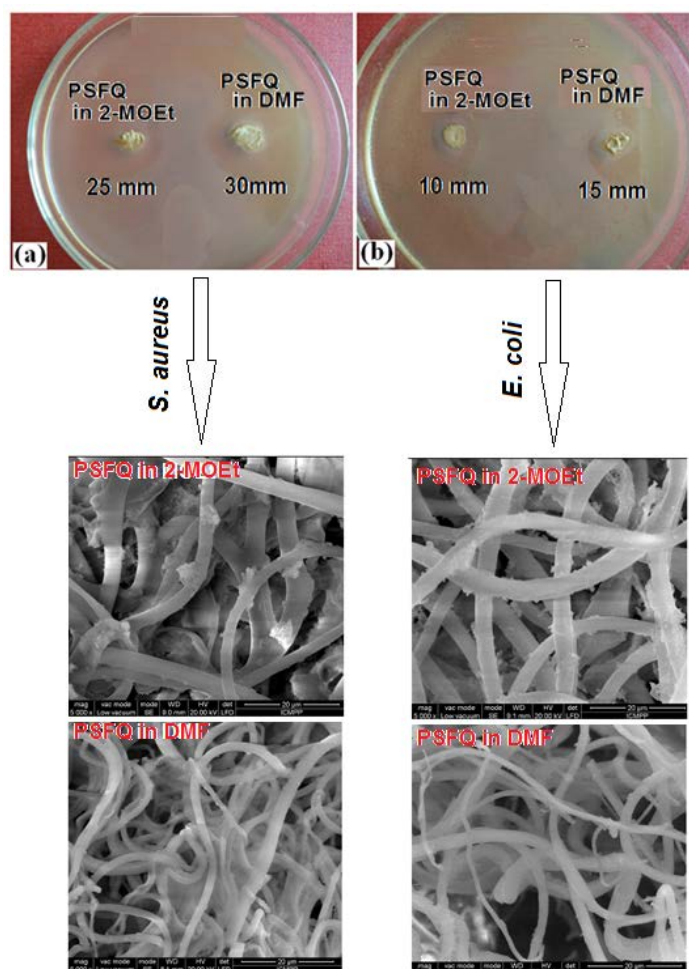


Figure 4. Antibacterial testes for PSFQ fibers obtained from solutions in DMF and 2-MOEt at 40% polymer concentration, against *S. aureus* (a) and *E. coli* (b). SEM images of PSFQ fibers after inoculated of bacteria for 50 μm scan area and magnification of 2000x.

4. Conclusions

Processing of the functionalized polysulfones with quaternary ammonium groups (PSFQ) solutions to obtain new materials with high-performance characteristics - biologically active surfaces - designed to be integrated in a bioinspired system in medical therapy, was carried out by electrospinning. Thus, long, uniform, and continuous fibers without any beads structure, which exhibit a smooth surface with variations of diameters were obtained. Fibers morphology with different forms and dimensions can be explained in terms of the various electrospinning parameters, solution properties and environmental parameters, as well as the intramolecular repulsive interactions between the ionized groups (i.e., ammonium groups). Additionally, certain inhibitory effects of PSFQ electrospun fibers on the growth of *S. aureus* and *E. coli* bacteria have been observed.

The antimicrobial activity of polysulfones with quaternary ammonium groups is considered to be one of the most important properties, directly related to new possible applications and this indicates that the PSFQ fibers are potential materials for biomedical applications. Consequently, the electrospinning it proved to extend the possible applications of quaternized polysulfones by preparing continuous fine fibers with characteristics which recommend them for applications in biomedical fields.

Author Contributions: Anca Filimon and Nicolae Olaru have designed the experiments (processing of polysulfones solutions by electrospinning), discussed and validated the obtained data and wrote the paper. Florica Doroftei has performed the scanning electron microscopy measurements. Simona Dunca has investigated the effectiveness of nanofibers as biocides through antibacterial assays. Cristian Logigan has accomplished the characterization of the synthesized polysulfones.

Funding: The financial support of European Social Fund for Regional Development, Competitiveness Operational Programme Axis 1 – Project "Petru Poni Institute of Macromolecular Chemistry - Interdisciplinary Pol for Smart Specialization through Research and Innovation and Technology Transfer in Bio(nano)polymeric Materials and (Eco)Technology", InoMatPol (ID P_36_570, Contract 142/10.10.2016, cod MySMIS: 107464) is gratefully acknowledged.

Acknowledgments: We thank to Dr. Ecaterina Avram (1950–2016), Department of Functionalized Polymers, "Petru Poni" Institute of Macromolecular Chemistry, Iasi, Romania, for the polysulfones synthesis.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Lim, S.K.; Lee, S.-K.; Hwang, S.-H.; Kim, H. Photocatalytic deposition of silver nanoparticles onto organic/inorganic composite nanofibers. *Macromol. Mater. Eng.* **2006**, *291*, 1265–1270.
2. Peng, Y.; Dong, Y.; Fan, H.; Chen, P.; Li, Z.; Jiang, Q. Preparation of polysulfone membranes via vapor-induced phase separation and simulation of direct-contact membrane distillation by measuring hydrophobic layer thickness. *Desalination* **2013**, *316*, 53–66.
3. Yongquan, D.; Ming, W.; Lin, C.; Mingjun, L. Preparation, characterization of P(VDF-HFP)/[bmim]BF₄ ionic liquids hybrid membranes and their pervaporation performance for ethyl acetate recovery from water. *Desalination* **2012**, *295*, 53–60.
4. Reneker, D.H., Fong, H. *Polymeric Nanofiber*; American Chemical Society Publishers: Washington, 2006; pp. 1–6.
5. Chen, L., Bromberg, L., Hatton, T.A., Rutledge, G.C. Catalytic hydrolysis of p-nitrophenyl acetate by electrospun polyacrylamidoxime nanofibers. *Polymer* **2007**, *48*, 4675–4682.
6. Shang, L., Yu, Y., Liu, Y., Chen, Z., Kong, T., Zhao, Y. Spinning and applications of bioinspired fiber systems. *ACS Nano* **2019**, *13*, 2749–2772.
7. Katepalli, H., Bikshapathi, M., Sharma, C.S., Verma, N., Sharma, A. Synthesis of hierarchical fabrics by electrospinning of PAN nanofibers on activated carbon microfibers for environmental remediation applications. *Chem. Eng. J.* **2011**, *171*, 1194–1200.
8. Kijenska, E., Prabhakaran, M.P., Swieszkowski, W., Kurzydowski, K.J., Ramakrishna, S. Electrospun bio-composite P(LLACL)/collagen I/collagen III scaffolds for nerve tissue engineering. *J. Biomed. Mater. Res. B: Appl. Biomater.* **2012**, *100B*, 1093–1102.
9. Bhardwaj, N., Kundu, S.C. Electrospinning: A fascinating fiber fabrication technique. *Biotechnol. Adv.* **2010**, *28*, 325–347.
10. Avram, E., Butuc, E., Luca, C., Druta, I. Polymers with pendent functional groups. III. Polysulfone containing viologen group. *J. Macromol. Sci. Pure Appl. Chem.* **1997**, *34*, 1701–1714.
11. Avram, E. Polymers with pendent functional groups. VI. A comparative study on the chloromethylation of linear polystyrene and polysulfone with paraformaldehyde/Me₃SiCl. *Polym. Plast. Technol. Eng.* **2001**, *40*, 275–281.
12. Luca, C., Avram, E., Petrariu, I. Quaternary ammonium polyelectrolytes. V. Amination studies of chloromethylated polystyrene with N,N-dimethylalkylamines. *J. Macromol. Sci. Part A* **1988**, *25*, 345–361.
13. A. Filimon, E. Avram, S. Dunca, Surface and interface properties of functionalized polysulfones: cell-material interaction and antimicrobial activity, *Polym. Eng. Sci.* **55** (2015) 2184–2194.
14. Miculescu, M., Thakur, V.K., Miculescu, F., Voicu, S.I. Graphene-based polymer nanocomposite membranes: A review. *Polym. Adv. Technol.* **2016**, *27*, 844–859.
15. Perreault, F., Tousley, M.E., Elimelech, M. Thin-film composite polyamide membranes functionalized with biocidal graphene oxide nanosheets. *Environ. Sci. Technol. Lett.* **2014**, *1*, 71–76.
16. Filimon, A., Stoica, I., Onofrei, M.D., Bargan, A., Dunca, S. Quaternized polysulfones-based blends: Surface properties and performance in life quality and environmental applications. *Polym. Test.* **2018**, *71*, 285–295.

17. Noh, H. K., Lee, S. W., Kim, J. M., Oh, J. E., Kim, K. H., Chung, C. P., Choi, S. C., Park, W. H., Min, B. M. Electrospinning of chitin nanofibers: degradation behavior and cellular response to normal human keratinocytes and fibroblasts. *Biomaterials* **2006**, *27*, 3934-3944.
18. Haider, A., Gupta, K.C., Kang, I.-K. Morphological effects of HA on the cell compatibility of electrospun HA/PLGA composite nanofiber scaffolds. *BioMed Res. Int.* **2014**, Article ID 308306, 1-11.
19. Wu, J., Xie, L., Lin, W.Z.Y., Chen, Q. Biomimetic nanofibrous scaffolds for neural tissue engineering and drug development. *Drug Discov. Today* **2017**, *22*, 1375-1384.
20. Wei, G., Ma, P.X. Nanostructured biomaterials for regeneration. *Adv. Funct. Mater.* **2008**, *18*, 3566-3582.
21. Subramanian, S., Seeram, R. New directions in nanofiltration applications—are nanofibers the right materials as membranes in desalination? *Desalination* **2013**, *308*, 198-208.
22. Feng, C., Khulbe, K.C., Matsuura, T., Tabe, S., Ismail, A.F. Preparation and characterization of electro-spun nanofiber membranes and their possible applications in water treatment. *Sep. Purif. Technol.* **2013**, *102*, 118-135.
23. Baharifar, H., Honarvarfard, E., Malek-kheili, M.H., Maleki, H., Barkhi, M., Ghasemzadeh, Ali., Khoshnevisan, K. The potentials and applications of cellulose acetate in biosensor technology. *Nanomed. Res. J.* **2017**, *2*, 216-223.
24. Wang, S., Li, S., Yu, Y. Immobilization of cholesterol oxidase on cellulose acetate membrane for free cholesterol biosensor development. *Artif. Cell. Blood Sub. Biotechnol.*, **2004**, *32*, 413-425.
25. Huang, Z.-M., He, C.-L., Yang, A., Zhang, Y., Han, X.-J., Yin, J., Wu, Q. Encapsulating drugs in biodegradable ultrafine fibers through co-axial electrospinning. *J. Biomed. Mater. Res., Part A* **2006**, *77*, 169-179.
26. Filimon, A., Dobos, A. M., Avram, E. Ionic transport processes in polymer mixture solutions based on quaternized polysulfones. *J. Chem. Thermodyn.* **2017**, *106*, 160-167.
27. Huang, Z., Zhang, Y., Kotaki, M., Ramakrishna, S. A review on polymer nanofibers by electrospinning and their applications in nanocomposites. *Compos. Sci. Technol.* **2003**, *63*, 2223-2253.
28. Fong, H., Reneker, D.H. *Structure Formation in Polymeric Fibers*; Hanser: Munich, Germany, 2001.
29. Bae, H.-S., Haider, A., Selim, K.M.K., Kang, D.-Y., Kim, E.-J., Kang, I.-K. Fabrication of highly porous PMMA electrospun fibers and their application in the removal of phenol and iodine. *J. Polym. Res.* **2013**, *20*, 1-7.
30. Haider, S., Al-Zeghayer, Y., Ahmed Ali, F., Haider, A., Mahmood, A., Al-Masry, W., Imran, M., Aijaz, M. Highly aligned narrow diameter chitosan electrospun nanofibers. *J. Polym. Res.* **2013**, *20*, 1-11.
31. Kanani, A. Gholipour, Bahrami, S.H., Effect of changing solvents on poly(e-caprolactone) nanofibrous webs morphology. *J. Nanomater.* **2011**, Article ID 724153, 1-10.
32. Sill, T.J., von Recum, H.A. Electrospinning: applications in drug delivery and tissue engineering. *Biomaterials* **2008**, *29*, 1989-2006.
33. Muñoz-Bonilla, A., Cerrada, M., Fernández-García, M. *Polymeric Materials with Antimicrobial Activity: From Synthesis to Applications*; Royal Society of Chemistry Thomas Graham House: Milton Road, Cambridge, UK, 2013.
34. Ong, Y.-L., Razatos, A., Georgiou, G., Sharma, M.M. Adhesion forces between E. coli bacteria and biomaterial surface. *Langmuir* **1999**, *15*, 2719-2725.

