

2 The relationship between the degree of conversion in dental di- 3 methacrylate polymers determined by infrared spectroscopy 4 and polymerization shrinkage[†]

5 Marta Chrószcz ^{1,*}, Izabela Barszczewska-Rybarek ¹ and Promise Wori ¹6 ¹ Department of Physical Chemistry and Technology of Polymers, Silesian University of Technology, Strzody
7 9, 44-100 Gliwice; izabela.barszczewska-rybarek@polsl.pl

8 * Correspondence: marta.chroszcz@polsl.pl

9 † Presented at the 2nd International Electronic Conference on Applied Sciences, 15-31.10.2021; Available
10 online: <https://asec2021.sciforum.net/>.

11 **Abstract:** In this work, the relationship between the degree of conversion (DC) in the Bis-
12 GMA/TEGDMA polymer networks, determined by two methods – Fourier transform infrared spec-
13 troscopy (DC_{IR}) and polymerization shrinkage (DC_S), was studied. The DC_{IR} was calculated by using
14 the internal standard method, whereas the DC_S was calculated by measuring differences in the mon-
15 omer and polymer densities, resulting in the polymerization shrinkage. Both methods revealed the
16 same trend in the DC changes with alterations in the Bis-GMA/TEGDMA ratio. However, the DC_S
17 values were lower, in comparison to the DC_{IR} values on average by 18 %.

18 **Keywords:** dental resin composite, dimethacrylate composite matrix, degree of conversion, Fourier
19 transform infrared spectroscopy, polymerization shrinkage

21 1. Introduction

22 The degree of conversion (DC) is the most useful parameter in the characterization
23 of dental composite restorative materials based on dimethacrylates. Its value informs
24 about curing efficiency. If the curing level is insufficient, the physicochemical and me-
25 chanical properties of the composite can significantly deteriorate [1]. Inadequate curing
also decreases the biocompatibility of the material, due to an increase in free monomer
content, which tends to leach from the composite matrix [2,3].

It is known from the literature that the DC depends on the monomer chemical struc-
ture [1,3,4]. Monomers of highly elastic molecules polymerize to higher DCs, whereas
those of stiff molecules polymerize to lower DCs. In particular, bisphenol A glycerolate
dimethacrylate (Bis-GMA), the most important and commonly used dental monomer, has
a stiff and spacious molecule, willing to form hydrogen bonds, which cause a serious DC
limitation. Therefore, it can achieve a limiting DC of 39 % when homopolymerized [4]. It
is the major drawback of Bis-GMA because the DC below 55 % is not acceptable in prac-
tical applications [5]. To achieve a sufficiently high DC, Bis-GMA has to be copolymerized
with monomers of more elastic and smaller molecules [6,7]. Triethylene glycol dimethac-
rylate (TEGDMA) is the most commonly used in this field. In addition to the monomer
chemical structure, several other factors influence the DC. They include i) initiation
method and initiator type [8,9], ii) irradiation time [7], iii) sample thickness [10], iv) irra-
diation lamp [11], and v) filler type and content [12].

The most popular techniques used for the DC determination include i) Fourier trans-
form infrared spectroscopy (FTIR), ii) Raman spectroscopy (RS), iii) solid-state nuclear
magnetic resonance (ssNMR), and iv) differential scanning calorimetry (DSC).

26 **Citation:** Lastname, F.; Lastname, F;
27 Lastname, F. Title. *Proceedings* 2021,
28 68, x. <https://doi.org/10.3390/xxxxx>

29 Published: date

30
31
32 **Publisher's Note:** MDPI stays neu-
33 tral with regard to jurisdictional
34 claims in published maps and institu-
35 tional affiliations.



36
37
38 **Copyright:** © 2021 by the authors
39 Submitted for possible open access
40 publication under the terms and
41 conditions of the Creative Commons
42 Attribution (CC BY) license
43 (<https://creativecommons.org/licenses/by/4.0/>).

The DC determination method that uses FTIR is the most common, simple, and gives the most reliable results [1]. It is based on the monitoring of changes in the absorption intensity of several bands resulting from vibrations of the C=C double bond, present in the methacrylate group. They include: i) twisting vibrations (816 cm^{-1}), ii) wagging vibrations (948 cm^{-1}), and iii) stretching vibrations (1637 cm^{-1}) [1,13]. The intensity of these bands decreases due to polymerization. As the band located at 1637 cm^{-1} is the most resolved and intense, it is the most commonly used for DC determination [13]. However, to comply with the Beer-Lambert law, the C=C absorption intensity has to be related to the absorption intensity of an internal standard – the band whose absorption intensity does not alter due to the polymerization [14]. The band corresponding to the skeletal stretching vibrations of the C-C bonds in the aromatic ring, located at 1608 cm^{-1} , usually serves as an internal standard [4]. If the system lacks an aromatic ring, the band corresponding to the C=O stretching vibrations, located within 1715 and 1720 cm^{-1} , can be used [4]. However, this method produces underestimated DC values and therefore it is recognized as less reliable compared to that using aromatic internal standard [15,16].

An alternative solution for the DC determination in dimethacrylate composites might be a method based on measuring differences in the monomer and polymer densities resulting from the polymerization shrinkage and calculating its theoretical value (DCs). The calculation of the latter uses the literature information that the molar volume of one mole of the methacrylate group decreases by 22.5 cm^3 [17] due to polymerization, in the course of which van der Waals forces that occur between monomer molecules turn into covalent bonds that constitute crosslinks of hardened composite matrix [1]. This method has already been applied in the survey on the DC of dimethacrylate systems, however, its reliability has not yet been established.

In this study, a series of dimethacrylate copolymers consisted of various Bis-GMA/TEGDMA various ratios were subjected to FTIR and polymerization shrinkage analyses to determine the DC and relationship between the results from both methods.

2. Materials and Methods

2.1. Materials

Bis-GMA, CQ (camphorquinone), DMAEMA (dimethylaminoethyl methacrylate), and TEGDMA were purchased from Sigma Aldrich (St. Louis, MO, USA).

2.2. Sample preparation

Seven Bis-GMA/TEGDMA mixtures were prepared. The Bis-GMA weight fraction ranged from 20 to 80 % and increased by 10 % each time. TEGDMA content decreased proportionally. The mixtures were admixed with the 0.4 wt.% CQ and 1 wt.% DMAEMA that was a photoinitiating system, composed of respectively, initiator/and accelerator. Thus prepared compositions were introduced into silicon molds with a diameter of 15 cm and 5 cm thick, covered with PET film to prevent oxygen inhibition, and irradiated with the UV-VIS lamp (Ultra Vitalux 300, Osram, Munich, Germany, 280 to 750 nm, 2400 mW/cm²) for 1h, from a distance of 15 cm.

2.3. Fourier transform infrared spectroscopy (FTIR)

2.3.1. Instrumentation

FTIR spectra were recorded with the use of Spectrum Two (Perkin-Elmer, Waltham, MA, USA) spectrometer, with 128 scans at resolutions of 1 cm^{-1} . Monomers and polymers were tested as KBr pellets. A thin layer of a monomer was placed between two KBr pellets, whereas a polymer was ground into a fine powder with a grain size smaller than $25\text{ }\mu\text{m}$, mixed with KBr powder, and pressed into a pellet.

2.3.2. Calculation of the degree of conversion (DC_{IR})

The DC_{IR} was calculated with the use of the following equation:

$$DC_{IR}(\%) = \left(\frac{\left(\frac{A_{C=C}}{A_{Ar}} \right)_{polymer}}{\left(\frac{A_{C=C}}{A_{Ar}} \right)_{monomer}} \right) \times 100, \quad (1)$$

where $A_{C=C}$ is the absorption intensity of the band resulting from the carbon-carbon double bond stretching vibrations, located at 1637 cm^{-1} , and A_{Ar} is the absorption intensity of the internal standard – the band resulting from the skeletal stretching vibrations of the carbon-carbon bonds in the aromatic rings, located at 1608 cm^{-1} .

2.4. Polymerization shrinkage

2.4.1. Density measurements

Densities of monomers (d_m) were measured with the use of a 1 mL pycnometer, according to the ISO 1675 standard [18]. Densities of polymers (d_p) were determined with the use of an analytical balance (XP balance, Mettler Toledo, Greifensee, Switzerland), equipped with a density determination kit, that uses the Archimedes' principle.

2.4.2. Calculation of the polymerization shrinkage

The experimental polymerization shrinkage (S) was calculated with the use of the following equation:

$$S(\%) = \left(1 - \frac{d_m}{d_p} \right) \times 100, \quad (2)$$

where d_m is the density of a monomer mixture, and d_p is the density of the corresponding polymer.

The theoretical polymerization shrinkage (S_{theor}) was calculated on the assumption that the volumetric shrinkage of one mole of the methacrylate double bonds is equal to 22.5 cm^3 [17], according to the following equation:

$$S_{theor}(\%) = \left(1 - \frac{\frac{MW}{d_m} - 2 \times 22.5}{\frac{MW}{d_m}} \right) \times 100, \quad (3)$$

where MW is the molecular weight of a monomer mixture, d_m is the density of a monomer mixture, 2 is the number of double bonds in the monomer molecule and 22.5 is the volumetric contraction of one mole of the methacrylate group due to its polymerization [17].

2.4.3. Calculation of the degree of conversion (DCs)

The DCs was calculated according to the following equation:

$$DC_S(\%) = \frac{S}{S_{theor}} \times 100, \quad (1)$$

where S is the experimental polymerization shrinkage, and S_{theor} is the theoretical polymerization shrinkage.

3. Results and Discussion

In this study, seven compositions of Bis-GMA and TEGDMA monomers were prepared, polymerized, and characterized for the density, polymerization shrinkage, and degree of conversion. The latter was determined by two methods – Fourier transform infrared spectroscopy and polymerization shrinkage.

The weight ratios of prepared compositions, their molecular weights (MW), concentrations of double bonds (x_{DB}), and densities of the samples, before and after curing, are summarized in Table 1. The x_{DB} values ranged from 4.52 to 6.37 mol/kg. Its value decreased as the Bis-GMA content increased. The percentage difference between the x_{DB} of the B20:T80 and B80:T20 samples was 41 %. As the x_{DB} value informs about the theoretical crosslink density of the dimethacrylate polymer network, it can be said that the greater

the Bis-GMA concentration in the monomer mixture, the lower the crosslink density in the resulting polymer network [1,4,8].

As can be seen from Table 1, the densities of monomer mixtures (d_m) ranged from 1.106 to 1.147 g/cm³. The d_m value increased as the Bis-GMA content increased. The percentage difference between the d_m values determined for the B20:T80 and B80:T20 samples was 4 %. As expected, polymerization resulted in tighter packing, which was reflected in higher densities of cured materials compared to the densities of their uncured counterparts (on average by 7.5 %). The polymer densities (d_p) ranged from 1.194 to 1.233 g/cm³. Its value increased with the increase of the Bis-GMA content up to 70 wt.% and then decreased. The percentage difference between the largest and the smallest d_p values was 3 %. The density values of cured and uncured samples were used to determine the experimental and theoretical polymerization shrinkages (respectively, S and S_{theor}). These results are summarized in Table 2.

Table 1. Sample names, their chemical compositions, and properties: MW – molecular weight, x_{DB} – concentration of double bonds, d_m – density of uncured samples, and d_p – density of cured samples.

Sample name	Weight ratios		MW (g/mol)	x_{DB} (mol/kg)	d_m (g/cm ³)		d_p (g/cm ³)	
	Bis-GMA	TEGDMA			avg.	SD	avg.	SD
B20:T80	20	80	314.07	6.37	1.106	0.024	1.194	0.029
B30:T70	30	70	330.09	6.06	1.113	0.052	1.204	0.025
B40:T60	40	60	347.78	5.75	1.121	0.072	1.207	0.061
B50:T50	50	50	367.51	5.44	1.127	0.046	1.210	0.014
B60:T40	60	40	389.60	5.13	1.133	0.062	1.219	0.016
B70:T30	70	30	414.50	4.83	1.141	0.094	1.233	0.033
B80:T20	80	20	442.81	4.52	1.147	0.135	1.216	0.019

Table 2. The theoretical (S_{theor}) and experimental polymerization shrinkage (S) as well as the degree of conversion, calculated from the polymerization shrinkage (DC_s) and absorption intensity (DC_{IR}).

Sample name	S_{theor} (%)	S (%)		DC_s (%)		DC_{IR} (%)	
		avg.	SD	avg.	SD	avg.	SD
B20:T80	15.85	7.39	0.45	46.64	2.32	55.30	5.23
B30:T70	15.17	7.55	0.52	49.81	2.56	60.47	4.78
B40:T60	14.49	7.21	0.41	49.75	2.31	61.01	5.23
B50:T50	13.80	6.89	0.46	49.88	3.04	63.97	3.56
B60:T40	13.09	7.11	0.39	54.33	4.34	64.87	4.87
B70:T30	12.38	7.57	0.55	61.23	3.45	72.83	5.44
B80:T20	11.66	5.44	0.25	46.68	2.98	61.34	5.34

The S values ranged from 5.44 to 7.57 %. They showed no clear trend throughout the studied series. The highest S value was determined for the B70:T30 sample, whereas the lowest S value was determined for the B80:T20 sample. The percentage difference between the largest and smallest S values was 40 %. The S_{theor} values ranged from 11.66 to 15.85 % and decreased with the increase in the Bis-GMA content. This relationship resulted from a decreasing concentration of double bonds in this order, since the lower the concentration of double bonds, the lower the volumetric contraction can occur. The percentage difference between the lowest and highest S_{theor} values was 34 %. S_{theor} and S were further used to determine the DC_s (Table 2). The DC_s values ranged from 46.68 to 61.23 %. It can be seen that the DC_s increased with the increasing Bis-GMA content up to 70 wt.% and then decreased.

The degree of conversion was also examined using the FTIR technique (DC_{IR}). Representative FTIR spectra of the B80:T20 uncured and cured samples are shown in Figure 1. The results obtained for the DC_{IR} are summarized in Table 2. DC_{IR} values ranged from 55.30 to 61.34 %. As can be seen from Table 2, the DC_{IR} values were higher than the corresponding DC_S values. Nevertheless, it is worth noting that a similar tendency was observed in both methods. The DC_{IR} values increased as the Bis-GMA content increased up to 70 % and then decreased when the Bis-GMA content exceeded 70 %. The difference between the DC_S and DC_{IR} values ranged from 15.66 to 23.90 %.

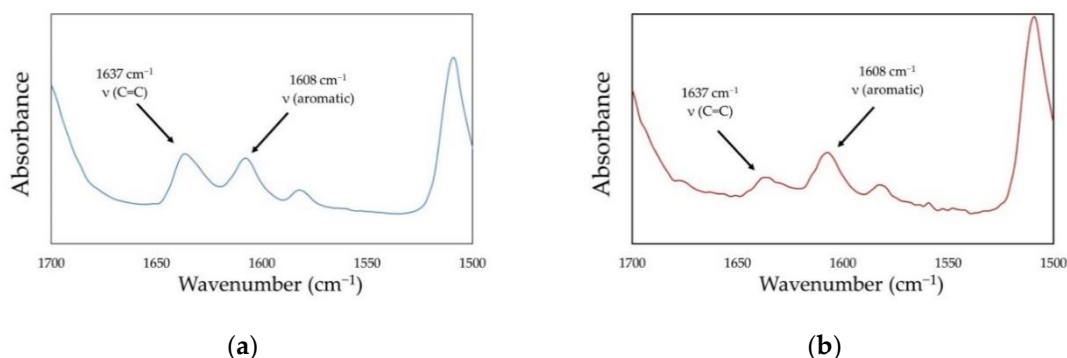


Figure 1. The representative FTIR spectra of the B80:T20 composition in its uncured (a) and cured (b) forms.

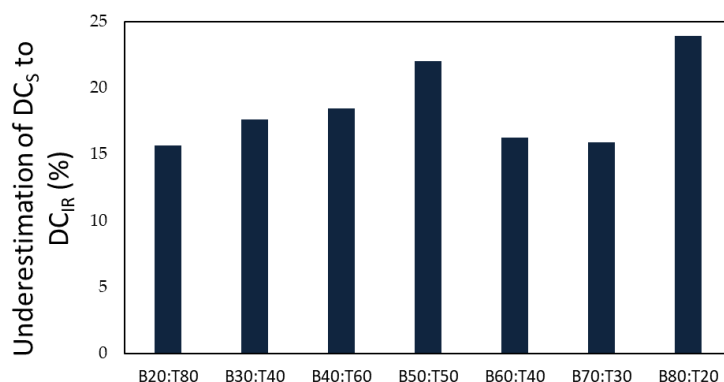


Figure 2. The percentage of underestimation of the DC_S values to the DC_{IR} values.

The underestimation of the DC_S values to the DC_{IR} values can be explained by the fact that the volumetric contraction does not only depend on the concentration of double bonds, but other factors, too, play an essential role in this phenomenon. They include dimensions, shapes, and hydrophilicity of monomer molecules [19]. The Bis-GMA molecule is large, stiff, and hydrophilic. On the contrary, the TEGDMA molecule is small, elastic, and little hydrophilic. By increasing the Bis-GMA content, its molecular features increase their impact on the ability to tight packing. It probably resulted in lower d_p values than expected. In addition, the increase in the Bis-GMA content caused an increase in the viscosity of the monomer mixture, which might increase the inaccuracy of the d_p measurement (the higher the viscosity, the higher the air trapping probability that decreases density). However, the literature shows that the DC_{IR} values calculated with the use of the carbonyl internal standard (instead of the aromatic one) are also underestimated. Collares et al. [16] found that the DC_{IR} values of the Bis-GMA/TEGDMA compositions, determined with the use of carbonyl internal standard, were lower by 23 % in comparison to the DC_{IR} determined with the use of the aromatic internal standard.

4. Conclusions

The methodology of the degree of conversion determination in dimethacrylate polymers based on the measurements of the polymerization shrinkage can be a valuable alternative to the methodology based on the FTIR measurements. It produces underestimated results compared to the methodology using an aromatic internal standard. However, the results achieved with the use of the carbonyl internal standard can be less consistent.

Author Contributions: Conceptualization, I.B.R.; methodology, I.B.R. and M.Ch.; investigation, M.Ch and P.W.; resources, I.B.R. and M.Ch.; data curation, I.B.R., M.Ch. and P.W.; writing—original draft preparation, I.B.R. and M.Ch.; writing—review and editing, I.B.R.; visualization, M.Ch.; supervision, I.B.R.; project administration, I.B.R. All authors have read and agreed to the published version of the manuscript.

Funding: This research received no external funding.

Data Availability Statement: Data supporting reported results are available from the authors.

Conflicts of Interest: The authors declare no conflict of interest. The funders had no role in the design of the study; in the collection, analyses, or interpretation of data; in the writing of the manuscript, or in the decision to publish the results.

References

1. Barszczewska-Rybarek, I.M.; A Guide through the Dental Dimethacrylate Polymer Network Structural Characterization and Interpretation of Physico-Mechanical Properties, *Materials* **2019**, *12*, 4057.
2. Gajewski, V.E.S.; Pfeifer, C.S.; Fróes-Salgado, N.R.G.; Boaro, L.C.C.; Braga, R.R. Monomers used in resin composites: Degree of conversion, mechanical properties and water sorption/solubility. *Braz. Dent. J.* **2012**, *23*, 508–514.
3. Kannurpatti, A.; Anseth, J.; Bowman, C.H.N. A study of the evolution of mechanical properties and structural heterogeneity of polymer networks formed by photo-polymerizations of multifunctional (meth)acrylates. *Polymer* **1998**, *39*, 2507–2513.
4. Sideridou, I.; Tserki, V.; Papanastasiou, G. Effect of chemical structure on degree of conversion in light-cured dimethacrylate-based dental resins. *Biomaterials* **2002**, *23*, 1819–1829.
5. Alshali, R.Z.; Silikas, N.; Satterthwaite, J.D. Degree of conversion of bulk-fill compared to conventional resin-composites at two time intervals. *Dent. Mater.* **2013**, *29*, e213–e217.
6. Dickens, H.; Stansbury, J.W.; Choi, K.M.; Floyd, C.J.E. Photopolymerization kinetics of methacrylate dental resins. *Macromolecules* **2003**, *36*, 6043–6053.
7. Pfeifer, C.S.; Shelton, Z.R.; Braga, R.R.; Windmoller, D.; Machado, J.C.; Stansbury, J.W. Characterization of dimethacrylate polymeric networks: A study of the crosslinked structure formed by monomers used in dental composites. *Eur. Polym. J.* **2011**, *47*, 162–170.
8. Stansbury, J.W. Dimethacrylate network formation and polymer property evolution as determined by the selection of monomers and curing conditions. *Dent. Mater.* **2012**, *28*, 13–22.
9. Barszczewska-Rybarek, I.; Chladek, G. Studies on the curing efficiency and mechanical properties of Bis-GMA and TEGDMA nanocomposites containing silver nanoparticles. *Int. J. Mol. Sci.* **2018**, *19*, 3937.
10. Par, M.; Gamulin, O.; Marovic, D.; Klaric, E.; Tarle, Z. Raman spectroscopic assessment of degree of conversion of bulk-fill resin composites—Changes at 24 hours post cure. *Open. Dent.* **2015**, *40*, e92–e101.
11. Randolph, L.D.; Palin, W.M.; Bebelman, S.; Devaux, J.; Gallez, B.; Leloup, G.; Leprince, J.G. Ultra-fast light-curing resin composite with increased conversion and reduced monomer elution. *Dent. Mater.* **2014**, *30*, 594–604.
12. Halvorson, R.H.; Erickson, R.L.; Davidson, C.L. The effect of filler and silane content on conversion of resin-based composite. *Dent. Mater.* **2003**, *19*, 327–333.
13. Lin-Vien, D.; Colthup, N.B.; Fateley, W.G.; Grasselli, J.G. *The Handbook of Infrared and Raman Characteristic Frequencies of Organic Molecules*; Academic Press: London, UK, 1991; pp. 137–281.
14. Moraes, L.G.; Rocha, R.S.; Menegazzo, L.M.; de Araújo, E.B.; Yukimito, K.; Moraes, J.C. Infrared spectroscopy: A tool for determination of the degree of conversion in dental composites. *J. Appl. Oral. Sci.* **2008**, *16*, 145–149.
15. Barszczewska-Rybarek, I.M. Quantitative determination of degree of conversion in photocured poly(urethane-dimethacrylate)s by FTIR spectroscopy. *J. Appl. Polym. Sci.* **2012**, *123*, 1604–1611.
16. Collares, F.M.; Portella, F.F.; Leitune, V.C.B.; Samuel, S.M.W. Discrepancies in degree of conversion measurements by FTIR. *Braz. Oral. Res.* **2014**, *28*, 9–15.
17. Patel, M.P.; Braden, M.; Davy, K.W.M. Polymerization shrinkage of methacrylate esters. *Biomaterials* **1987**, *8*, 53–56.
18. ISO 1675:1985. *Plastics – Liquid resins – Determination of density by the pycnometer method*; International Standard Organisation: London, UK, 1985.
19. Oliveira, K.M.; Lancellotti, A.C.; Ccahuana-Vásquez, R.A.; Consani, S. Shrinkage stress and degree of conversion of dental composite submitted to different photoactivation protocols. *Acta. Odontol. Latinoam.* **2012**, *25*, 115–122.