

Study of the Stabilizing Agent Influence in the Catalytic Degradation of Methylene Blue using Silver Nanoparticles

Max T. A. Lima¹, Danilo M. M. Figueiredo², Nayally R. S. Marques³, Giovannia A. L. Pereira⁴ and Goreti Pereira^{5,*}

¹ Departamento de Química Fundamental, Universidade Federal de Pernambuco; max.taylo@ufpe.br

² Departamento de Química Fundamental, Universidade Federal de Pernambuco; danilo.matheusmiranda@ufpe.br

³ Departamento de Química Fundamental, Universidade Federal de Pernambuco; nayally.rayany@ufpe.br

⁴ Departamento de Química Fundamental, Universidade Federal de Pernambuco; giovannia.pereira@ufpe.br

⁵ Departamento de Química Fundamental, Universidade Federal de Pernambuco; goreti.pereira@ufpe.br

* Correspondence: goreti.pereira@ufpe.br

Abstract: Inadequate treatment of industrial waste causes the contamination of rivers and seas, impacting Human health and aquatic biodiversity. Among the pollutants are industrial dyes, such as methylene blue (MB), which is toxic in high doses and prevents solar radiation to penetrate the water's surface. To reduce water pollution, the organic dyes could be degraded, generating less harmful and colourless substances. The use of nanoparticles as catalysts has been gaining attention since they have excellent catalytic activity due to their high surface-to-volume ratio. Thus, this work aims to study the use of silver nanoparticles (AgNPs) to degrade MB. AgNPs were prepared in water using the chemical reduction strategy and four different organic stabilizers: sodium citrate, ascorbic acid, polyvinylpyrrolidone, and poly(vinyl alcohol). The MB degradation in the presence of the AgNPs was monitored by UV-Vis absorption spectroscopy. The results showed the formation of AgNPs with a spherical shape for all the stabilizers used. All the AgNPs prepared were efficient

in the degradation of MB, having degraded more than 90%. However, the AgNPs stabilized with sodium citrate and polyvinylpyrrolidone presented the best catalytic performance. Nevertheless, the four AgNPs prepared are potential catalysts for the degradation of organic dyes of wastewater.

Keywords: Organic dyes; Wastewater; Nanocatalysis; Nanomaterials

Citation: Lastname, F.; Lastname, F.; Lastname, F. Title. *Eng. Proc.* **2022**, *4*, x. <https://doi.org/10.3390/xxxxx>

Academic Editor: Firstname Lastname

Published: date

Publisher's Note: MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Copyright: © 2022 by the authors. Submitted for possible open access publication under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Water is the most abundant natural resource on the planet, and good public health largely depends on water readily available for consumption. Accordingly, to the World Health Organization (WHO) 2019 report, 844 million people do not have drinking water available. Thus, there is an urgent need for proper water management and wastewater treatment to meet global demand. Both economic growth and the quality of Life depend on the efficient water management.[1]

Among water contaminants, we can find the organic dyes used in the textile industries, such as methylene blue. These synthetic dyes have been greatly used due to their lower cost and better adherence to textile materials. However, dye discarded in water waste without adequate treatment represents a serious problem, since they present a danger to Human health and the environment.[2]

In the last years, some alternatives have been proposed to overcome the inadequate treatment of residual waters, namely the ones contaminated with industrial waste. Among these strategies, we can highlight nanocatalysis. Catalytic reactions using nanomaterials has been presented as an efficient process, which can be achieved under mild conditions and without organic solvents, accordingly to Green Chemistry principle. Nanostructures, due to their small size and high surface-to-volume ratio, present a higher number of reactive surface atoms that increases their catalytic activity. Furthermore, they have the potential to be easily recovered and reused, when compared to molecular catalysts.[3] In particular, silver nanoparticles (AgNPs) have stood out for their low cost, easy preparation, and optical properties.[4]

In this context, this work aimed to investigate the catalytic degradation of the organic dye methylene blue (MB) using AgNPs prepared with different capping agents, to evaluate the effect of the structure of the stabilizer in the reaction time and yield.

2. Materials and Methods

2.1. Preparation of AgNPs

Spherical AgNPs were synthesized with four stabilizers: trisodium citrate (TSC), ascorbic acid (AA), polyvinylpyrrolidone (PVP), and polyvinyl alcohol (PVA). The AgNPs were prepared by adding 1.25 mL of the stabilizer solution (TSC and AA - 2.0 mol.L⁻¹, PVA - 500 mg.L⁻¹, PVP - 500 mg.L⁻¹) to 25 mL of sodium citrate (2.5 mol.L⁻¹), and 1.5 mL of NaBH₄ (10 mol.L⁻¹). Finally, 10 mL of AgNO₃ solution (0.5 mol.L⁻¹) was added dropwise, and the mixture was stirred for 1 hour.

The AgNPs were characterized by absorption spectroscopy and transmission electronic microscopy (TEM).

2.2. Methylene Blue Degradation

For the MB degradation, 0.5 mL of methylene blue (0.32 mol.L⁻¹), 0.1 mL of NaBH₄ (0.05 mol.L⁻¹), and AgNPs (1.0; 0.75; 0.50 or 0.25 mL) were mixed in water, obtaining a final volume of 2.60 mL. The reaction was monitored by absorption spectroscopy (UV-Vis) every 5 min.

3. Results

3.1. Preparation of AgNPs

Silver nanoparticles were obtained with different stabilizers: AA, TCS, PVA, and PVP. The samples presented an absorption band around 400 nm (Figure 1A), which indicated the formation of spherical AgNPs.

TEM images (Figure 1B) confirmed their spherical shape, and showed the formation of AgNPs with an average diameter of 20 nm.

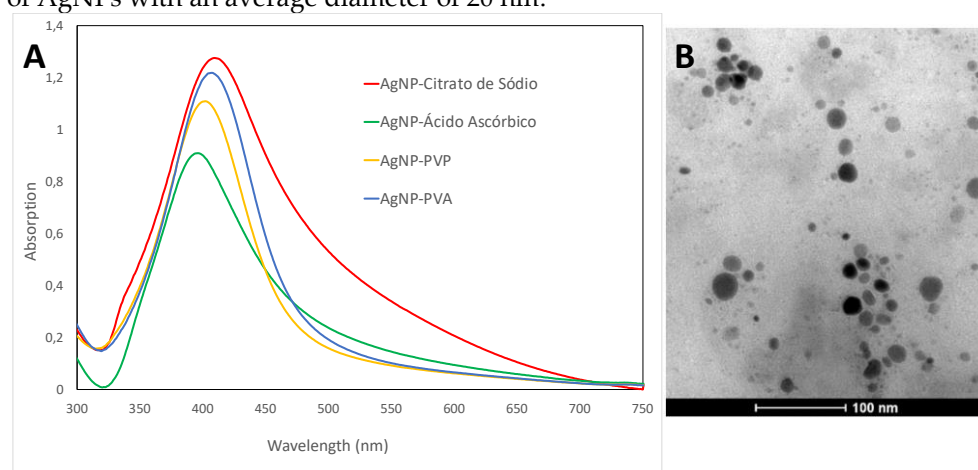


Figure 1. (A) Absorption spectra of AgNPs and (B) TEM image of AgNPs-PVP.

3.2. Methylene Blue Degradation

All AgNPs proved to be efficient catalysts, requiring less than 10 minutes for complete degradation to occur (Figure 2). Furthermore, for all AgNPs, we observed that the catalytic efficiency was dependent of the AgNPs concentration, since decreasing the concentration a lower MB degradation was observed.

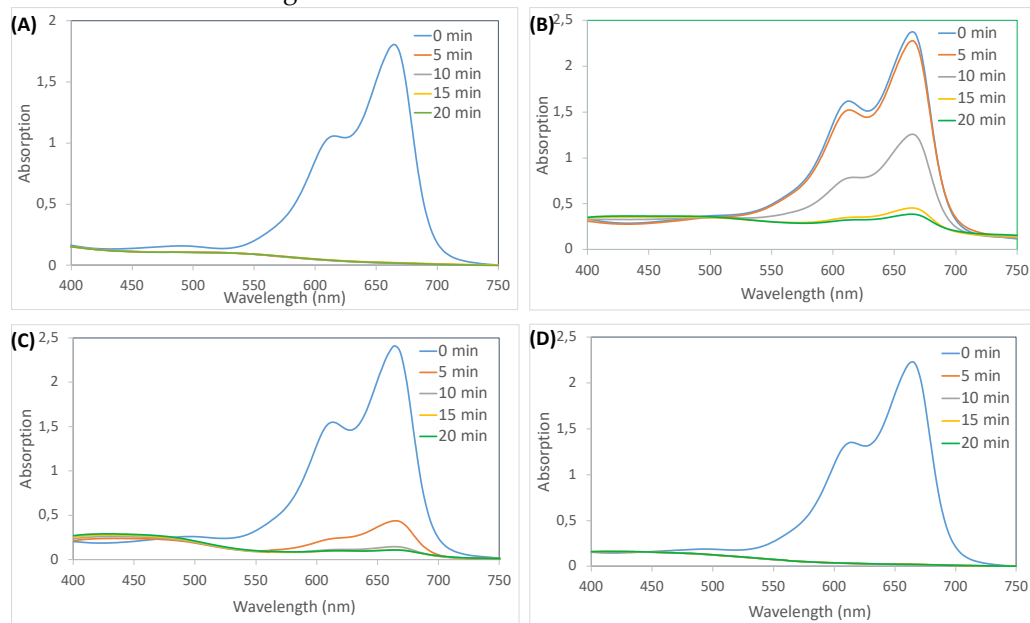


Figure 2. – AM degradation with (A) 0.5 ml of AgNP-TSC; (B) 1.0 ml of AgNP-AA; (C) 0.75 ml AgNP-PVA; (D) 0.5 mL AgNP-PVP.

4. Discussion

The nanoparticles stabilized with TSC and PVP showed very similar behavior and rapid degradation, in 5 minutes it was possible to observe a complete degradation of the dye using 1.0, 0.75, or 0.5 mL of AgNP (Figures 1A and D), showing a partial and slower degradation only when using 0.25 mL of AgNP.

The degradation of MB in the presence of AgNPs stabilized with AA and PVA was less efficient, requiring the use of 1.0 and 0.75 mL of AgNP (Figures 1B and C), respectively, to obtain a degradation greater than 90% of the MB with 15 minutes of reaction. From the results obtained, we can infer that the stabilizer used influences the catalytic efficiency of the nanoparticle. Among the stabilizers used, the most effective were PVP and TSC. The influence of the AgNP stabilizer on the reduction of 4-nitrophenol was already reported, and attributed to the differences in the hydrodynamic radius of the AgNP.[5] However, in this work we found that AgNPs with different stabilizers and comparable sizes gave similar degradation results, indicating that the chemical nature of the stabilizer must have a determining factor in the catalytic process.

5. Conclusions

The catalytic degradation of methylene blue by silver nanoparticles occurred significantly, as shown in the results. The degradation of MB using AgNPs stabilized with TSC and PVP occurred in less than five minutes for quantities of AgNPs higher than 0.50 mL. For nanoparticles stabilized with PVA and AA, it was necessary to use a higher amount of AgNP to achieve the same result. Thus, we concluded that the stabilizing agent used in the nanoparticle influences the kinetics of dye degradation. Furthermore, silver nanoparticles are excellent catalysts for the degradation of methylene blue, and have the potential to be used in the degradation of other synthetic dyes.

Author Contributions: Conceptualization, D.M.M.F., G.A.L.P. and G.P.; methodology, M.T.A.L., D.M.M.F. and G.P.; validation, M.T.A.L., D.M.M.F. and G.P.; formal analysis, M.T.A.L. and D.M.M.F.; investigation, M.T.A.L., D.M.M.F. and N.R.S.M.; writing—original draft preparation, M.T.A.L., D.M.M.F. and G.P.; writing—review and editing, M.T.A.L., D.M.M.F., N.R.S.M., G.A.L.P. and G.P.; supervision, G.P.; project administration, G.A.L.P. and G.P.; funding acquisition, G.P. All authors have read and agreed to the published version of the manuscript.

Funding: This research was funded by CNPq-Brazil, project ID: 425005/2018-6.

Data Availability Statement: Not applicable.

Acknowledgments: In this section, you can acknowledge any support given which is not covered by the author contribution or funding sections. This may include administrative and technical support, or donations in kind (e.g., materials used for experiments).

Conflicts of Interest: The authors declare no conflict of interest.

References

1. B. Adem Esmail, L. Suleiman, Analyzing evidence of sustainable urban water management systems: a review through the lenses of sociotechnical transitions. *Sustainability* **2020**, *12*, 4481. DOI: 10.3390/su12114481
2. H.B. Slama, A. Chenari Bouket, Z. Pourhassan, F.N. Alenezi, A. Silini, H. Cherif-Silini, T. Oszako, L. Luptakova, P. Golińska, L. Belbahri, Diversity of Synthetic Dyes from Textile Industries, Discharge Impacts and Treatment Methods. *Applied Sciences* **2021**, *11*, 6255. DOI: 10.3390/app11146255
3. K. Zhang, J.M. Suh, J.-W. Choi, H.W. Jang, M. Shokouhimehr, R.S. Varma, Recent Advances in the Nanocatalyst-Assisted NaBH₄ Reduction of Nitroaromatics in Water. *ACS Omega* **2019**, *4*, 483-495. DOI: 10.1021/acsomega.8b03051
4. C. Liang, Z.-A. Lu, J. Wu, M.-X. Chen, Y. Zhang, B. Zhang, G.-L. Gao, S. Li, P. Xu, Recent Advances in Plasmon-Promoted Organic Transformations Using Silver-Based Catalysts. *ACS Applied Materials & Interfaces* **2020**, *12*, 54266-54284. DOI: 10.1021/acsami.0c15192
5. C. Kästner, A.F. Thünemann, Catalytic Reduction of 4-Nitrophenol Using Silver Nanoparticles with Adjustable Activity. *Langmuir* **2016**, *32*, 7383-7391.