

Development of Au Nanostars/Graphene Oxide Paper for SERS

Eduarda F. Silva ¹, Gil Gonçalves ² and Sara Fateixa ^{1,*†}

¹ CICECO—Aveiro Institute of Materials Department of Chemistry, University of Aveiro, Aveiro 3810-193, Portugal; eduarda.filipa.silva@ua.pt

² TEMA, Mechanical Engineering Department, University of Aveiro, Aveiro 3810-193, Portugal; ggoncalves@ua.pt

* Correspondence: sarafateixa@ua.pt

† Presented at the 4th International Online Conference on Nanomaterials, 5–19 May 2023; Available online: <https://iocn2023.sciforum.net>.

Abstract: Graphene oxide (GO) has attracted significant attention due to its unique optical properties and tunable surface chemistry, making it an excellent platform for optical sensing applications. Combining GO with metallic nanoparticles allows the fabrication of highly sensitive surface-enhanced Raman scattering (SERS) substrates for analytical purposes. Here, we report our research on chemical strategies to decorate GO paper with Au nanostars (AuNSs) for the SERS detection of methylene blue, a water pollutant model. Several preparative approaches were employed to evaluate their sensitivity to detect MB molecules, including polyelectrolytes, distinct graphene-based materials, and the deposition method of the AuNSs.

Keywords: graphene oxide; Au nanostars; SERS; methylene blue

1. Introduction

Surface-enhanced Raman scattering (SERS) spectroscopy is a vibrational technique that enhances the Raman signal of vestigial molecules of interest adsorbed on rough metal surfaces or metallic nanostructures [1,2]. There are two mechanisms underlying the SERS effect: the electromagnetic mechanism (EM), which is the main contributor, and the chemical mechanism (CM) [1,2]. The CM involves charge transfers between the molecules and the metallic nanostructure by forming an analyte-metal complex [1]. The EM occurs due to the metallic nanostructure's localized surface plasmon resonance (LSPR), which significantly increases the electromagnetic field on the particle's surface when irradiated with an excitation light source [2]. This causes a drastic enhancement of the Raman modes of the molecule adsorbed at the metal surface. Since EM is hugely dependent on the metallic nanostructure, the fabrication of highly active SERS substrates is a hot topic among the scientific community.

Graphene-based materials, namely graphene, graphene oxide (GO) and reduced GO (rGO), have gained special attention due to their electrical conductivity, mechanical strength, chemical and thermal stability, and more recently as SERS sensors [3]. Indeed, graphene has been proven to be a relevant SERS active substrate due to its capability of detecting analytes with high sensitivity, giving rise to a new modality defined as Graphene-enhanced Raman scattering (GERS) [3,4]. The signal enhancement in graphene-based materials is based on the CM, occurring through charge transfer between the graphene and analyte molecules [5,6]. However, CM provides a limited contribution to SERS by itself compared to EM. Meanwhile, research has been done on fabricating hybrid materials containing graphene-based materials and metallic nanostructures, combining the CM effect of the 2D material with the EM of the plasmonic particles, thus achieving high sensitivity [6]. For example, the authors already reported in situ surface modification of GO with Au nanoparticles for highly efficient SERS detection of Rhodamine 6G at low

Citation: Silva, E.F.; Gonçalves, G.; Fateixa, S. Development of Au Nanostars/Graphene Oxide Paper for SERS. *Mater. Proc.* **2023**, *14*, x. <https://doi.org/10.3390/xxxxx>
Published: 5 May 2023



Copyright: © 2023 by the authors. Submitted for possible open access publication under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

concentrations [7]. Nevertheless, fewer studies have been conducted on hybrid sensors containing GO paper for SERS applications [8,9]. This work uses chemical strategies to fabricate hybrid sensors based on GO paper decorated with Au nanostars (AuNSs). The AuNSs/GO papers were used as SERS substrates to detect trace levels of organic dyes in water, namely methylene blue (MB) (Figure 1). Several strategies were employed to evaluate the SERS performance of the hybrid material, namely, adding polyelectrolytes to the GO surface, using GO and rGO, and the deposition method of the AuNSs. We demonstrate that the AuNSs/GO papers are efficient SERS platforms for detecting vestigial amounts of MB, but in principle, the methodology can be extended to other analytes.

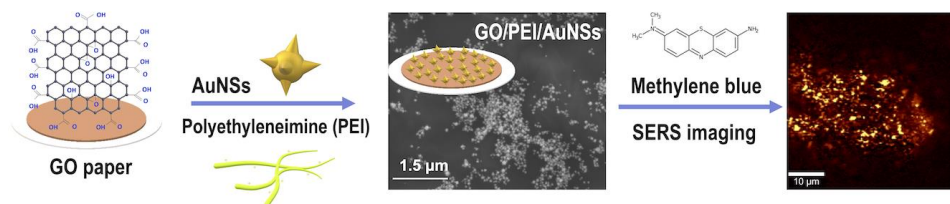


Figure 1. AuNSs/PEI/GO paper for the SERS detection of MB.

2. Materials and Methods

2.1. Materials

The following chemicals were used as purchased: Chloroauric acid trihydrate ($\text{HAuCl}_4 \cdot 3\text{H}_2\text{O}$; 99.9 %, Sigma-Aldrich), ascorbic acid ($\text{C}_6\text{H}_8\text{O}_6$, J. M. Vaz Pereira), silver nitrate (AgNO_3 , 99.9%, Sigma-Aldrich), acid chloride (HCl , 37%, AnaloR Normapur), branched polyethyleneimine (PEI, Mw = 750 k, Sigma-Aldrich), and methylene blue (MB, $\text{C}_{16}\text{H}_{18}\text{N}_3\text{SCl}$, Riedel-De Haën). All the solutions were freshly prepared using ultrapure water ($18.2 \text{ m}\Omega \cdot \text{cm}$). GO was supplied by Graphenea with a concentration of 4 mg/mL.

2.2. GO Paper Preparation

GO paper was prepared using a method used by Gonçalves et al. [10], consisting of the filtration under reduced pressure of 10 mL of GO aqueous colloidal solution (2 mg/mL) through a polyamide membrane filter (Whatman, diameter: 47 mm; pore size: 0.22 mm) placed into a filter membrane holder, until complete drying. Usually, GO sheets are assembled horizontally into a thin layer at the interface with the PA filter membrane. This thin GO layer can be easily removed after drying. A GO paper was then heat-treated at 200 °C in a Vacuotherm vacuum oven for 12 h to achieve rGO paper.

2.3. Au Nanostars (AuNSs) Preparation

The Au NSs were prepared by seed-mediated growth method.[11] First, a Au seed colloidal solution was prepared by adding all at once 10 mL of trisodium citrate (38.8 mM) into a refluxed (90 °C) aqueous solution of HAuCl_4 (1 mM). The colloidal Au seeds were kept in the dark at a temperature of 5 °C before use. Then, the as-prepared Au seeds (100 μL) were added to 10 mL of a HAuCl_4 solution (0.25 mM), followed by 5 μL HCl (1 M) at room temperature and vigorous stirring for 5 s. Then, 100 μL of silver nitrate (8 mM) and 50 μL of ascorbic acid (100 mM) were simultaneously added. The solution was stirred for 30 s as its colour rapidly turned from light red to greenish-black.

2.4. AuNSs/GO Hybrid Sensors Preparation

A positively charged polyelectrolyte, such as PEI (2 mg/mL), was added to GO paper by soaking it in the PEI aqueous solution for 1 min. Then, the GO paper was immersed into the AuNSs colloidal solution (**AuNSs/PEI/GO_1**). In a second approach, drops of

AuNSs colloidal solution were added to the GO paper already coated with PEI. This process was repeated at least 3 times (**AuNSs/PEI/GO_1drop**, **AuNSs/PEI/GO_2drop** and **AuNSs/PEI/GO_3drop**).

2.5. SERS Measurements

For the SERS measurements, MB was used as an analyte model to evaluate the SERS sensitivity of the substrates. An aliquot (10 μL) of an aqueous solution of MB (100 μM) was dropped on the hybrid substrates and let dry at room temperature. Ten spectra were acquired (10 acquisitions, 5 s each) on each substrate, and an average Raman spectrum was obtained using WITec software (Project 5.3⁺). Pure GO paper was used as the control sample. SERS measurements were performed in 3 replicas in different substrate areas to evaluate reproducibility. The same procedure was used to detect crystal violet (CV) and Rhodamine B (RhB), both with a concentration of 100 μM . Raman imaging took 22,500 Raman spectra in a uniform $50 \times 50 \mu\text{m}$ grid. A 100 \times objective was used, and the integration time for each spectrum was 0.05 s. Raman image was constructed by integrating the absolute area underneath the MB Raman band at 1620 cm^{-1} using Project 5.3⁺.

2.6. Instrumentation

Scanning electron microscopy (SEM) images were obtained with a SU-70 Hitachi instrument. FTIR measurements were performed in a Bruker Optics Tensor 27 spectrometer, using 256 scans at a 4 cm^{-1} resolution. Raman studies were carried out on a Raman-AFM-SNOM WITec alpha 300RAS⁺. A He:Ne laser operating at 633 nm and a Nd:YAG laser operating at 532 nm were used as the excitation source with a power set at 0.1 mW. The zeta potential measurements were performed in a ZetaSizer Nano ZS model Zen3500.

3. Results and Discussion

GO and rGO membranes thermally reduced at 200 $^{\circ}\text{C}$ were characterized using SEM and FTIR. The SEM analysis revealed a rough membrane with well-packed layers through the cross-section of the GO paper (Figure 2A(a,b)). At the same time, the side view of rGO demonstrates a less packed layer due to the heat treatment (Figure 2B). This effect can be attributed to the thermal expansion between the GO nanosheets caused by the increasing pressure of the adsorbed water and the reduction of the oxygen functional groups [12]. In Figure 2C(a), the FTIR spectrum of GO paper shows the characteristic vibrational modes for GO powder, including $\nu(\text{C-O})$ from epoxy groups at 1031 cm^{-1} , $\nu(\text{C-OH})$ at 1100 cm^{-1} , skeletal C=C bond vibrations of the graphitic domains at 1636 cm^{-1} , and $\nu(\text{C=O})$ from carbonyl and carboxylic groups at 1735 cm^{-1} [13–15]. In the case of rGO, the FTIR spectrum is very different (Figure 2C(b)). The disappearance or decrease of the bands in the FTIR spectrum indicates the removal of oxygen-containing functional groups (carboxyl, hydroxyl and epoxy) from the GO surface to a certain degree [15]. This result demonstrates that 12 h is enough to reduce the GO membrane.

The GO and rGO membranes were used as SERS platforms to detect MB, a cationic dye commonly used in the textile industry that can produce potentially carcinogenic aromatic amines (benzidine and methylene) [16,17]. Figure 1D shows the average Raman spectra of MB (100 μM) adsorbed on the GO and rGO paper. The conventional Raman spectrum of MB (0.1 M, Figure 2D(a)) is compared. In both GO samples, the characteristic Raman features for carbon materials can be observed: the D band (disorder band) at 1345 cm^{-1} and the G band (graphite band) at 1568 cm^{-1} . These results agree with reports in the literature for GO samples [18,19]. Then, while the Raman analysis on rGO did not show the Raman signal for MB molecules (Figure 2D(c)), the Raman spectrum of MB adsorbed on GO shows the characteristic Raman bands of the MB (Figure 2D(b)), including the skeletal deformation (CN, CS and CH_3) at 441 cm^{-1} , $\delta_{\text{in-plane}}$ (thiazine ring) at 496 cm^{-1} and $\nu(\text{CC})$, $\delta_{\text{in-plane}}$ (CH) from the ring and $\nu(\text{CN})$ at 1618 cm^{-1} [16,20]. One possible explanation for this result is the formation of π - π interaction between the aromatic rings from MB and the

carbons of the hexagonal lattice and through electrostatic interactions between the functional groups present in the GO surface that are negatively charged and the positive charge of the MB molecules [21]. This result indicates that the functional groups of GO present an important role in the adsorption of MB; thus, the fabrication of hybrid materials containing AuNSs was performed using GO papers.

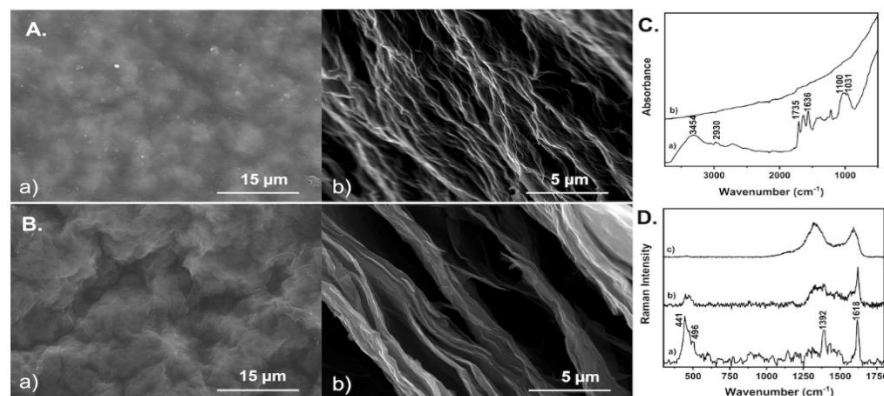


Figure 2. SEM images (A) and SEM side view images (B) of GO (a) and rGO (b) papers; (C) FTIR spectra of GO (a) and rGO (b) and (D) Conventional Raman spectrum of MB (1 mM) on a glass slide (a) and SERS spectra of MB (100 μM) adsorbed on GO (b) and rGO (c) used as substrates.

Due to functional groups, GO has a negatively charged surface in aqueous solutions (-35.2 ± 2.7 mV; pH 6.8).[13] Because the AuNSs also displayed a negative zeta potential (-26.0 ± 5 mV, pH = 2.6), attaching AuNSs onto the GO paper will not be favourable due to electrostatic repulsion. Therefore, the AuNSs/GO hybrid sensors were obtained by attaching the AuNSs onto GO previously modified with a positive polyelectrolyte (PEI) by dip coating and drop cast. The presence of AuNSs on the GO paper was confirmed by SEM analysis, as illustrated in Figure 3A,B. Due to the preparation method, the AuNSs/PEI/GO_1 paper (Figure 3A) presents fewer AuNSs than the AuNSs/PEI/GO_1drop paper (Figure 3B). Still, in both methods, the AuNSs retained their star-shape morphology.

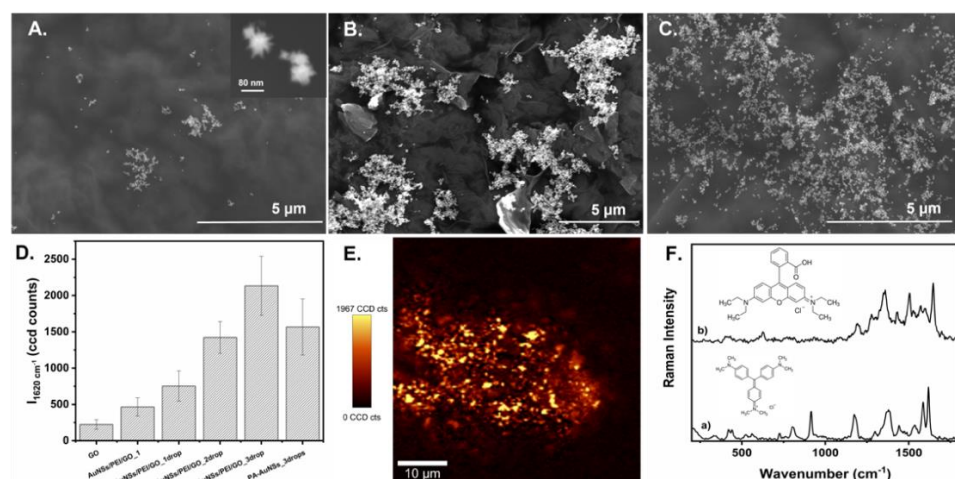


Figure 3. SEM images of AuNSs/PEI/GO_1 (A); AuNSs/PEI/GO_1drop (B) and AuNSs/PEI/GO_3drops (C); (D) Plots of the average Raman intensity of the band at 1620 cm^{-1} in the MB SERS spectrum (100 μM) for GO, AuNSs/PEI/GO_1, AuNSs/PEI/GO_1drop, AuNSs/PEI/GO_2drop, AuNSs/PEI/GO_3drop, PA/AuNSs_3drop; E) Raman image obtained by integrating the area of the band at 1620 cm^{-1} of MB (100 μM) using AuNSs/PEI/GO_3drop; F) SERS spectra of (a) CV (100 μM) and (b) RhB (100 μM) adsorbed on AuNSs/PEI/GO_3drop.

The influence of the hybrid substrates' preparation method on MB's SERS detection was investigated and compared with the SERS signal obtained for GO paper (without AuNSs). Figure 3D plots the average intensity of the MB band at 1620 cm^{-1} for GO, AuNSs/PEI/GO_1 and AuNSs/PEI/GO_1drop hybrid sensors. An enhancement of MB Raman signal is observed for the substrates with AuNSs (466 ± 125 ccd counts for AuNSs/PEI/GO_1 and 754 ± 208 for AuNSs/PEI/GO_1drop) compared to the pure GO paper (223 ± 66 ccd counts), being more sensitive the AuNSs/PEI/GO substrates prepared by drop cast. The detection limit for MB using both substrates was also evaluated, being $1\text{ }\mu\text{M}$ for AuNSs/PEI/GO_1 and 100 nM for AuNSs/PEI/GO_1drop. This result can be explained by the higher amount of AuNSs added to the GO paper surface using the drop cast approach, promoting the formation of more active regions or the so-called "hot spots".

Because the AuNSs/PEI/GO_1drop sensor presents the best SERS performance, more AuNSs drops were added to the GO papers to evaluate their sensitivity to detect MB. The SERS analysis demonstrates an increase in the Raman signal of MB from 1 drop to 3 drops of AuNSs, as illustrated in Figure 3D. This result shows that not only the increase of the AuNSs amount on the GO paper surface increases the Raman signal of MB, which is in line with the SEM image for AuNSs/PEI/GO_3drop (Figure 3C) but also the AuNSs play an essential role for the SERS detection of MB. Considering this, 3 drops of AuNSs were added to a polyamide filter membrane (PA) and used as SERS substrate to detect MB. The Raman signal of MB adsorbed on the PA/AuNSs_3drops was lower than the Raman signal obtained using AuNSs/PEI/GO_3drop. This result can be explained by the conjugation of the electromagnetic mechanism from the AuNSs and the chemical mechanism of GO materials, which can interact with the MB through electrostatic interactions and π - π interaction [21]. The distribution of the MB molecules was monitored by SERS imaging using AuNSs/PEI/GO_3drop (Figure 3E). The SERS image was obtained by integrating the area of the MB Raman band at 1620 cm^{-1} . The yellow/orange areas match the zones with stronger Raman signals for MB molecules adsorbed on the AuNSs distributed over the GO surface. The AuNSs/PEI/GO_3drop paper was also used as SERS sensors to detect other organic dyes, namely CV and RhB (Figure 3F), showing the Raman signal of both organic dyes. This result opens a new field of research for developing hybrid sensors containing GO for optical sensing applications to detect a variety of molecular probes.

4. Conclusions

In conclusion, we have successfully prepared hybrid sensors with high sensitivity for the optical detection of organic dyes by combining the plasmonic properties of AuNSs with GO papers. For the first time, GO papers functionalized with a positive polyelectrolyte and coated with AuNSs were used as sensors for the SERS detection of MB. The AuNSs/PEI/GO substrates were more efficient in detecting MB molecules than the GO paper without AuNSs, or AuNSs dispersed in a PA filter membrane due to the combination of the electromagnetic mechanism from the AuNSs and the chemical mechanism of GO materials, which can interact with the MB through electrostatic interactions and π - π interaction. This research opens a new perspective to develop new hybrid materials containing 2D materials for the optical detection of molecules in vestigial amounts in other analytical contexts.

Author Contributions: E.F.S.: Investigation. G.G.: Supervision, Research planning, Methodology, Writing—review & editing, S.F.: Research planning, Methodology, Supervision, Writing—original draft, Writing—review & editing. All authors have read and agreed to the published version of the manuscript.

Funding: This research received no external funding.

Acknowledgments: This work was developed within the scope of the project CICECO-Aveiro Institute of Materials, UIDB/50011/2020, UIDP/50011/2020 & LA/P/0006/2020, financed by national funds through the FCT/MCTES (PIDDAC). The financial support of TEMA by the projects

UIDB/00481/2020 and UIDP/00481/2020 from FCT; and CENTRO-01-0145-FEDER-022083—Centro Portugal Regional Operational Programme (Centro 2020), under the PORTUGAL 2020 Partnership Agreement, through the European Regional Development Fund. G.G. and S.F. thanks to the Fundação para a Ciência e Tecnologia for the Programme Stimulus of Scientific Employment—Individual Support (CEECIND/01913/2017) and research contract REF-069-88-ARH-2018, respectively.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Fateixa, S.; Nogueira, H.I.S.; Trindade, T. Hybrid Nanostructures for SERS: Materials Development and Chemical Detection. *Phys. Chem. Chem. Phys.* **2015**, *17*, 21046–21071. <https://doi.org/10.1039/c5cp01032b>.
2. Ding, S.Y.; Yi, J.; Li, J.F.; Ren, B.; Wu, D.Y.; Panneerselvam, R.; Tian, Z.Q. Nanostructure-Based Plasmon-Enhanced Raman Spectroscopy for Surface Analysis of Materials. *Nat. Rev. Mater.* **2016**, *1*, 16021.
3. Lai, H.; Xu, F.; Zhang, Y.; Wang, L. Recent Progress on Graphene-Based Substrates for Surface-Enhanced Raman Scattering Applications. *J. Mater. Chem. B* **2018**, *6*, 4008–4028.
4. Xu, W.; Mao, N.; Zhang, J. Graphene: A Platform for Surface-Enhanced Raman Spectroscopy. *Small* **2013**, *9*, 1206–1224. <https://doi.org/10.1002/sml.201203097>.
5. Ling, X.; Xie, L.; Fang, Y.; Xu, H.; Zhang, H.; Kong, J.; Dresselhaus, M.S.; Zhang, J.; Liu, Z. Can Graphene Be Used as a Substrate for Raman Enhancement? *Nano Lett.* **2010**, *10*, 553–561. <https://doi.org/10.1021/nl903414x>.
6. Nurrohman, D.T.; Chiu, N.-F. A Review of Graphene-Based Surface Plasmon Resonance and Surface-Enhanced Raman Scattering Biosensors: Current Status and Future Prospects. *Nanomaterials* **2021**, *11*, 216. <https://doi.org/10.3390/nano11010216>.
7. Gonçalves, G.; Marques, P.A.A.P.; Granadeiro, C.M.; Nogueira, H.I.S.; Singh, M.K.; Grácio, J. Surface Modification of Graphene Nanosheets with Gold Nanoparticles: The Role of Oxygen Moieties at Graphene Surface on Gold Nucleation and Growth. *Chem. Mater.* **2009**, *21*, 4796–4802. <https://doi.org/10.1021/cm901052s>.
8. Liu, J.; Liu, L.; Wu, X.; Zhang, X.; Li, T. Environmentally Friendly Synthesis of Graphene-Silver Composites with Surface-Enhanced Raman Scattering and Antibacterial Activity via Reduction with L-Ascorbic Acid/Water Vapor. *New J. Chem.* **2015**, *39*, 5272–5281. <https://doi.org/10.1039/c5nj00414d>.
9. Li, S.K.; Yan, Y.X.; Wang, J.L.; Yu, S.H. Bio-Inspired in Situ Growth of Monolayer Silver Nanoparticles on Graphene Oxide Paper as Multifunctional Substrate. *Nanoscale* **2013**, *5*, 12616–12623. <https://doi.org/10.1039/c3nr03857b>.
10. Gonçalves, G.; Borme, J.; Bdkin, I.; González-Mayorga, A.; Irurueta, G.; Nogueira, H.I.S.; Serrano, M.C.; Alpuim, P.; Marques, P.A.A.P. Reductive Nanometric Patterning of Graphene Oxide Paper Using Electron Beam Lithography. *Carbon* **2018**, *129*, 63–75.
11. Yuan, H.; Khoury, C.G.; Hwang, H.; Wilson, C.M.; Grant, G.A.; Vo-Dinh, T. Gold Nanostars: Surfactant-Free Synthesis, 3D Modelling, and Two-Photon Photoluminescence Imaging. *Nanotechnology* **2012**, *23*, 75102–75111. <https://doi.org/10.1088/0957-4484/23/7/075102>.
12. Gonçalves, G.; Borme, J.; Bdkin, I.; González-Mayorga, A.; Irurueta, G.; Nogueira, H.I.S.; Serrano, M.C.; Alpuim, P.; Marques, P.A.A.P. Reductive Nanometric Patterning of Graphene Oxide Paper Using Electron Beam Lithography. *Carbon* **2018**, *129*, 63–75.
13. Feito, M.J.; Cicuéndez, M.; Casarrubios, L.; Diez-Orejas, R.; Fateixa, S.; Silva, D.; Barroca, N.; Marques, P.A.A.P.; Portolés, M.T. Effects of Graphene Oxide and Reduced Graphene Oxide Nanostructures on CD4+ Th2 Lymphocytes. *Int. J. Mol. Sci.* **2022**, *23*, 10625. <https://doi.org/10.3390/ijms231810625>.
14. Jasim, D.A.; Lozano, N.; Kostarelos, K. Synthesis of Few-Layered, High-Purity Graphene Oxide Sheets from Different Graphite Sources for Biology. *2D Mater* **2016**, *3*, 014006. <https://doi.org/10.1088/2053-1583/3/1/014006>.
15. Faniyi, I.O.; Fasakin, O.; Olofinjana, B.; Adekunle, A.S.; Oluwasusi, T.V.; Eleruja, M.A.; Ajayi, E.O.B. The Comparative Analyses of Reduced Graphene Oxide (RGO) Prepared via Green, Mild and Chemical Approaches. *SN Appl. Sci.* **2019**, *1*, 1181. <https://doi.org/10.1007/s42452-019-1188-7>.
16. Fateixa, S.; Wilhelm, M.; Nogueira, H.I.S.; Trindade, T. SERS and Raman Imaging as a New Tool to Monitor Dyeing on Textile Fibres. *J. Raman Spectrosc.* **2016**, *47*, 1239–1246. <https://doi.org/10.1002/jrs.4947>.
17. Al-Tohamy, R.; Ali, S.S.; Li, F.; Okasha, K.M.; Mahmoud, Y.A.G.; Elsamahy, T.; Jiao, H.; Fu, Y.; Sun, J. A Critical Review on the Treatment of Dye-Containing Wastewater: Ecotoxicological and Health Concerns of Textile Dyes and Possible Remediation Approaches for Environmental Safety. *Ecotoxicol. Env. Saf.* **2022**, *231*, 113160.
18. Ma, B.; Rodriguez, R.D.; Ruban, A.; Pavlov, S.; Sheremet, E. The Correlation between Electrical Conductivity and Second-Order Raman Modes of Laser-Reduced Graphene Oxide. *Phys. Chem. Chem. Phys.* **2019**, *21*, 10125–10134. <https://doi.org/10.1039/c9cp00093c>.
19. López-López-Díaz, D.; López, M.; Holgado, L.; García-Fierro, J.J.; Mercedes Velázquez-velázquez, M. Evolution of the Raman Spectrum with the Chemical Composition of Graphene Oxide. *J. Phys. Chem. C* **2017**, *121*, 20489–20497. <https://doi.org/10.1021/acs.jpcc.7b06236>.
20. Xiao, G.N.; Man, S.Q. Surface-Enhanced Raman Scattering of Methylene Blue Adsorbed on Cap-Shaped Silver Nanoparticles. *Chem. Phys. Lett.* **2007**, *447*, 305–309. <https://doi.org/10.1016/j.cplett.2007.09.045>.

-
21. Ederer, J.; Ecorchard, P.; Slušná, M.Š.; Tolasz, J.; Smržová, D.; Lupínková, S.; Janoš, P. A Study of Methylene Blue Dye Interaction and Adsorption by Monolayer Graphene Oxide. *Adsorpt. Sci. Technol.* **2022**, *2022*, 7385541. <https://doi.org/10.1155/2022/7385541>.

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.