

Effect of fly ash on geotechnical properties of soft soil: A critical review [†]

Srijan ^{1,2,*}, Gautam Narula ^{1,3}, Aditi Sharma ^{1,4} and Vijayinder Kumar Dogra ¹¹ Shri Mata Vaishno Devi University, Katra, India; srijanpurvey@gmail.com² Delhi Technological University, New Delhi, India; srijanpurvey@gmail.com³ Indian Institute of Technology, Roorkee, India; happysince1995@gmail.com⁴ Guru Nanak Dev University, Amritsar, Punjab, India; adisharma32@gmail.com* Correspondence: srijanpurvey@gmail.com; Tel.: (optional; include country code; if there are multiple corresponding authors, add author initials)

† Presented at The 4th International Electronic Conference on Applied Sciences, place, and date.

Abstract: An industrial by-product known as fly ash is produced when coal is burned for electricity production and is considered an environmental pollutant. A comprehensive fly ash utilisation programme must be implemented to reduce environmental pollution, including numerous factors at different levels. Fly ash's geotechnical qualities, including its specific gravity, permeability, internal angular friction, and consolidation characteristics, make it ideal for structural fill, particularly on clay soils, when building highways and embankments. Much research has been done on how fly ash affects soil stability. In order to determine the impact of fly ash addition on soil properties, this inquiry reviewed a few of these papers and conducted a critical assessment. This study also looked at combined fly ash and clay soil. Numerous investigations indicate that fly ash generally improves soil stability, notably when analysing CBR values and soil permeability, and reduces volumetric changes in the soil. The ground has gotten more compact due to particle size and form and a decrease in volumetric dilatation. Because the additives to the hardened soil do not dissolve, the soil's behaviour is still being modified.

Keywords: Fly ash; clayey soil; strength parameters; waste material.

1. Introduction

Reduced construction sites are a significant issue globally, particularly in the highly populated nations of south and southeast Asia [1,2]. As a result, it became necessary to execute land reclamation to utilise this kind of land. Thus, it has been revealed that it is possible to transform such unproductive lands using ground development technologies. Numerous geotechnical construction techniques are used to improve the performance of weak/soft clay [3,4,5]. The rising demand for electrical power has resulted in millions of tonnes of rubbish developed by the coal-burning electric power thermal plant. Fly ash (FA) and ground-granulated blast furnace slag (GGBFS) are examples of this waste [6]. The ecology is now greatly concerned with the disposal and recycling of such waste goods, which also consumes vast funds. Some of these studies concentrated on increasing the soil's capacity using fly ash, a waste product of thermal power plants [7,8].

Fly ash is the primary by-product of thermal power plants, which use coal to produce energy. Numerous chemical substances and minerals, including unoxidised carbon, silicon, iron oxides, and aluminium, are found in fly ash [6]. It is possible to modify the volume of clay soils and increase strength by stabilising them using admixtures [9]. Additionally, using FA can improve the soil's engineering qualities [10]. By using the FA in soil improvement, there was a reduction in settlement during construction and hence the

Citation: To be added by editorial staff during production.

Academic Editor: Firstname Last-name

Published: date



Copyright: © 2023 by the authors. Submitted for possible open access publication under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

time required to achieve complete settlement [11]. FA can be used in the soil to increase its bearing capacity, stability, and shear strength. Using FA to improve soil can make it less plastic and have higher free swelling index (FSI) values [12]. For stabilisation of poor soil, a number of researches are done that study the impact of fly ash in addition to other materials such as geopolymer, slag, bentonite, sand and gypsum. Plasticity index, Atterberg limits and free swell index fall when different amounts of cement and fly ash are mixed in the soil, whereas there was an increase in unconfined compressive strength (UCS) and CBR [13]. Thus, as per the results, for subgrade and pavement applications, fly ash containing 5-20% geopolymer allowed better stability to black cotton soil when cured at 25 °C for a minimum of fourteen days[14].

A range of research investigations on FA productivity in clay soils is presented in this study. Though the problem of expanding soil and the alternatives for recycling industrial waste must be dealt with separately, utilising such waste is a viable strategy to encourage long-term growth. Recent initiatives show that funds can be saved using effective waste management methods, including soil stability.

2. Fly ash and other properties:

To understand the various properties and its effect a brief analysis of few of the methodologies adopted by various researchers have been explained in brief. Salim[15] conducted a laboratory test where soil classification (as per ASTM D 854-000), compaction tests (as per ASTM D 422-63) were carried out. Further swelling consolidation test (as per ASTM D 4829-03) was done to determine the swelling pressure and free swell. Various other researchers used unconfined compressive strength test (UCS) to determine the index characteristics, compaction impact, and compressive strength of clayey soil along with the various combinations of using fly ash with it. The optimal moisture content (OMC) and maximum dry density (MDD) for various mix were determined. A 38.10 mm diameter and 76.20 mm height UCS cylindrical mould was used to create the samples. The samples underwent 7, 14, and 28 days of dehydration. Following that, their compressive strength was assessed in both soaked and unsoaked situations, and the findings were shared. The effect on fly ash on various properties have been discussed below:

2.1. Fly ash and swelling of soil

Salim conducted lab tests [15] to find how swell potential, FSI and swelling pressure are affected by the FA content of soil of expansive nature. The organic soils have a comparable impact as the admixtures. It was seen that as the bentonite percentage rises, so do the swelling and swell pressure. There was a decline in swelling pressure and swelling itself with an increase in the percentage of fly ash. A drastic reduction in the said properties was noted at 5% of fly ash content.

Zha et al. [16] added that FA and FA lime have a stabilised expansive soil and noted an effective reduction in the ability of soil to expand and contract. Further, the soil properties of swelling pressure, swelling capabilities and free swell were reduced with increased lime ash and FA content. Both FA and Lime-ash soil samples' swelling capacity and inflation pressure decrease despite increased curing time, as illustrated in Figs. 1 and 2.

In order to stabilise black cotton soil, Murmu and Patel [14] investigated the effectiveness of FA and Geopolymer (RHA-based, which is a blend of sodium hydroxide (SH) and sodium silicate (SS)). It was noted that geo-polymerisation leads to a great fall in the susceptibility to swelling and shrinkage of black cotton soil.

2.2. Fly ash and soil settlement

Via oedometer studies in the lab, Saha and Pal [17] focused on the settlement behaviour of clay soil concerning FA content. The settlement of the module of Soil-FA-Soil noted a reduction of 0.30 mm, and the module of FA-Soil-FA noted a decrease of 0.26 mm. for reference. The actual initial settlement value of FA specimens was 0.19 mm. The changes observed in settlements can be attributed to modifying molecular structures in the samples. The relation between applied pressure in the form of a logarithm axis ($\log p$) and settlement is shown in Fig. 3. The final consolidation settling of clay soil, according to Karim et al., [11] is 20% of fly ash, or 0.638 mm, at the optimal level. However, above this percentage, there was a minor rise.

During the research of Somnath [18], the researcher blended the soil specimens with various percentage levels of FA and observed the results with plain FA and plain samples. The maximum settlement noted for the plain soil samples was 0.45 mm, compared to 0.17 mm for plain FA samples. Fig. 4 displays settlement values and $\log p$. The settlement was 0.27 mm for 30% of FA and 0.28 mm for 20% of FA.

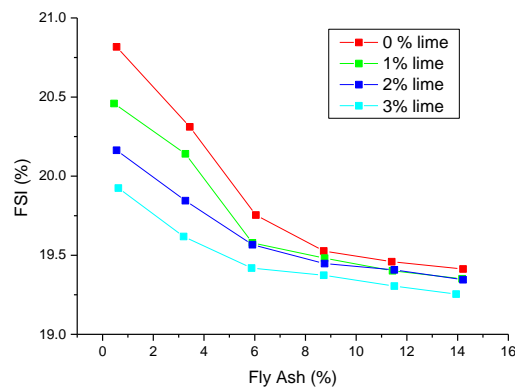


Figure 1. Impact of addition of FA-lime on FSI after 7-day curing time (modified from Zha et.

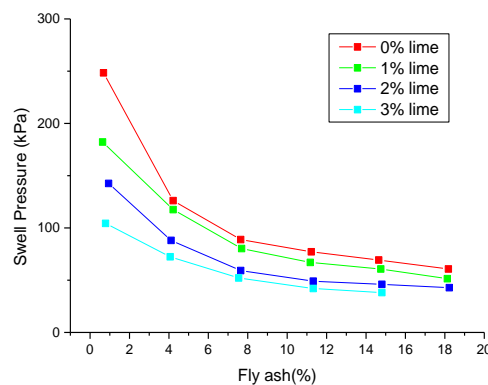


Figure 2. Effect of addition of FA-lime additive after 7-day curing time on swelling pressure(modified from Zha et al. [15]).

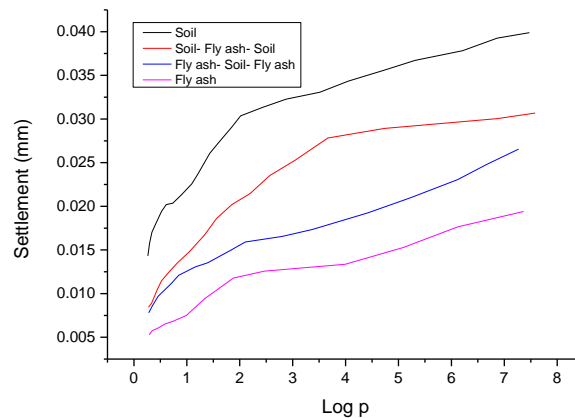


Figure 3. Settlement estimates for different specimens with and without FA (modified from Saha and Pal [17]).

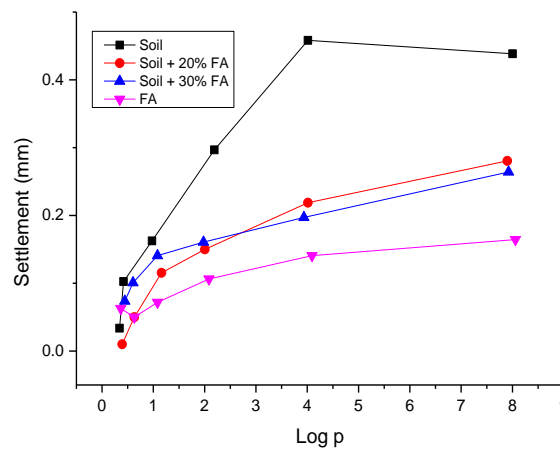


Figure 4. FA percentage's impact on settlement values (modified from Somnath [18]).

2.3 Fly ash and soil shear strength

Due to its very high water content, the excavated clay and black cotton soil could not be utilised directly again in geotechnical applications. Dewatering is, therefore, necessary before any further advancement. Because of the performance of outstanding flocculation, for dewatering, chemical flocculants are deployed [19,20]. The study conducted by Bose [21], where the researcher varied the FA content from 0-90%, is depicted in Fig. 5. At 20% of FA concentration, UCS increased; data over this proportion indicate a UCS decrease. Under the given circumstances, 20% of FA is the amount that will best help the mixed soils acquire their shear strength. The results showed that adding FA to the ideal level can cause cemented materials to exhibit pozzolanic behaviour, significantly increasing shear strength. Contrarily, when FA is present more than the optimal level, it behaves as unbound silt particles that lack cohesion and perceptible friction, reducing strength.

From Fig.6, the increase in the UCS value was explained by Nath et al. [22]. The author defined that during the interaction of CaO present in fly ash with soil's Al_2O_3 and SiO_2 , cementation gels (hydrate) were formed, which is responsible for an increase in the UCS value of the sample. Further, there is a rise in the compressive strength of the FA-stabilised soil with higher curing time.

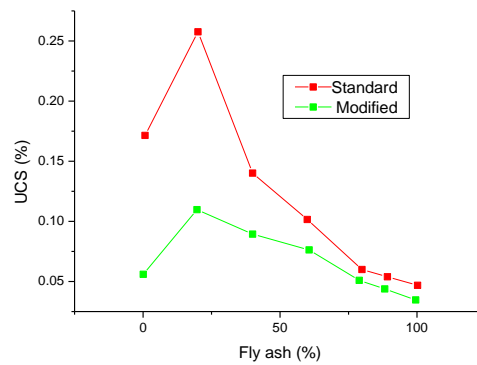


Figure 5. Unconfined compressive strength varies depending on the amount of FA (modified from Bose [21]).

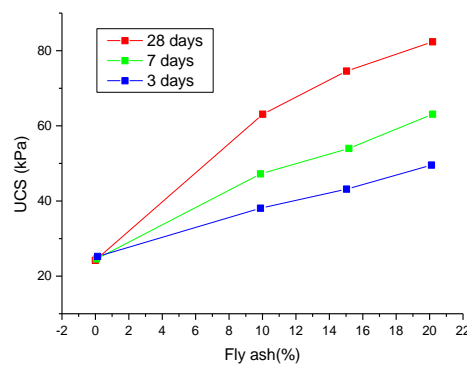


Figure 6. UCS variation with ash content (modified from Nath et al. [22]).

2.4. Fly ash and California Bearing Ratio Test

The stabilisation of black cotton soil using fly ash was experimented with by Kumar and Harika [23]. The California Bearing Ratio test values for untreated soil were noted at 2.189%, But when the soil was treated with fly ash, the California Bearing Ratio test value reached 10.3%. Thus, the study recommended blending black cotton soil with 10% fly ash for pavement and foundation work.

Edil et al. [24] conducted an experimental investigation on soil-FA mixtures at varying FA levels (10–30%) to understand the effect of adding FA to the CBR value. The CBR value of the soil and fly ash combination rose with a rise in FA content. With 10% FA added to the fine-grained soil, it resulted in a 4% rise in the value of CBR. The CBR value was noted to decrease with a rise in water content.

3. Future Scope

It is clear from the literature analysis above that different fly ash material sources will provide diverse fly ash properties and will affect the synthesis of fly ash and soil in different ways. Thus, additional research on various fly ash sources is required to determine the impact of the same on the soil's engineering qualities. Additionally, a great deal of research on the behaviour of fly ash-mixed soil has been published. Examining bottom ash as a soil supplement in place of fly ash is necessary, though. Therefore, before adding this technology to the application of geotechnical engineering, a thorough investigation is required to clarify and validate the knowledge that is currently accessible on this subject.

It is also possible to research how plastic debris, such as plastic bottle cuts and rubber tyre powder, affects soil stability. They are materials that pollute and do not biodegrade quickly.

4. Conclusion

The following statements show how fly ash and other additives are effective and act as a sustainable option in construction applications while summarising their exceptional engineering properties:

- FA use during clay soil treatment. Waste materials raise the standards for soil consolidation. The compressibility of soil is found to be increased multiple times by the addition of FA, as FA has excellent pozzolanic behaviour.
- The swelling potential and free swelling index decrease with increased fly ash and fine sand and content to clay soil of expansive behaviour.
- On blending soil clay with fly ash, secondary consolidation occurs sooner than when the soil clay is not treated. This means that the consolidation settling under the buildings is reduced and attained in less time in engineering applications.
- The soil treated with fly ash was found to have a CBR value of 10.3% compared to the CBR value of the untreated sample, which was found to be 2.189%. The study suggests combining black cotton soil with fly ash in amounts up to 10% for foundation and pavement work.

Supplementary Materials: All the materials have been provided in the current manuscript.

Author Contributions: A short paragraph specifying their individual contributions must be provided for research articles with several authors. The following statements should be used "Conceptualization, S; methodology, S; investigation, Srijan and GN; resources, S; AS; data curation, S; writing—original draft preparation, S; writing—review and editing, S; GN; VKD; visualisation, S; supervision, VKD; project administration, S.

Funding: This research received no external funding.

Data Availability Statement: The current manuscript has provided all the relevant data.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Ravallion, M.; Chen, S.; Sangraula, P. New Evidence on the Urbanization of Global Poverty. *Popul. Dev. Rev.*, 2007; 33, 667–701. <https://doi.org/10.1111/j.1728-4457.2007.00193.x>.
2. Faisal Noaman, M.; Khan, M.A.; Ali, K. Effect of artificial and natural fibers on behavior of soil. *Mater. Today: Proc.*, 2022; 64, 481–487. <https://doi.org/10.1016/j.matpr.2022.04.954>.
3. Srijan and Gupta A.K. A Review article on Construction, Parametric Study and Settlement Behavior of Stone Column. *IOP Conference Series: Earth and Environmental Science* 2021, vol. 796, no. 1. <https://doi.org/10.1088/1755-1315/796/1/012021>.
4. Srijan and Gupta, A.K. Effectiveness of triangular and square pattern of stone column with varying s/d ratio on consolidation behaviour of soil. *Second ASCE India Conference CRISIDE, 2020*, 1, 1648-1654.
5. Srijan and Gupta, A.K. The effect of using a sand column on the expansive soil's swelling characteristics. *Journal of Current Research in Engineering and Science* 2022, 5(1), 1-6.
6. Hassan, A.; Arif, M.; Shariq, M. Effect of curing condition on the mechanical properties of fly ash-based geopolymer concrete. *SN Appl. Sci.*, 2019b, 1, 1694. <https://doi.org/10.1007/s42452-019-1774-8>.
7. Ozdemir, M.A. Improvement in Bearing Capacity of a Soft Soil by Addition of Fly Ash. *Procedia Eng.*, 2016, 143, 498–505. <https://doi.org/10.1016/j.proeng.2016.06.063>.
8. Ram, L.C.; Mastro, RE Fly ash for soil amelioration: A review on the influence of ash blending with inorganic and organic amendments. *Earth Sci. Rev.*, 2014, 128, 52–74. <https://doi.org/10.1016/j.earscirev.2013.10.003>.
9. Seco, A.; Ramirez, F.; Miqueleiz, L.; Garcia, B. Stabilization of expansive soils for use in construction. *Appl. Clay Sci.*, 2011, 51, 348–352. <https://doi.org/10.1016/j.clay.2010.12.027>.
10. Kim, B.; Prezzi, M. Evaluation of the mechanical properties of class-F fly ash. *Waste Manage.*, 2008, 28 (3), 649–659. <https://doi.org/10.1016/j.wasman.2007.04.006>.
11. Karim, H.H.; Samueel, Z.W.; Jassem, AH Behaviour of soft clayey soil improved by fly ash and geogrid under cyclic loading. *Civ. Eng. J. (Iran)*, 2020b, 6. <https://doi.org/10.28991/cej-2020-03091466>.

12. Tastan, E.O.; Edil, T.B.; Benson, C.H.; Aydilek, A.H. Stabilization of Organic Soils with Fly Ash. *J. Geotech. Geoenviron. Eng.*, 2011, 137, 819–833. [https://doi.org/10.1061/\(ASCE\)GT.1943-5606.0000502](https://doi.org/10.1061/(ASCE)GT.1943-5606.0000502).
13. Rai, P.; Qiu, W.; Pei, H.; Chen, J.; Ai, X.; Liu, Y.; Ahmad, M.; Wu, Y.Z. Effect of Fly Ash and Cement on the Engineering Characteristic of Stabilized Subgrade Soil: An Experimental Study. *Geofluids*, 2021, 1–11. <https://doi.org/10.1155/2021/1368194>.
14. Murmu, A.L.; Patel, A. Studies on the Properties of Fly Ash-Rice Husk Ash-Based Geopolymer for Use in Black Cotton Soils. *Int. J. Geosynthetics Ground Eng.*, 2020, 6 <https://doi.org/10.1007/s40891-020-00224-z>.
15. Salim, N.M., 2021. Improvement of the Geotechnical Properties of Expansive Soils Using Fly Ash. *J. Southwest Jiaotong University* 56. <https://doi.org/10.35741/issn.0258-2724.56.1.9>.
16. Zha, F.; Liu, S.; Du, Y.; Cui, K. Behavior of expansive soils stabilised with fly ash. *Nat. Hazards*, 2008, 47, 509–523. <https://doi.org/10.1007/s11069-008-9236-4>.
17. Saha, S.; Pal, S.K. Compressibility behavior of soil and fly ash used in successive layers. *Electron. J. Geotech. Eng.*, 2012, 17 T, 2659–2670.
18. Somnath, S. Permeability and Volume Change Behaviour of Soil Stabilised with Fly ash. *Int. J. Eng. Res. Technol. (IJERT)*, 2015, 4, 840–846.
19. Xu, G.Z.; Qiu, C.C.; Song, MM; Cao, Y.P.; Yin, J. Flocculant effects on fluidity and strength behavior of cemented dredged clay with high water content. *Mar. Georesour. Geotechnol.*, 2021, 39 (8), 951–961. <https://doi.org/10.1080/1064119X.2020.1786198>.
20. Yin, J.; Hu, M.M.; Xu, G.Z.; Han, W.X.; Miao, Y.H. Effect of salinity on rheological and strength properties of cement-stabilised clay minerals. *Mar. Georesour. Geotechnol.*, 2020, 38 (5), 611–620. <https://doi.org/10.1080/1064119X.2019.1608484>.
21. Bose, B. Geo-engineering properties of expansive soil stabilised with fly ash. *Electronic Journal of Geotechnical Engineering*, 2012, 17 J, 1339–1353.
22. Nath, B.D.; Molla, M.K.A.; Sarkar, G. Study on Strength Behavior of Organic Soil Stabilized with Fly Ash. *Int. Scholarly Res. Notices*, 2017, 1–6. <https://doi.org/10.1155/2017/5786541>.
23. Kumar, P.G.; Harika, S. Stabilization of expansive subgrade soil by using fly ash. *Mater. Today: Proc.*, 2021, 45, 6558–6562. <https://doi.org/10.1016/j.matpr.2020.11.469>.
24. Edil, T.B.; Acosta, H.A.; Benson, C.H. Stabilizing Soft Fine-Grained Soils with Fly Ash. *J. Mater. Civ. Eng.*, 2006, 18, 283–294. [https://doi.org/10.1061/\(asce\)0899-1561\(2006\)18:2\(283\)](https://doi.org/10.1061/(asce)0899-1561(2006)18:2(283)).

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.