

Type of the Paper (Abstract, Meeting Report, Preface, Proceedings, etc.)

Experimental and theoretical approach to the corrosion inhibition of mild steel in HCl solution by a newly coumarin

Fanar Hashim ¹, Khalida Al-Azawi ¹, Shymaa Al-Bghdadi ², Lina Shaker ², Ahmed Al-Amiery ^{2,*}

¹ Applied Science Department, University of Technology, Baghdad 10001, Iraq; fanarghanim@gmail.com (F.G.H.); khalidachemistry@gmail.com (K.F.A.)

Energy and Renewable Energies Technology Center, University of Technology, Baghdad 10001, Iraq; shaimaalbaghdadi1980@gmail.com (S.A.); linamohammed91@gmail.com (L.M.S.).

* Correspondence: dr.ahmed1975@gmail.com; Tel.: +96-4770-067-1115 (A.A.)

Received: date; Accepted: date; Published: date

Abstract: New coumarin namely 2-(3-(7-methylcoumarin)acetamido)benzoic acid (MAB) was successfully synthesized by reaction of ethyl 2-(7-methylcoumarin)acetate with anthranilic acid. The chemical structure of MAB was confirmed by FT-IR, NMR spectroscopies and Elemental Analysis. The inhibition performance of MAB was investigated using the weight loss method. The results illustrate the strong adsorption of MAB molecules on the mild steel coupon surface and this adsorption follows the Langmuir adsorption isotherm. DFT calculations were performed to show the relationship between the MAP molecular structure and inhibition performance.

Keywords: coumarin 1; corrosion 2; inhibitor 3; anthranilic acid

1. Introduction

As a significant alloy in the universe, mild steel is the substance of choice in oil manufactures for its ability to work mechanical and low coast [1,2]. In most industrial processes, acid is used in the treatment, cleaning and removal of rust [3]. The use of acids during treatment and cleaning processes will lead to corrosion of the metal surface, therefore, an appropriate corrosion inhibitor is urgently needed. Organic compounds containing a heteroatom, such as nitrogen, oxygen, sulfur and phosphorus, or containing double and triple bonds, as well as aromatic rings are considered one of the most important materials recognized in practice and used as anti-corrosion inhibitor. To protect mild steel from corrosive environment, and also to reduce the consumption of acidic solutions that occur during prolonged operation [4-9]. Inhibitors have the ability to control the dissolution of metals and alloys by twisting a layer of anti-corrosion on the surface of the metal or alloy to prevent corrosion thus not exposed to acidic solution [10]. The approach of adsorption inhibitor consists on the inhibitor chemical structure and the nature of the solution acid or base [11]. In general, the cyclic organic compounds containing heteroatoms reported have an excellent inhibition efficiency, but they are limited to use due to the following: (1) high production cost, (2) Toxicity of the secondary compounds which formed during their production or via side reactions resulting in ecological concern and (3) the specificity of work related with the utilize of individual organic corrosion inhibitors. Thus, inhibitors must be active, not expensive and eco-friendly [12,13]. Following up of the investigations for efficient corrosion inhibitor [14-37], this investigation reports the inhibitive effects of new corrosion inhibitor. The synthesized new corrosion inhibitor namely 2-(3-(7-methylcoumarin)acetamido)benzoic acid (MAB), was characterized with FTIR and NMR spectroscopies. The corrosion inhibition behavior on the surface of mild steel in corrosive

environment was studied using weight loss techniques. Density functional theory (DFT) were used to corroborate mythological findings.


2. Experimental Section

2.1. Materials

Mild steel coupons (2.5cm×2.0cm×0.025cm) were used for weight loss techniques with following composition: 99.210Fe; 0.210C; 0.380 Si; 0.090P; 0.05S; 0.050Mn and 0.010Al. The coupons were cleaned with double distilled water, acetone, and dried before each test. The hydrochloric acid solution was used with concentration of 1M as corrosive environment.

2.2. Inhibitor

A mixture of equimolar of methyl 2-(7-methyl-2-oxo-2H-chromen-4-yl)acetate and 2-aminobenzoic acid (2.0 mM) was heated for 24 hours at 120 oC. After completion of the reaction, the precipitate was acidified with 2% hydrochloric acid, filtered, recrystallized from ethyl alcohol and dried to yield 55% of yellow solid, melting point: 252 °C. The chemical structure of MAB was demonstrated in Scheme 1. The MAB molecule was characterized by Fourier-transform infrared (FTIR) and Nuclear magnetic resonance (NMR) spectroscopical techniques in addition to a CHN analysis (a carbon, hydrogen and nitrogen analyzer). CHN, analytical calculation/found for the MAB molecule with the chemical formula C₁₉H₁₅NO₅: C, 67.65 /67.13; H, 4.48/5.45; N, 4.15/4.07. FT-IR (cm⁻¹): 3283.7 (N-H),1736.1 (C=O lactone) and 1707.5 (C=O carboxyl). ¹H NMR in DMSO-d₆ (ppm): δ 2.59 (3H, s), 3.41 (2H, s), 5.89 (1H, s), 7.29-7.41 and 7.61-7.73 (1H, aromatic), 7.88 (1H, NH).

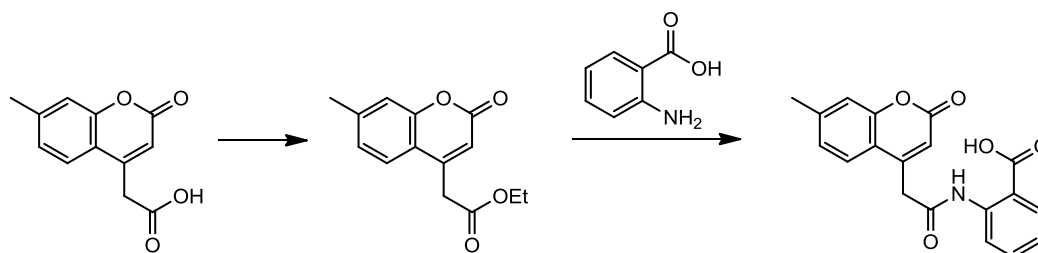

Scheme 1. Chemical structure of the MAB.

2.3. Gravimetric Measurements.

The weight loss measurements were performed using mild steel coupons in corrosive environment in absence and presence MAB. The mild steel coupons were cleaned and weighted. Mild steel coupons were immersed in 1 M HCl for 5 h at 303 K in absence and presence MAB. After that the loss in weight was calculated through by the variation in mild steel coupons weights. Corrosion rate (CR), inhibition efficiency (IE%), and mild steel surface coverage (θ) were measured via equations 1-3.

$$C_R = \frac{W}{At} \quad 1$$

$$IE\% = \frac{C_R - C_{R(i)}}{C_R} \times 100 \quad 2$$

$$\theta = \frac{C_R - C_{R(i)}}{C_R} \quad 3$$

where W is the loss in weight of the mild steel coupon in milligram, A represent the area in cm², t is the immersion time in hours and C_{R(i)} is the corrosion rate in presence of MAB.

2.4. DFT.

Quantum chemical studies for the molecules of MAB as corrosion inhibitor were performed neutral mode by using of via the Density functional theory calculation with GAUSSIAN 03W software/B3LYP functional [38–40] with a 6-31G basis set [41]. The significant factors have been calculated using the electronic values of the most stable structure of the studied MAB molecules. HOMO and LUMO energies were used to calculate significant parameters such as ΔE , η , σ , χ and ΔN [42,43] using the following equations 4-7.

$$\Delta E = E_{HOMO} - E_{LUMO} \quad 4$$

$$\eta = -0.5 (E_{HOMO} - E_{LUMO}) \quad 5$$

$$\sigma = \frac{1}{\eta} \quad 6$$

$$\Delta N = \frac{\chi_{Fe} - \chi_{inh}}{2\eta_{Fe} + 2\eta_{inh}} \quad 7$$

where χ represent the electronegativity and η represent the represent the hardness.

3. Results and discussion

3.1. Weight loss measurements.

The gravimetric results for mild steel coupons in the hydrochloric acid environment with and without of MAB as corrosion inhibitor were demonstrated in Figures 1-2.

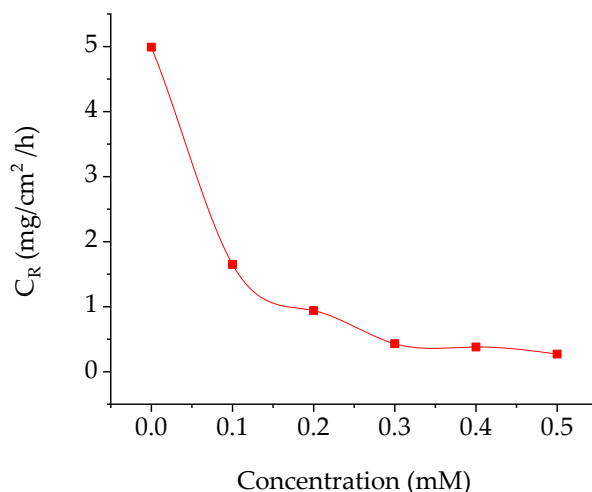


Figure 1. Inhibition efficiencies Corrosion rate for mild steel coupons with and without MAB in 1 M HCl at 308 K

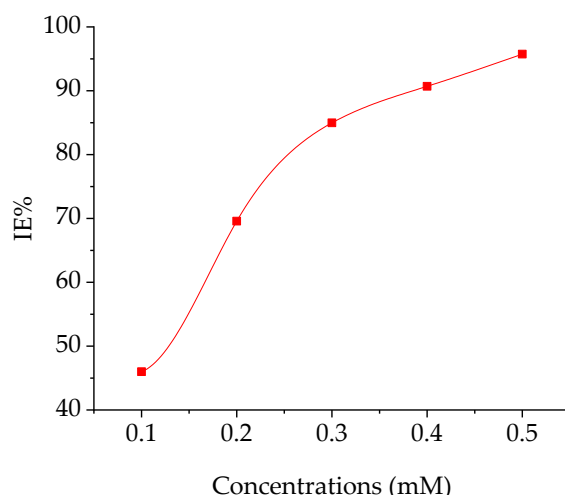


Figure 2. Effect of various concentrations of MAB on the inhibition efficiency for mild steel coupons in 1 M hydrochloric acid at 303 K.

The excellent inhibition efficiency of new synthesized corrosion inhibitor for mild steel coupons in corrosive environment was attributed to the existence of a number of heteroatoms (Nitrogen and oxygen), aromatic rings and the system α,β -unsaturated carbonyl compound in MAB molecule in addition to big molecular structure of MAB.

3.2. Adsorption Isotherms.

The values obtained for surface coverage (θ) were used by weight loss calculations to find the best and most suitable adsorption isotherm. The adsorption isotherm helps to realize the bonding between the MAP molecules and the coupon surface. The MAP molecules on the coupon surface are absorbed chemically or physically. To realize the adsorption phenomenon, isothermal adsorption (Temkin, Freundlich, and Langmuir isotherms) was utilized to methodological results. It was noted that the adsorption isotherm of Langmuir was very well constructed, with the regression coefficient (R^2) value of MAP, indicating a good fit. The obtained slope was 0.78009 and intercept value obtained for the Langmuir isotherm was 2.55971. The Langmuir isotherm plot between C/θ and C_i demonstrate in Figure 3.

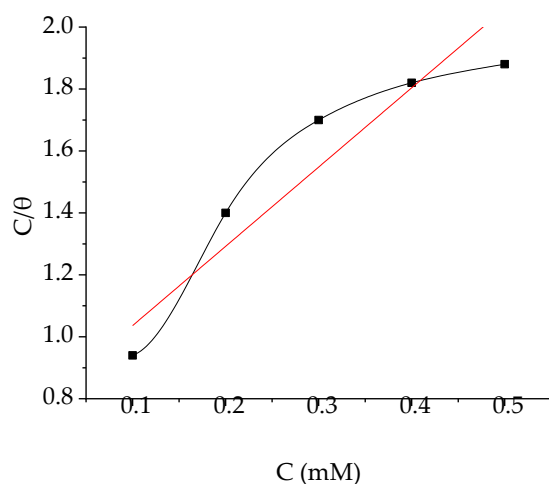


Figure 3. Langmuir adsorption isotherm for mild steel coupon in the presence of MAB.

Adsorption equilibrium constant value was obtained through a straight line of C/θ and C (as in equation 8), to obtain free energy of adsorption ΔG_{ads} as in equation 9.

$$\frac{\text{Concentration of the inhibitor } (C)}{\text{Surface area } (\theta)} = \frac{1}{\text{Adsorption equilibrium } (K_{ads})} + C \quad 8$$

$$\Delta G_{ads} = -R(\text{gas constant})T(\text{absolute temperature}) \ln(55.5K_{ads}) \quad 9$$

From equation 9, the ΔG_{ads} value was calculated. It is published recently that if ΔG_{ads} value in the more negative value of -40 kJ/mol implies chemisorption adsorption. On the other hand if ΔG_{ads} value less negative value or around -20 kJ/mol suggest physisorption [64,47]. The ΔG_{ads} value for MAB 36.7 kJ/mol, indicates chemisorption adsorption.

3.3. Quantum Chemical Calculations.

The DFT studies are quite significant in realizing extra knowledge on the corrosion inhibition phenomenon. The corrosion impedance effectiveness of a molecule as corrosion inhibitor is correlated with some quantum parameters (EHOMO, ELUMO, ΔE , η , σ , χ and ΔN and Mulliken charges). The quantum studied factors can be observed by the optimization of the investigated inhibitor [48,49].

The quantum chemical factors give the information about the connection between mild steel surface and inhibitor molecules. Herein, the results of this study are demonstrated in Figure 4 and Table 1. The inhibition efficiency of MAB as new synthesized tested corrosion inhibitor can be understanding through HOMO "Highest Occupied Molecular Orbital", and LUMO "Lowest Unoccupied Molecular Orbital". The 3d structure, HOMO and LUMO of MAB are showed in Figure 4. Generally, the value HOMO elucidates the ability of donating electrons of MAB molecule. EHOMO with high value imply that the MAB molecules have a good affinity to donate electrons to an empty orbital of the mild steel surface, whereas the value of LUMO infer to the ability of accepting electrons from mild steel surface. In general, the LUMO with lower value implies that the MAB molecules have the ability to accept electrons from the surface of mild steel coupon through back-donation [50, 51].

Hardness and softness are also significant parameters deal with the stability of the inhibitor molecule and reactivity [52].

The hardness with high value and softness with low value infer to a excellent inhibition efficiency [53,54]. Table 1 display that the value ΔE for MAB (7.264 eV) indicate that the MAB is an excellent corrosion inhibitor. The values of ΔE , η , σ and ΔN (fraction of electrons transferred) for MAB are in support of experimental results. The values of EHOMO and ELUMO were -11.628 eV and -4.364 eV respectively, which is agree with the experimental results.


The Mulliken charges were important to figured the adsorption centers of corrosion inhibitor molecules. The atom with high negative charge, has the ability to be adsorbed on the surface of mild steel. From Table 2, the MAB, molecule have the higher negative charges on O8, O9, N12 and O13, which implies that these atoms have the abilities to coordinate with the unoccupied d-orbital of iron atoms on the surface of mild steel.

Table 1. DFT quantum parameters for MAB molecule.


Inhibitor	EHOMO (eV)	ELUMO (eV)	ΔE	I	A	σ	χ	η	ΔN
MAB	-11.62	-4.36	-7.26	11.62	4.36	3.632	7.996	0.275	2.539

Table 2. Mulliken Charges of MAB atoms


Atoms	Charges	Atoms	Charges	Atoms	Charges	Atoms	Charges	Atoms	Charges
C(1)	0.3580	C(6)	-0.1614	C(11)	-0.1551	C(16)	0.0234	C(21)	-0.1481
C(2)	-0.1526	C(7)	-0.0583	O(12)	-0.3394	C(17)	-0.1421	C(22)	0.1103
C(3)	0.1341	O(8)	-0.3600	N(13)	-0.3396	C(18)	-0.0836	O(23)	-0.1897
C(4)	-0.1593	O(9)	-0.3417	C(14)	0.3312	C(19)	-0.1575	O(24)	-0.2824
C(5)	-0.0739	C(10)	0.3171	C(15)	-0.2074	C(20)	-0.0233	C(25)	-0.1868

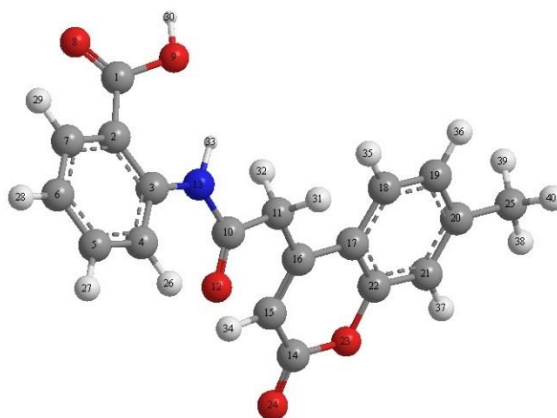

A

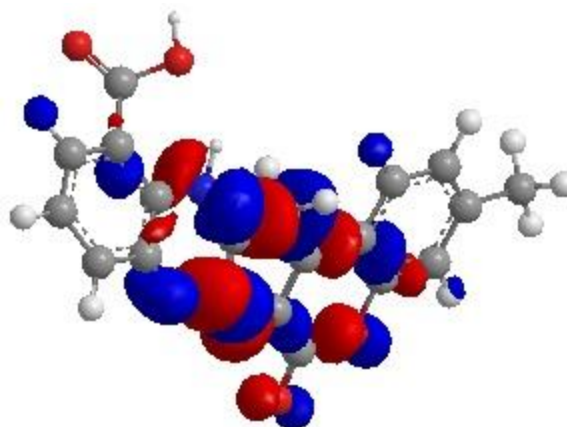

B

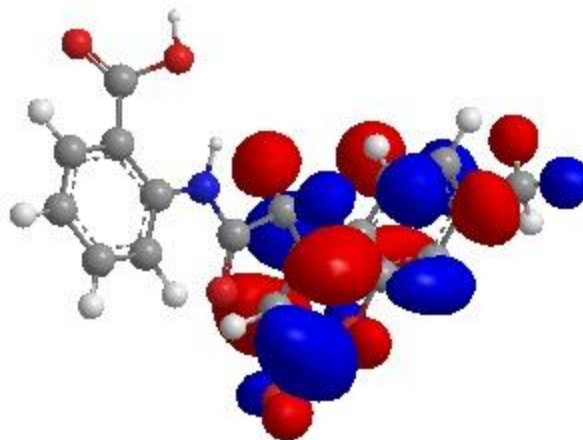

C

Figure 4. Optimized molecular structure (A), HOMO (B) and LUMO (D) of MAB molecule calculated by DFT.

4. Conclusions

1. New coumarin namely 2-(3-(7-methylcoumarin)acetamido)benzoic acid (MAB) was successfully synthesized and the chemical structure of MAB was confirmed by FT-IR, NMR spectroscopies and Elemental Analysis.
2. MAB acts as excellent corrosion inhibitor for mild steel in 1M hydrochloric acid solution.
3. Inhibition performance increased with increasing MAB concentration
4. Evaluation of adsorption isotherm parameters implies the formation of protective layer at the mild steel/corrosive environment interface.
5. Quantum chemical calculations were performed on MAB and various molecular structural factors were estimated and discussed.

Author Contributions: conceptualization, F. H.; methodology, K. A.; software, S. A.; validation, A.A.; formal analysis, A.A.; investigation, K.A.; resources, F.H.; data curation, S.A.; writing—original draft preparation, A.A.; writing—review and editing, L.S.

Funding: This research was funded by University of technology, grant number 2019.

Acknowledgments The authors gratefully acknowledge University of Technology/Iraq for providing the facilities for the work.

Conflicts of Interest: There are no conflicts to declare.

References

1. Adewuyi, A., Göpfert, A. & Wolf, T. Succinyl amide gemini surfactant from Adenopusbreviflorus seed oil: a potential corrosion inhibitor of mild steel in acidic medium. *Ind. Crops Prod.* 52, 439–449 (2014).
2. Anupama, K. K., Ramya, K. & Joseph, A. Electrochemical measurements and theoretical calculations on the inhibitive interaction of Plectranthusamboinicus leaf extract with mild steel in hydrochloric acid. *Measurement* 95, 297–305 (2017).
3. Uhlig, H. H. & Revie, R. W. *Corrosion and Corrosion Control*, Wiley, New York (1985).
4. Sigircik, G., Tüken, T. & Erbil, M. Assessment of the inhibition efficiency of 3,4-diaminobenzonitrile against the corrosion of steel. *Corros. Sci.* 102, 437–445 (2016).
5. Keles, H., Emir, D. M. & Keles, M. A comparative study of the corrosion inhibition of low carbon steel in HCl solution by an imine compound and its cobalt complex. *Corros. Sci.* 101, 19–31 (2015).
6. Zhang, D. et al. The inhibition performance of long chain alkyl-substituted benzimidazole derivatives for corrosion of mild steel in HCl. *Corros. Sci.* 102, 517–522 (2016).
7. Mobin, M., Aslam, R., Zehra, S. & Ahmad M. Bio-/Environment-Friendly Cationic Gemini Surfactant as Novel Corrosion Inhibitor for Mild Steel in 1M HCl Solution. *J. Surf. Det.* 20, 57–74(1).
8. Mobin, M., Zehra, S. & Aslam, R. L-Phenylalanine methyl ester hydrochloride as a green corrosion inhibitor for mild steel in hydrochloric acid solution and the effect of surfactant additive. *RSC Adv.* 6, 5890–5902 (2016).
9. Kicir, N., Tansug, G., Erbil, M. & Tuken, T. Investigation of ammonium (2,4-dimethylphenyl)-dithiocarbamate as a new, effective corrosion inhibitor for mild steel. *Corros. Sci.* 105, 88–99 (2016).
10. Mourya, P., Singh, P., Tewari, A. K., Rastogi, R. B. & Singh, M. M. Relationship between structure and inhibition behavior of quinolinium salts for mild steel corrosion: Experimental and theoretical approach. *Corros. Sci.* 95, 71–87 (2015).
11. Banerjee, S., Srivastava, V. & Singh, M. M. Chemically modified natural polysaccharide as green corrosion inhibitor for mild steel in acidic medium. *Corros. Sci.* 59, 35–41 (2012).

12. Morad, M. S. Inhibition of iron corrosion in acid solutions by Cefatrexyl: Behaviour near and at the corrosion potential. *Corros. Sci.* 50, 436–448 (2008).
13. Abiola, O. K. & James, A. O. The Effects of Aloe Vera Extract on Corrosion and Kinetics of Corrosion Process of Zinc in HCl Solution. *Corros. Sci.* 52, 661–664 (2010).
14. Junaedi, S; Kadhum, A; Al-Amiery, A; Mohamad, A; Takriff, M. Synthesis and characterization of novel corrosion inhibitor derived from oleic acid: 2-Amino-5-Oleyl-1,3,4-Thiadiazol (AOT). *Int J Electrochem Sci.* 2012, 7, 3543–3554.
15. Al-Amiery, A.A.; Kadhum, A.A.H.; Mohamad, A.B.; Junaedi, S. A Novel Hydrazinecarbothioamide as a Potential Corrosion Inhibitor for Mild Steel in HCl. *Materials* 2013, 6, 1420–1431.
16. Al-Amiery, A; Kadhum, A; Mohamad, A; Musa, A; Li, C. Electrochemical study on newly synthesized chlorocurcumin as an inhibitor for mild steel corrosion in hydrochloric acid. *Materials.* 2013, 6, 5466–5477
17. Al-Amiery, A. Kadhum, A. Mohamad, A. Musa, C. Li, Electrochemical study on newly synthesized chlorocurcumin as an inhibitor for mild steel corrosion in hydrochloric acid, *Materials*, vol. 6, 5466–5547, 2013.
18. Kadhum, A.A.H.; Mohamad, A.B.; Hammed, L.A.; Al-Amiery, A.A.; San, N.H.; Musa, A.Y. Inhibition of Mild Steel Corrosion in Hydrochloric Acid Solution by New Coumarin. *Materials* 2014, 7, 4335–4348.
19. Al-Amiery, A.A.; Kadhum, A.A.H.; Kadhim, A.; Mohamad, A.B.; How, C.K.; Junaedi, S. Inhibition of Mild Steel Corrosion in Sulfuric Acid Solution by New Schiff Base. *Materials* 2014, 7, 787–804.
20. Al-Amiery, A.A.; Kadhum, A.A.H.; Alobaidy, A.H.M.; Mohamad, A.B.; Hoon, P.S. Novel Corrosion Inhibitor for Mild Steel in HCl. *Materials* 2014, 7, 662–672.
21. Mohamad, A; Kadhum, A; Al-Amiery, A; Ying, L; Musa, A. Synergistic of a coumarin derivative with potassium iodide on the corrosion inhibition of aluminum alloy in 1.0M H₂SO₄. *Met Mater Int.* 2014, 20, 459–467.
22. Obayes R, Al-Amiery A, Alwan G, Alobaidy A, Al-Amiery A, Kadhum A, Mohamad A (2014) Quantum chemical assessment of benzimidazole derivatives as corrosion Inhibitors. *Chem Cent J* 8(21):1–8
23. A.A. Al-Amiery, Y.K. Al-Majedy, A.A.H. Kadhum and A.B. Mohamad, "New Coumarin Derivative as an Eco-Friendly Inhibitor of Corrosion of Mild Steel in Acid Medium", *Molecules*, 20, 366–383, 2015.
24. Yousif, E; Win, Y; Al-Hamadani, A; Al-Amiery, A; Kadhum, A; Mohamad, A. Furosemi as an environmental-friendly inhibitor of corrosion of zinc metal in acid medium experimental and theoretical studies. *Int J Electrochem Sci.* 2015, 10, 1708–1718.
25. Rubaye, A; Abdulwahid, A; Al-Baghdadi, S; Al-Amiery, A; Kadhum, A; Mohamad, A. Cheery sticks plant extract as a green corrosion inhibitor complemented with LC-EIS/ MS spectroscopy. *Int J Electrochem Sci.* 2015, 10, 8200–8209.
26. Al-Obaidy, A; Kadhum, A; Al-Baghdadi, S; Al-Amiery, A; Kadhum, A; Yousif, E. Eco-friendly corrosion inhibitor: experimental studies on the corrosion inhibition performance of creatinine for mild steel in HCl complemented with quantum chemical calculations. *Int J Electrochem Sci.* 2015, 10, 3961–12972.
27. Al-Baghdadi, S. B.; Noori, F. T. M.; Ahmed, W. K.; Al-Amiery, A. A. Thiadiazole as a Potential Corrosion Inhibitor for Mild Steel in 1 M HCl. *J. Adv. Electrochem.* 2016, 2, 67–69.
28. A. A. Al-Amiery, F. A. B. Kassim, A. A. H. Kadhum, and A. B. Mohamad, "Synthesis and characterization of a novel eco-friendly corrosion inhibition for mild steel in 1 M hydrochloric acid," *Scientific reports*, vol. 6, 2016.
29. Kadhim, A; Al-Okbi, A.K; Jamil, D. M; Qussay A; Al-Amiery A. A; Gaaz TS. Experimental and theoretical studies of benzoxazines corrosion inhibitors. *Results Phys.* 2017, 7, 4013–4019.

30. Obayes R, Al-Amiery A, Alwan G, Abdullah T, Kadhum A, Mohamad A (2017) Sulphonamides as corrosion inhibitor: experimental and DFT studies. *J Mol Struct* 1138:27–34.
31. Al-Baghdadi SB, Hashim FG, Salam AQ, Abed TK, Gaaz TS, Al-Amiery AA, Kadhum AH, Reda KS, Ahmed WK (2018) Synthesis and corrosion inhibition application of NATN on mild steel surface in acidic media complemented with DFT studies. *Results Phys* 8:1178–1184
32. Habeeb HJ, Luaibi HM, Dakhil RM, Kadhum AH, Al-Amiery AA, Gaaz TS (2018) Development of new corrosion inhibitor tested on mild steel supported by electrochemical study. *Results Phys* 8:1260–1267.
33. K. F. Al-Azawi, I. M. Mohammed, S. B. Al-Baghdadi, T. A. Salman, H. A. Issa, A. A. Al-Amiery, T.S. Gaaz and A. A. H. Kadhum, "Experimental and quantum chemical simulations on the corrosion inhibition of mild steel by 3-((5-(3,5-dinitrophenyl)-1,3,4-thiadiazol-2-yl)imino)indolin-2-one", *Results Phys.*, 9, 278–283, 2018.
34. Jamil, D. M; Al-Okbi, A. K; Al-Baghdadi, S. B; Al-Amiery, A. A; Kadhim, A; Gaaz, T. S. Experimental and theoretical studies of Schiff bases as corrosion inhibitors. *Chem Cent J*. 2018, 12, 1-7.
35. Ahmed, M; Al-Amiery, A; Al-Majedy, Y; Kadhum, A; Mohamad, A; Gaaz, T. Synthesis and characterization of a novel organic corrosion inhibitor for mild steel in 1 M hydrochloric acid. *Results Phys*. 2018, 8, 728–33
36. Salman, T. Zinad, D. Jaber, S. Al-Ghezi, M. Mahal, A. Takrif, M. Al-Amiery, A. Effect of 1,3,4-Thiadiazole Scaffold on the Corrosion Inhibition of Mild Steel in Acidic Medium: An Experimental and Computational Study. *Journal of Bio- and Tribo-Corrosion* (2019) 5:48, 1-11.
37. Salman, T. A., Al-Azawi, K. F., Mohammed, I. M., Al-Baghdadi, S. B., Al-Amiery A. A., Gaaze, T. S., Kadhum, A. H. "Experimental studies on inhibition of mild steel corrosion by novel synthesized inhibitor complemented with quantum chemical calculations", *Results Phys*, 2018; 10, 291-296.
38. Becke, A. D. Density-Functional Thermochemistry. III. The Role of Exact Exchange. *J. Chem. Phys.* 1993, 98, 5648–5652.
39. Becke, A. D. Density-Functional Exchange-energy Approximation with correct Asymptotic Behaviour. *Phys. Rev. A* 1988, 38, 3098–3100.
40. Lee, C.; Yang, W.; Parr, R. G. Development of the ColleSalvetti Correlation-energy Formula into a Functional of the Electron Density. *Phys. Rev. B* 1988, 37, 785–789.
41. Frisch, M. J.; et al. Gaussian 03, revision E.01; Gaussian Inc.: Wallingford, CT, 2007.
42. Martinez, S. Inhibitory Mechanism of Mimosa Tannin using Molecular Modeling and Substitutional Adsorption Isotherms. *Mater. Chem. Phys.* 2003, 77, 97–102.
43. Olasunkanmi, L. O.; Obot, I. B.; Kabanda, M. M.; Ebenso, E. E. Some Quinoxalin-6-yl Derivatives as Corrosion Inhibitors for Mild Steel in Hydrochloric Acid: Experimental and Theoretical Studies. *J. Phys. Chem. C* 2015, 119, 16004–16019.
44. Pearson, R. G. Absolute Electronegativity and Hardness: Application to Inorganic Chemistry. *Inorg. Chem.* 1988, 27, 734–740.
45. Singh, A.; Ansari, K. R.; Haque, J.; Dohare, P.; Lgaz, H.; Salghi, R.; Quraishi, M. A. Effect of electron donating functional groups on corrosion inhibition of mild steel in hydrochloric acid: Experimental and quantum chemical study. *J. Taiwan Inst. Chem. Eng.* 2018, 82, 233–251.
46. Verma, C.; Olasunkanmia, L. O.; Ebensoa, E. E.; Quraishi, M. A. Substituents effect on corrosion inhibition performance of organic compounds in aggressive ionic solutions: A review. *J. Mol. Liq.* 2018, 251, 100–118.
47. Singh, P.; Ebenso, E. E.; Olasunkanmi, L. O.; Obot, I. B.; Quraishi, M. A. Electrochemical, Theoretical, and Surface Morphological Studies of Corrosion Inhibition Effect of Green

- Naphthyridine Derivatives on Mild Steel in Hydrochloric Acid. *J. Phys. Chem. C* 2016, 120, 3408–3419.
48. Obot, I. B.; Madhankumar, A.; Umoren, S.; Gasem, Z. Surface protection of mild steel by benzimidazole derivatives: Electrochemical evaluation, weight loss study, surface analyses and theoretical approaches. *J. Adhes. Sci. Technol.* 2015, 29, 2130–2152
 49. Singh, P.; Singh, A.; Quraishi, M. A. Thiopyrimidine derivatives as new and effective corrosion inhibitors for mild steel in hydrochloric acid: Electrochemical and quantum chemical studies. *J. Taiwan Inst. Chem. Eng.* 2016, 60, 588–601.
 50. Ansari, K. R.; Quraishi, M. A. Experimental and Computational Studies of Naphthyridine Derivatives as Corrosion Inhibitor for N80 Steel in 15% Hydrochloric Acid. *Phys. E* 2015, 69, 322–331.
 51. Singh, P.; Makowska-Janusik, M.; Slovensky, P.; Quraishi, M. A. Nicotinonitriles as green corrosion inhibitors for mild steel in hydrochloric acid: Electrochemical, computational and surface morphological studies. *J. Mol. Liq.* 2016, 220, 71–81.
 52. Abd El-Lateef, H. M. Experimental and computational investigation on the corrosion inhibition characteristics of mild steel by some novel synthesized imines in hydrochloric acid solutions. *Corros. Sci.* 2015, 92, 104–117.
 53. Abd El-Lateef, H. M.; Abu-Dief, A. M.; Abdel-Rahman, L. H.; Sanudo, E. C.; Aliaga-Alcalde, N. Electrochemical and theoretical quantum approaches on the inhibition of C1018 carbon steel corrosion in acidic medium containing chloride using some newly synthesized phenolic Schiff bases compounds. *J. Electroanal. Chem.* 2015, 743, 120–133.
 54. Olasunkanmi, L. O.; Obot, I. B.; Ebenso, E. E. Adsorption and corrosion inhibition properties of N-{n-[1-R-5-(quinoxalin-6-yl)-4,5-dihydropyrazol-3 yl] phenyl} methane sulfon amides on mild steel in 1 M HCl: experimental and theoretical studies. *RSC Adv.* 2016, 6, 86782–86797.



© 2019 by the authors. Submitted for possible open access publication under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).