

# Development of Metal Nanoparticles Based Sensing Platform for Lead in Aqueous Samples <sup>†</sup>

Kalyan Vaid <sup>1,2,\*</sup>, Jasmeen Dhiman <sup>1</sup>, Nikita Sarawagi <sup>1</sup>, Suresh Kumar <sup>3</sup> and Vanish Kumar <sup>1,\*</sup>

<sup>1</sup> National Agri-Food Biotechnology Institute (NABI), S.A.S. Nagar, Punjab 140306, India; jasmeendhiman10@gmail.com (J.D.); nikitasarawagi6@gmail.com (N.S.)

<sup>2</sup> Centre for Nanoscience and Nanotechnology, Panjab University, Chandigarh-160014, India

<sup>3</sup> Department of Applied Sciences, UIET, Panjab University, Chandigarh-160014, India; sureshcsio@gmail.com

\* Correspondence: vanish@nabi.res.in or vanish.saini01@gmail.com (V.K.); vaidkalyan@gmail.com (K.V.)

<sup>†</sup> Presented at the 2nd International Online-Conference on Nanomaterials, 15–30 November 2020; Available online: <https://iocn2020.sciforum.net/>.

Published: 15 November 2020

**Abstract:** Lead (Pb) is one of the highly persistent and major toxic health hazard listed by various health organizations. A stable, specific, and simple sensor which can rapidly detect Pb in drinking water is required urgently. To this end, we have prepared stable and uniformly sized colloidal silver nanoparticles (AgNPs) using citric acid for the color-based sensing of Pb in water samples. The synthesized AgNPs are characterized by UV-vis spectroscopy, DLS-Zeta, and TEM to access their optical and morphological properties. The cit-AgNPs have shown a great affinity/selectivity towards Pb over Cd, Mn, Cr, Fe, Co, Pb, Hg, Zn, and Ti ions. Thus, based on the interaction of cit-AgNPs and Pb, a colorimetric sensor for selective, specific, and expeditious detection of Pb ions has been developed.

**Keywords:** heavy metals; sensing; lead; health; toxic; functionalization

## 1. Introduction

Metals have been an important component of the dietary intakes and play a major role in the metabolism and functioning of the human body [1]. Metals like zinc (Zn), copper (Cu), manganese (Mn) serve as essential minerals which are a part of biochemical pathways. Whereas, metals like mercury (Hg), lead (Pb), arsenic (As) are non-essential and can be lethal even if trace amounts are ingested by living organisms [2].

Pb has been one of the most devastating metals that can lead to several health risks. In humans, it can cause increase in blood pressure, neuropathy, fatigue, fertility disorders, and, in severe cases, encephalopathy or even death [3]. Considering such outcomes, WHO has enlisted Pb as one of the toxic metal pollutants [4]. The interference of such toxic heavy metals can be avoided if sensed timely.

Nanomaterials, especially nanoparticles (NPs) can serve as an indicator for the presence of heavy metals in the food and water samples [5]. The unique optical properties and characteristic surface plasmon resonance (SPR) signals of NPs provide an edge over using classical analytical techniques (such as atomic absorption, ICP-MS) for being feasible, rapid, and cost effective [6].

Among different NPs, silver nanoparticles (AgNPs) are one of the promising candidates suitable for the color based detection because of efficient electronic, physical, and chemical properties [7]. The colloidal solution of spherical AgNPs is of yellow-color exhibiting characteristic SPR signal at 350–400 nm [8]. In this study, the SPR properties of stable citrate-AgNPs (cit-AgNPs) were utilized for the specific qualitative sensing of Pb ions.

## 2. Materials


Silver nitrate ( $\text{AgNO}_3$ ) was purchased from MP Biomedicals (P) Ltd, India. Trisodium citrate (TSC), sodium borohydride ( $\text{NaBH}_4$ ), sodium ascorbate, lead chloride ( $\text{PbCl}_2$ ), zinc chloride ( $\text{ZnCl}_2$ ), ferrous chloride ( $\text{FeCl}_2$ ), chromium chloride ( $\text{CrCl}_2$ ), manganese chloride ( $\text{MnCl}_2$ ), cobalt chloride ( $\text{CoCl}_2$ ), titanium oxide ( $\text{TiO}_2$ ), mercury chloride ( $\text{HgCl}_2$ ), and cadmium chloride ( $\text{CdCl}_2$ ) were purchased from Sigma-Aldrich, USA. All the purchased chemicals were of analytical grade. All the aqueous solutions were prepared using Milli-Q (MQ) water having 18  $\text{M}\Omega\cdot\text{cm}$  resistivity.

## 3. Method


The citrate-AgNPs were prepared by chemical reduction method [9]. Briefly, 10 mM  $\text{AgNO}_3$  was dropwise added to ice-cold solution containing 1 mM  $\text{NaBH}_4$  and 0.30 mM TSC. The solution was stirred continuously till it turned yellow. The synthesized nanoparticles were washed and re-dispersed in Milli-Q (MQ) water for further use.

## 4. Results and Discussion


The synthesis of cit-AgNPs was completed when colloidal solution turned into yellow (Figure 1). The synthesis of cit-AgNPs was further confirmed by the appearance of characteristic SPR signal for AgNPs at 398 nm [8] (Figure 1). The cit-AgNPs particles were stable and exhibited -24 eV zeta potential due the presence of negatively charged citrate group as the capping agent (Figure 2). The TEM imaging revealed the uniform distribution of cit-AgNPs with 20 nm average size (Figure 3).

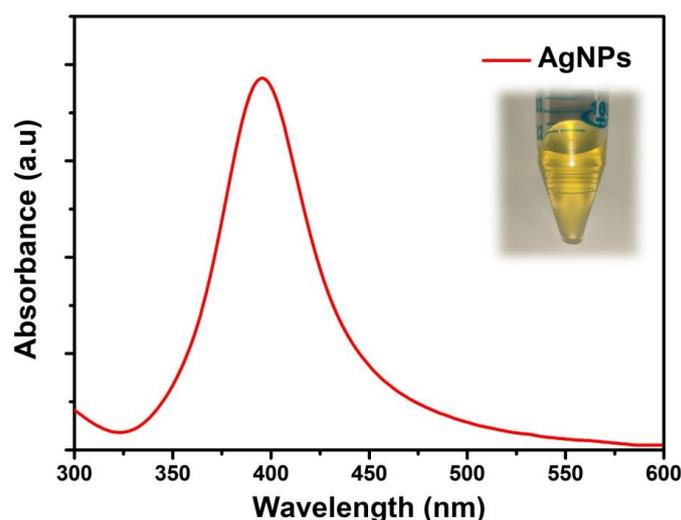

**Figure 1.** The AgNPs synthesized by chemical reduction (inset). The characteristic SPR signal (398 nm) of citrate-AgNPs as obtained in UV-Vis.

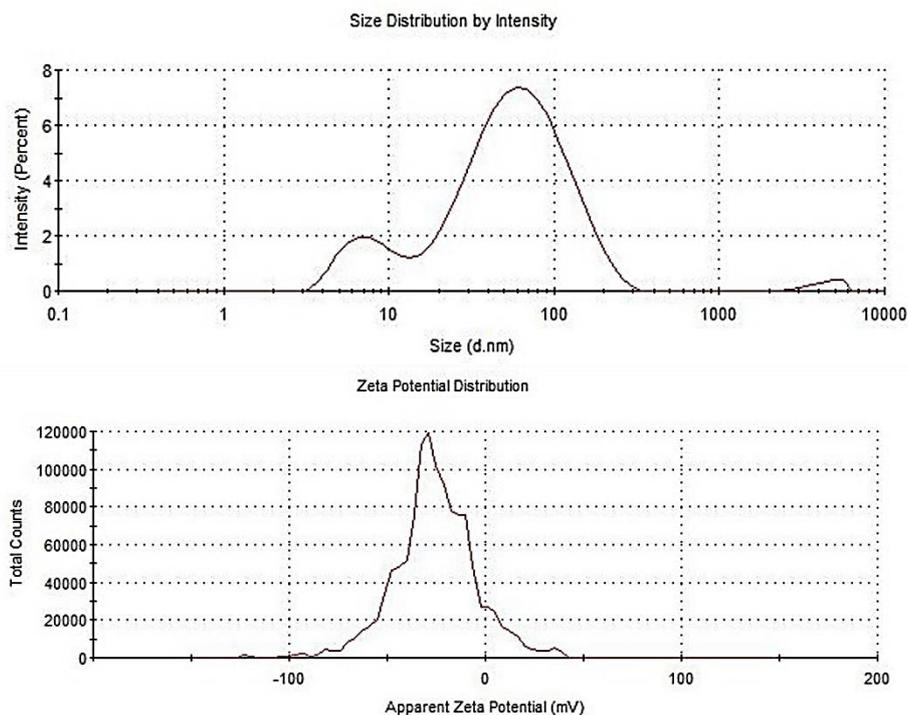


**Figure 2.** Size and zeta potential of cit-AgNPs as measured using dynamic light scattering (DLS).

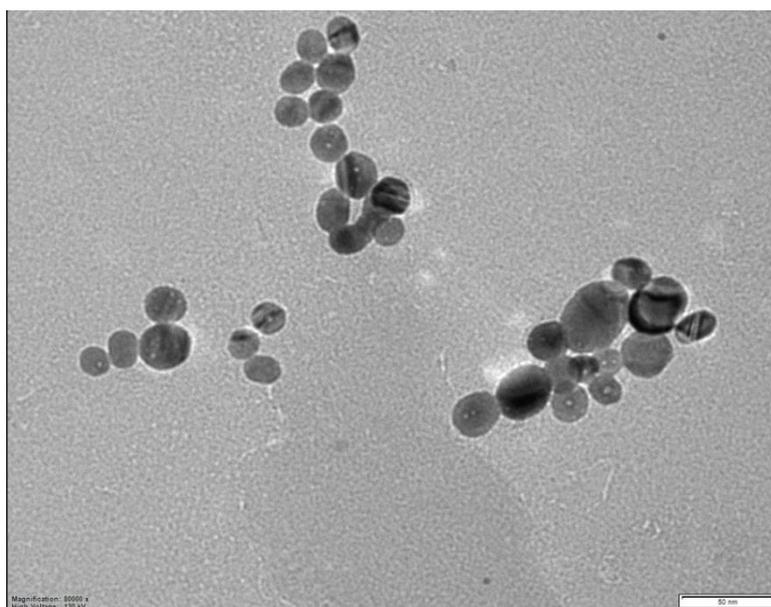


**Figure 3.** The TEM image for the citrate-AgNPs.

The interaction of different metal ions (10 ppm each) with cit-AgNPs was performed. The equal volume of metal salt solution was individually mixed with AgNPs solution. Out of tested metal ions (e.g., Cd, Mn, Cr, Fe, Co, Pb, Hg, Zn, and Ti), only Pb ions were capable of turning the cit-AgNPs solution from yellow to colorless (Figure 4). The specific sensing of Pb was also performed spectroscopically by UV-vis spectroscopy. The solution containing Pb loses its stability and aggregates the AgNPs and correspondingly, there is a clear change observed in the UV-Vis spectrum (Figure 5).

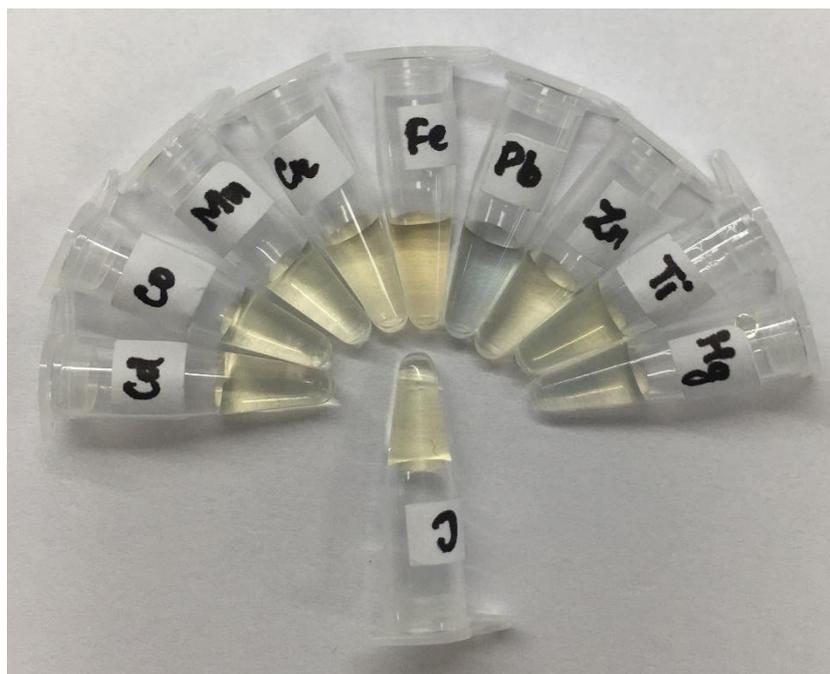

**Figure 4.** The color of colloidal cit-AgNPs in presence of different metals as compared to cit-AgNPs as control (C).

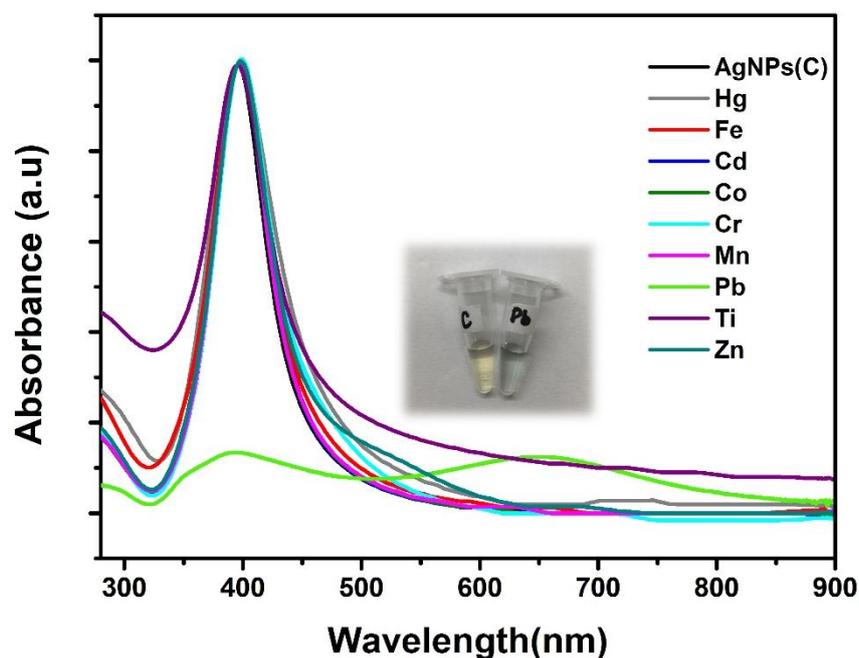

**Figure 5.** The UV-vis spectra for cit-AgNPs in the presence of different metal ions. Difference in the color of cit-AgNPs in the presence of Pb (inset).

## 5. Conclusions

Lead (Pb) ions have been listed as one of the most toxic pollutants for the environment. Herein, we have prepared and used well characterized AgNPs for the colorimetric and spectroscopic sensing of Pb ions. The use of AgNPs helped in quick detection of Pb, which would be highly beneficial for point-of-care qualitative detection. The developed cit-AgNP displayed color change and shift in SPR signal after interaction with Pb. Notably, these NPs did not show any color change in presence of interfering heavy metals, e.g., Cd, Mn, Cr, Fe, Co, Hg, and Zn.

**Acknowledgments:** This research acknowledges the support from the Department of Science and Technology, New Delhi, India in the form of an INSPIRE Faculty Award (DST/INSPIRE/04/2017/002953) and from the Science and Engineering Research Board (SERB), Government of India under the Early Career Research (ECR) award (File No. ECR/2018/000748).

## References

1. Virk, R.K.; Shafique, M.; Vaid, K.; Verma, S.; Bansal, M.P.; Garg, M.L.; Mohanty, B.P. Tracing biodistribution of essential and toxic elements in rat liver through PIXE. *Nucl. Instrum. Methods Phys. Res. Sect. B Beam Interact. Mater. At.* **2020**.
2. Dai, X.; Wu, S.; Li, S. Progress on electrochemical sensors for the determination of heavy metal ions from contaminated water. *J. Chin. Adv. Mater. Soc.* **2018**, *6*, 91–111.
3. Kumar, A.; MMS, C.-P.; Chaturvedi, A.K.; Shabnam, A.A.; Subrahmanyam, G.; Mondal, R.; Gupta, D.K.; Malyan, S.K.; S Kumar, S.; A Khan, S. Lead Toxicity: Health Hazards, Influence on Food Chain, and Sustainable Remediation Approaches. *Int. J. Environ. Res. Public Health* **2020**, *17*, 2179.
4. Organization, W.H. *International Lead Poisoning Prevention Week 2019 Campaign Resource Package*; World Health Organization: Geneva, Switzerland, 2019.
5. Vaid, K.; Dhiman, J.; Sarawagi, N.; Kumar, V. Experimental and computational study on the selective interaction of functionalized gold nanoparticles with metal ions: Sensing prospects. *Langmuir* **2020**.
6. Hou, H.; Zeinu, K.M.; Gao, S.; Liu, B.; Yang, J.; Hu, J. Recent advances and perspective on design and synthesis of electrode materials for electrochemical sensing of heavy metals. *Energy Environ. Mater.* **2018**, *1*, 113–131.
7. Sang, S.; Li, D.; Zhang, H.; Sun, Y.; Jian, A.; Zhang, Q.; Zhang, W. Facile synthesis of AgNPs on reduced graphene oxide for highly sensitive simultaneous detection of heavy metal ions. *RSC Adv.* **2017**, *7*, 21618–21624.
8. Aadil, K.R.; Pandey, N.; Mussatto, S.I.; Jha, H. Green synthesis of silver nanoparticles using acacia lignin, their cytotoxicity, catalytic, metal ion sensing capability and antibacterial activity. *J. Environ. Chem. Eng.* **2019**, *7*, 103296.
9. Preciado-Flores, S.; Wheeler, D.A.; Tran, T.M.; Tanaka, Z.; Jiang, C.; Barboza-Flores, M.; Qian, F.; Li, Y.; Chen, B.; Zhang, J.Z. SERS spectroscopy and SERS imaging of *Shewanella oneidensis* using silver nanoparticles and nanowires. *Chem. Commun.* **2011**, *47*, 4129–4131.

**Publisher's Note:** MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



© 2020 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).